

STATE LIBRARY OF PENNSYLVANIA



3 0144 00400421 4

CLASS W34.2 BOOK EX 7

VOLUME

1924



PENNSYLVANIA
STATE LIBRARY




Digitized by the Internet Archive
in 2013

MILITARY EXPLOSIVES

PREPARED IN THE OFFICE OF
THE CHIEF OF ORDNANCE

August, 1919

Revised January, 1924



WASHINGTON
GOVERNMENT PRINTING OFFICE
1924

WAR DEPARTMENT
Document No. 947
Office of The Adjutant General

Revised January, 1924

WAR DEPARTMENT.

WASHINGTON, *February 12, 1924.*

The following publication, entitled "Military Explosives," is published for the information and guidance of all concerned.

[A. G. 062.1.]

BY ORDER OF THE SECRETARY OF WAR:

JOHN J. PERSHING,

General of the Armies,

Chief of Staff.

OFFICIAL:

ROBERT C. DAVIS,

Major General,

The Adjutant General.

III

211083

PREFACE TO FIRST EDITION.

This publication has been prepared by the Explosives Section, Ammunition Division, Ordnance Department, United States Army, for use of the Ordnance Department in the instruction of student officers.

A large portion of the original manuscript was prepared by Capt. John A. Marshall, Ordnance Department, but it has been considerably enlarged and revised by Lient. Col. C. G. Storm, Ordnance Department. Acknowledgment is also made of the assistance of Maj. J. Herbert Hunter, Ordnance Department; Capt. C. A. Tibbals, jr., Ordnance Department; and Lient. J. E. Woods, Ordnance Department, in connection with the preparation and revision of the text.

August, 1919.

PREFACE TO SECOND EDITION.

The revision of this publication has been necessitated by the exhaustion of the original edition and the continued demand for copies for instruction purposes.

In this revision certain obsolete material has been eliminated and some new material added, and methods of inspection and analysis have been brought up to date to agree with the present approved procedure of the Ordnance Department.

This revision has been prepared by the Explosives Section, Ammunition Division, Ordnance Department, with the assistance of Picatinny Arsenal.

JANUARY, 1924.

CONTENTS.

PART I. PROPELLANTS.

Page.

Introduction	7
--------------------	---

CHAPTER I.—MANUFACTURE OF SMOKELESS POWDER.

General	11
Manufacture	12
Purification of cotton	13
Picking of cotton	13
Drying of cotton	14
Nitrating	14
Du Pont mechanical dipper process	15
Centrifugal process	17
Pot process	18
Purification	22
Pulping	23
Poaching	24
Wringing	28
Dehydration	29
Mixing	32
Pressing	33
Graining and cutting	36
Solvent recovery	37
Drying	39
Air dry treatment	39
Water dry treatment	42
Alcohol dry treatment	43
Blending	44

CHAPTER II.—GRANULATION OF SMOKELESS POWDER.

General	47
Shape of granulation	47
Size of granulation	49
Effect of weight of charge	50
Effect of weight of projectile	51
Effect of solvent on shrinkage of powder	51
Effect of moisture and volatiles	52
Effect of methods of drying	52
Dry dimensions	55
Web	55
Perforation	55
Diameter	55
Needle wire	55
Pin circle	57
Slope of cone	57
Quick powder—Slow powder	57
Calculation of average dry web	58
Calculation of required dry dimensions	58
Calculation of per cent shrinkage	59

CHAPTER III.—STABILITY OF SMOKELESS POWDER.

	Page.
Stability tests.....	60
Causes of instability.....	61
Stabilizers.....	61
Reworked powder.....	62
Storage of smokeless powder.....	64

CHAPTER IV.—INSPECTION OF SMOKELESS POWDER.

Analysis of cellulose.....	67
Analysis of diphenylamine.....	68
Analysis of mixed acids.....	70
Analysis of alcohol.....	74
Analysis of ether.....	75
Du Pont nitrometer.....	75
Analysis of nitrocellulose.....	77
Analysis of smokeless powder.....	80

CHAPTER V.—COMPOUND PROPELLANTS.

Sporting ballistite and infallible powder.....	86
E. C. powder.....	87

CHAPTER VI.—BLACK POWDER.

General.....	88
Manufacture.....	89
Process.....	89
Finishing.....	90
Packing.....	91
Inspection.....	91
Use.....	91
Methods of analysis.....	92
Sampling.....	92
Moisture.....	92
Potassium nitrate.....	92
Sulphur.....	92
Charcoal.....	93
Ash.....	93
Specific gravity.....	93
Determination of granulation.....	94
Moisture and ash, free analysis.....	94
Determination of potassium.....	94
Chlorides, chlorates, and perchlorates.....	95
Storage.....	95

PART II. MILITARY HIGH EXPLOSIVES.

Introduction.....	97
-------------------	----

CHAPTER VII.—TRINITROTOLUENE (TNT).

General.....	98
Properties.....	98
Manufacture.....	100

	Page.
Purification -----	102
Crystallization from sulphuric acid -----	103
Crystallization from alcohol -----	103
Sulphite purification -----	103
Use -----	105
Inspection -----	105
Specifications -----	105
Analysis and testing -----	105
Solidification point -----	106
Ash -----	106
Insoluble matter -----	106
Moisture -----	106
Acidity -----	106
Nitrogen -----	107
Fineness -----	107
Storage -----	107

CHAPTER VIII.—AMMONIUM PICRATE (EXPLOSIVE D).

General -----	108
Properties -----	108
Manufacture -----	109
Reworking -----	109
Use -----	112
Inspection -----	112
Specifications -----	112
Analysis and testing -----	112
Ammoniacal nitrogen -----	112
Moisture -----	113
Insoluble material -----	113
Mineral matter (ash) -----	113
Free ammonia -----	113
Storage -----	113

CHAPTER IX.—PICRIC ACID.

General -----	115
Properties -----	115
Manufacture -----	116
Phenol process -----	117
Chlorbenzene process -----	117
Catalytic process -----	117
Use -----	117
Inspection -----	118
Specifications -----	118
Analysis and testing -----	118
Solidification point -----	118
Moisture -----	119
Sulphuric acid -----	119
Nitric acid -----	119
Ash -----	119
Insoluble material -----	119
Soluble lead -----	120
Storage -----	120

CHAPTER X.—NITROSTARCH EXPLOSIVES.

	Page.
General nature.....	121
Reasons for adoption.....	121
Manufacture.....	121
Chemical and physical properties.....	122
Sensitiveness.....	123
Stability.....	124
Explosive properties.....	125
Use, military and commercial.....	126
Care in storage and handling.....	126
Inspection.....	127
Specifications.....	127
Methods of analysis.....	127
Moisture.....	127
Ether extract.....	127
Water extract.....	128
Sodium bicarbonate.....	128
Ammonium nitrate.....	128
Sodium nitrate.....	128
Charcoal.....	128
Nitrostarch.....	129

CHAPTER XI.—TETRYL.

Manufacture.....	130
Chemical and physical properties.....	130
Stability and sensitiveness.....	131
Explosive properties.....	131
Use, military and commercial.....	131
Precautions in handling and storage.....	132
Inspection.....	132
Specifications.....	132
Methods of testing.....	132
Melting point.....	132
Insoluble matter.....	133
Acidity.....	133
Moisture and volatiles.....	133
Sand test.....	134

CHAPTER XII.—TETRANITROANILINE (TNA).

Manufacture.....	136
Chemical properties.....	136
Toxic properties.....	137
Sensitiveness to heat, shock, and detonation.....	137
Explosive properties.....	138
Use.....	138
Precaution in handling and storage.....	139
Inspection.....	139
Nitrogen content.....	139
Melting point.....	139
Insoluble in acetone.....	139
Moisture.....	139
Acidity.....	139

CHAPTER XIII.—MERCURY FULMINATE.

	Page.
Manufacture.....	140
Chemical and physical properties.....	141
Impurities.....	141
Action on metals.....	142
Stability and sensitiveness.....	142
Explosive properties.....	143
Use.....	143
Precaution in handling and storage.....	144
Inspection.....	144
Specifications.....	144
Methods of analysis.....	144
Screen test.....	144
Acidity.....	145
Insoluble matter.....	145
Free mercury.....	145
Chlorides.....	145
Mercury fulminate content.....	146
Sand test.....	146

CHAPTER XIV.—AMATOL.

General.....	148
Properties.....	148
Manufacture or method of mixing.....	148
Methods of analysis.....	148
Raw materials.....	148
Sampling.....	149
Moisture.....	149
TNT.....	149
Ammonium nitrate.....	149

LIST OF ILLUSTRATIONS.

Plate No.	Page.
1. Du Pont mechanical dipper process, nitrating floor, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	15
2. Du Pont mechanical dipper process, wringing centrifugal floor, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	16
3. Du Pont mechanical dipper process, immersing basin and exit flume floor, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	17
4. Exterior of boiling tub unit, Old Hickory Smokeless Powder Plant, Nashville, Tenn.-----	18
5. Boiling tubs for purification of nitrocellulose before pulping, Smoke- less Powder Factory, Picatinny Arsenal, N. J.-----	20
6. General assembly of apparatus for pulping nitrocellulose showing concentrating sieve, Jordan engine, and feed tank, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	21
7. Detail of pulping equipment showing Jordan engine, Smokeless Pow- der Factory, Picatinny Arsenal, N. J.-----	23
8. Miller-Duplex type beater, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	24
9. Interior of poaching house, Old Hickory Smokeless Powder Plant, Nashville, Tenn.-----	25
10. Poaching tubs for purification of pulped nitrocellulose, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	26
11. Schematic sketch of Packer pulp screen.-----	28
12. Operating floor, dehydrating press house, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	29
13. Schematic sketch of dehydrating system.-----	30
14. Large dehydrating press, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	31
15. Mixer ready for discharge, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	33
16. Macaroni press, first stage, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	34
17. Macaroni press, final block, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	35
18. Graining press room, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	36
19. Charging floor, can type, solvent recovery house, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	37
20. Can and discharge floor, can type, solvent recovery house, Smoke- less Powder Factory, Picatinny Arsenal, N. J.-----	38
21. Exterior of "continuous" process dry house, Old Hickory Smokeless Powder Plant, Nashville, Tenn.-----	39
22. Interior of "continuous" process dry house, Old Hickory Smokeless Powder Plant, Nashville, Tenn.-----	40

Plate No.	Page.
23. Cannon powder blender. Old Hickory Smokeless Powder Plant, Nashville, Tenn.-----	41
24. Cannon powder blender, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	42
25. Hoisting belt in blender, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	43
26. Box filling and weighing floor, cannon powder blender, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	44
27. Powder box testing house, Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	45
28. Powder die assembly used for cylindrical grains-----	53
29. Sketch showing webs of cylindrical smokeless powder grain-----	54
30. Sketch showing dimensions of cylindrical smokeless powder grains--	56
31. Die body, pin plate, plug, water jacket, water jacket head, and smokeless powder grain for 12-inch gun-----	57
32. Mill for reworking unstable powder. Smokeless Powder Factory, Picatinny Arsenal, N. J.-----	62
33. Solution kettle for recrystallization of ammonium picrate, Picatinny Arsenal, N. J.-----	110
34. Equipment for drying and screening recrystallized ammonium picrate, Picatinny Arsenal, N. J.-----	111
35. Apparatus for sand test-----	135

QUESTIONS ON THE TEXT OF "MILITARY EXPLOSIVES."

INTRODUCTION.

1. Differentiate between the terms "explosive" and "high explosive."
2. Define the terms "explosion" and "detonation."
3. Enumerate the three general divisions noted into which military explosives fall.
4. Define the term "propellant."
5. Give the characteristics of a propellant and of a high explosive. Distinguish between them and give an example of each.
6. What criteria are used in selecting or rejecting a new substance for use as an explosive?
7. Are high explosives ever used alone or in combination with other substances to constitute a propellant?
8. What is the function of a high explosive?
9. In general, what types of chemical reactions are involved in the decomposition of an explosive?

CHAPTER I.

1. Discuss briefly the historical development of nitrocotton.
2. Discuss the term "smokeless powder" from the physical and chemical standpoint.
3. Define the phrase "granulation of smokeless powder."
4. Discuss the various types of granulation of smokeless powder.
5. Classify the different processes involved in the manufacture of smokeless powder.
6. What is pyrocotton?
7. Differentiate between pyrocotton and smokeless powder.
8. What is the necessity of purifying raw cotton?
9. Describe the picking operation.
10. What would be the effect of nitrating cotton having a higher water content than that given by specifications—
 - (a) Upon the cotton?
 - (b) Upon the acid?
11. Describe the DuPont mechanical dipper process in detail.
12. What degree of nitration is attained in the ordinary manufacture of pyrocotton? Indicate the nearest empirical formula.

13. What considerations enter into the purification of pyro-cotton?
14. How are these processes classified? Describe each in detail.
15. Discuss the operation of the Jordan engine.
16. Define dehydration. What chemical principles are involved in this procedure?
17. Discuss the operation of dehydration in detail.
18. What is a stabilizer? Where, why, and how is it used?
19. Discuss the formation of the colloid, enumerating the several stages involved.
20. Indicate in a general manner, by diagram, the method used in forming a grain of powder from the finished colloid.
21. Define the term "solvent recovery." Describe two different methods of accomplishing this operation.
22. Discuss the air drying of powder.
23. Does all powder receive air-dry treatment?
24. What do you understand by the terms "water dry" and "alcohol dry"?
25. Describe the method of operation of a continuous drier.
26. What do you understand by blending of powder? Describe its principles and practice.

CHAPTER II.

1. Enumerate the phenomena occurring in sequence when a charge of smokeless powder is exploded in a gun.
2. What considerations govern the granulation of smokeless powder?
3. Enumerate and describe briefly the different shapes of granulation.
4. What considerations determine the size of a powder grain? Discuss each.
5. Discuss the relationship of the different methods of drying to ballistics and stability of smokeless powder.
6. What is meant by average web? Inner web? Outer web?
7. Should the green dimensions of powder correspond to the die dimensions? Discuss fully.
8. What considerations influence the calculation of web measurements?
9. What is the basis of calculation for all the dimensions of the dried powder grain?
10. Differentiate between single and multi-perforated grains, discussing the web dimensions in each case.
11. Describe the Walsh grain.
12. What advantages are claimed for the Walsh grain?

13. Give the formulas for determining "D" and "d" in single and multi-perforated grains.

14. Assuming that a lot of powder develops an excessive pressure in ballistic tests, what procedure should be followed in the calculation of die dimensions for a new lot of powder for use in the same type of gun?

15. Name the classes into which artillery is divided.

CHAPTER III.

1. Discuss stability of smokeless powder from the standpoint of storage.

2. Describe the stability tests that are applied to smokeless powder.

3. Mention some of the factors that may influence the stability of cellulose nitrate.

4. What substance is used as a stabilizer in smokeless powder? Discuss its action from the chemical standpoint.

5. What is meant by an indicator?

6. Why is it necessary to rework powder?

7. Describe the process of manufacture of reworked powder.

8. Discuss its points of similarity and difference as compared with the manufacture of straight smokeless powder.

9. What considerations govern the selection of a site for storage magazines?

10. How is smokeless powder stored?

11. Discuss the problems connected with fire protection in relation to the storage of smokeless powder.

12. What precautions would you observe in the hiring of labor for work around powder magazines?

13. Discuss the use of nonsparking tools.

CHAPTER IV.

1. What tests are made of the raw materials entering into the manufacture of smokeless powder?

2. Discuss in detail the tests made on any two raw materials.

3. Describe the method of making moisture and volatile determinations on smokeless powder.

4. Do you differentiate between moisture and volatiles and total volatiles?

5. What control tests are made during the manufacture of smokeless powder?

6. Enumerate the physical tests made upon smokeless powder.

7. Describe the method of making a determination of ether-alcohol insoluble material in nitrocellulose.

8. Describe the heat test at 65.5° C. on nitrocellulose.
9. Describe the 135° C. test.
10. Describe the method for making a determination of per cent nitrogen in nitrocellulose.
11. How would you make a determination of ash in smokeless powder?

CHAPTER V.

1. What is meant by the term "compound propellants"?
2. Describe the manufacture and uses of sporting ballistite and infallible powder.
3. Describe the method of making the fume test upon sporting ballistite.
4. Describe the manufacture and use of E. C. powder.
5. Discuss the inspection of E. C. powder.

CHAPTER VI.

1. Give a brief history of the development of black powder.
2. Mention the factors that have effected the change from black powder to smokeless powder as a propellant.
3. Discuss the present military uses of black powder.
4. Give the composition of black powder.
5. Briefly describe the method of manufacture of black powder.
6. Describe the method for determination of potassium nitrate.
7. Describe the method for determination of sulphur.
8. Describe the determination of specific gravity.
9. Give the necessary precautions for the storage and handling of black powder.

CHAPTER VII.

1. What is TNT?
2. Discuss its properties.
3. What grades of TNT are specified and how do they differ from each other?
4. What are the uses of each grade?
5. Outline the process of manufacture of TNT.
6. How may TNT be purified?
7. What criterion is used to determine purity during the manufacture of TNT? Describe the test involved.
8. How would you make a determination of ash in TNT?
9. Discuss the storage of TNT.
10. Discuss TNT poisoning.

CHAPTER VIII.

1. Discuss the properties of ammonium picrate.
2. Describe the manufacture of ammonium picrate.
3. Discuss the hygroscopicity of ammonium picrate as compared with other explosives.
4. For what purposes is the substance used?
5. Compare ammonium picrate with TNT as to sensitiveness.
6. What details of manufacture produce reddish crystals?
7. How may ammonium picrate be reworked?
8. Can you make a melting point determination of this substance?
9. Describe briefly the determination of ammoniacal nitrogen.
10. How is free ammonia determined quantitatively in ammonium picrate?

CHAPTER IX.

1. Discuss the uses of picric acid.
2. Discuss its advantages and disadvantages for use as a high explosive.
3. How may some of these disadvantages be overcome?
4. Describe the phenol process for the manufacture of picric acid.
5. Discuss briefly the chlorbenzene process of manufacture.
6. Describe the method of making a solidification point determination on picric acid.
7. Describe the method of making an ash determination on picric acid.
8. Why is the presence of soluble lead in picric acid objectionable?
9. Discuss briefly the storage of picric acid.

CHAPTER X.

1. Distinguish between "nitrostarch" and "nitrostarch explosive."
2. Give reasons for the adoption of nitrostarch explosives by the Ordnance Department.
3. What starch gives best results in the manufacture of nitrostarch?
4. Describe briefly the manufacture of nitrostarch.
5. Give reasons for the use of oil in nitrostarch explosives.
6. Compare sensitiveness with other military explosives.
7. What precautions are necessary in the storing and handling of nitrostarch and nitrostarch explosives?
8. Give the approximate compositions of Trojan explosive and Grenite.
9. Discuss the hygroscopicity of these two explosives.

CHAPTER XI.

1. Give chemical name of tetryl.
2. Give briefly method of manufacture.
3. What are the uses of tetryl?
4. Discuss the relative strength or power of tetryl as an explosive as compared with the other more common military explosives.
5. Discuss its relative sensitiveness.
6. Discuss briefly the procedure followed in making the sand test.
7. What precautions are necessary in the handling and storage of tetryl?

CHAPTER XII.

1. What is TNA?
2. Discuss briefly the method of manufacture.
3. Compare TNA with tetryl and TNT as to sensitiveness and explosive properties.
4. Discuss the uses of TNA.
5. Describe the method for the determination of acidity in TNA.
6. What precautions are necessary in the handling and storage of TNA?

CHAPTER XIII.

1. Describe in detail the manufacture of mercury fulminate.
2. Describe the appearance of mercury fulminate crystals.
3. What impurities must be avoided?
4. Discuss briefly the stability and sensitiveness of mercury fulminate.
5. Give reason for using potassium chlorate with mercury fulminate.
6. What precautions are necessary in the handling and storage of mercury fulminate?

CHAPTER XIV.

1. What is amatol?
2. For what reasons was it adopted as a military explosive?
3. What mixtures are authorized?
4. Discuss the manufacture of amatol.
5. What is the effect upon the product of impurities—
 - (a) In the TNT used?
 - (b) In the ammonium nitrate used?
6. Is amatol hygroscopic?
7. Discuss the action of amatol on metals.

PART I.—PROPELLANTS.

INTRODUCTION.

An *explosive* may be defined, in general, as being a gaseous, a liquid, or a solid substance, or mixture of substances, which, upon application of a blow to a small portion of its mass or by a rise in temperature, is converted in a small space of time into other substances more stable, which are mainly gases or vapors, but may include solids. The chemical changes thus produced develop a sudden rise in pressure in the surrounding medium, and the word "explosion" is applied as a general term to the different types of phenomena occurring in this sort of reactions. Coincident with this evolution of gas, a considerable amount of heat is evolved, which produces a flame. An explosion may therefore be defined as a reaction in which a large volume of gas is evolved very rapidly and which is accompanied by a report. A high explosive is one in which this change occurs within an exceedingly short space of time, and the phenomenon accompanying this decomposition is termed a "detonation." The term "detonation" is, therefore, applied to a very rapid explosion; it is not properly employed, however, when discussing the analogous reaction incident to the combustion of a slower burning explosive as smokeless powder. The general term "*explosive*," which finds universal acceptance, applies alike to high explosives, black powder, and smokeless powder. It will be seen, therefore, that the accepted distinction between the different classes of explosives is based primarily upon their relative speed of decomposition, and only those explosives are classified as *high explosives* in which this chemical change is considered practically instantaneous.

Berthelot (*Explosives and Their Power*—Trans: Hake & Macnab—John Murray, London) enumerates and distinguishes between eight different groups of explosive bodies which owe their transformation either to the application of some external circumstance, such as fire, shock, friction, or else to the aid of a secondary reagent or chemical agent which propagates within itself an explosive wave and finally accomplishes a general explosion. Of these eight groups the greater number of military explosives fall within the third, fourth, and eighth divisions:

(a) *Explosive inorganic compounds*.—Definite bodies, liquids or solids, as the azides.

(b) *Explosive organic compounds*.—Definite bodies, liquids or solids, in which classification occurs the nitrated derivatives of the carbohydrates, as nitrocellulose, nitrostarch, and the nitrated derivatives of the aromatic compounds as trinitrotoluene.

(c) Mixtures formed by oxidizable and oxidizing bodies, solid or liquid, neither of these being explosives separately, as, for instance, black powder, etc.

Marshall (Explosives, Blakistons & Co., 1917, vol. 1) defines an explosion thus: "When gas or vapor is released so suddenly as to cause a loud noise an explosion is said to take place, as, for instance, the explosion of a steam boiler or of a cylinder of compressed gas." The barrel of a gun may be considered, at the time of the explosion, as being a cylinder of compressed gas. The walls of the gun constitute the walls of the cylinder, the breech mechanism one end, and the projectile the other.

If an explosive were used which gave instantaneous detonation the force so generated would either burst the barrel of the gun or else (in the case of a reduced charge) would not impart sufficient velocity to the projectile to develop the maximum efficiency. This particular point illustrates the necessity of using a relatively slow burning explosive as the means of propelling the projectile from the muzzle of the gun; an explosive which may be designated as the propelling charge or propellant. The pressure in the powder chamber of the gun must be developed slowly at first, gradually increasing in intensity until the projectile, in the case of the ideal gun, is forced to the muzzle, at which place the maximum pressure of the charge is exerted. However, in actual practice the maximum compression in the gun is never developed at the muzzle, a condition which would cause bursting according to our present design, in which the maximum pressure is exerted just after the projectile starts moving from its original position; usually the maximum pressure occurs when the projectile is only 1 foot or so ahead of its original position. In this function of projecting a shot the high explosive as such finds no application. It may occur, however, as a constituent of a propellant, as, for example, nitroglycerin, a high explosive which is an ingredient of certain sporting powders, pistol powders, and in certain cannon powders such as cordite, ballistite, etc. The field of usefulness of the high explosive as a class is quite different and advantage is taken of its properties of detonation to use it within the shell or other bursting projectile so that at the proper time the shell will be disrupted through the detonation of the high explosive with which it was filled.

The present tendency is to draw a sharp distinction between two classes of explosive bodies in accordance with the use to which they

are put and also in accordance with the speed of reaction whereby combustion or decomposition takes place; for example:

First. Those substances or mixtures whose rate of combustion is such as to permit their use for propelling projectiles from guns are termed "propellants."

Second. Those substances whose rate of decomposition is so very high as to preclude their use as propellants, but which, on the other hand, bring about very powerful disruptive action, are known as detonating explosives, or more commonly, as *high explosives*.

The various substances used for high explosives are quite numerous, but at the present time one substance, with certain modifications and additions, is used as the base of the propelling charge. This substance is a colloid formed by the action of a solvent upon a nitrated cellulose with or without the addition of nitroglycerin, and in its final form is called smokeless powder.

The selection of these various substances is dependent upon their cheapness of manufacture and their safety in handling. In order that the suitability of substances for use in military explosives may be properly evaluated, it is also necessary that the following properties and measurements be determined:

First. The chemical equation involved in the change of the substance from the liquid or solid to the gaseous state.

Second. The thermo-chemical values as given in heats of formation of the different components.

Third. Their specific heats.

Fourth. Their densities.

Fifth. The relative pressure which may be developed by comparing equal parts of a new explosive and of one well known.

Sixth. The type and amount of energy required to initiate reaction.

Seventh. Rapidity of reaction.

Eighth. The relative power of the explosive.

CHAPTER I.

MANUFACTURE OF SMOKELESS POWDER.

General.—The first nitrocotton which was made was the result of an experiment performed in 1838, when Pérouze observed the action of nitric acid upon cotton. A few years later, in 1845, Schönbein realized the importance of this material as an explosive and developed it to such a point that he endeavored to sell the product to various governments. Early attempts at the use of this new explosive, however, especially in Austria-Hungary, were fraught with disaster, for factories were destroyed and guns were damaged as a result of unfamiliarity with the chemical and physical properties of this new substance.

The unfortunate experiences, however, of the Austrians did not deter the English chemists from developing the industry. Prominent among these men at this time was Sir Frederick Abel, who started a small factory for the manufacture of nitrocotton at Waltham Abbey. The industry received tremendous support, and the important progress which was made during the next few years was, in fact, responsible for the later developments of collodion-photography and for the artificial silk industry.

During this period the use of gun cotton as an explosive was restricted entirely to blasting purposes. In seeking for a new material which might be used in place of black powder, and which would not have the objectionable features of the old propellant, such as smoke, residue, etc., it occurred to Schultze that gun cotton would be a possible substitute for this purpose. Many different substances and compounds were experimented with, but the first ones to achieve any notable success were the Schultze and the E. C. powders. These won instant recognition as shotgun powders, but proved too quick for use in rifled arms.

About this time another important step in the development of *smokeless powder* was made by Vieille, a French chemist. He incorporated nitrocotton with a mixture of ether and alcohol, and rolled the resulting paste, a colloid, into thin sheets, which were cut into small squares and dried. Contemporaneous with this work, Nobel developed ballistite, a powder obtained by gelatinizing a low nitrated nitrocotton with nitroglycerin. Shortly after this, a modification of ballistite, known as cordite, was adopted as a *smokeless*

powder. This propellant consisted of a mixture of high nitrated gun cotton gelatinized by means of acetone. In this mixture nitroglycerin and vaseline were incorporated.

At the present time all nations use as a propellant either gelatinized nitrocotton alone or else gelatinized nitrocotton mixed with varying quantities of nitroglycerin.

The term "*smokeless powder*" when considered from the exact meaning of the words is a paradoxical misnomer, for the substance is not entirely smokeless and it is not a powder.

Smokeless powder may occur in the form of small flakes, strips, pellets, cylinders, or other different shapes, the cylinders varying in length from 1.45 millimeters for 8 mm. gun to 55 millimeters for a 16-inch gun. All these forms are spoken of as grains, each of which is termed the granulation of the sample of powder in question. The accepted form of granulation of *smokeless powder* used in this country is that of a cylinder in which one or more perforations extend longitudinally throughout the grain. In the smaller size grains of powder, as for instance for 8 mm., .30 caliber and 1 pounder weapons, there is only a single perforation. The larger sizes, however, have seven perforations. There is no intermediate number of perforations, the grain having either one or seven.

In addition to the cylindrical form of granulation, the so-called Walsh grain, or sliverless grain, has been devised to meet certain conditions incident to the firing of mortars. Instead of being a true cylinder the grain is scalloped on the outer surface. There are six of these indentations, and they are so placed that the apex of the reentrant angle occurs at a point exactly midway between the six outside perforations. This form of grain accomplishes the important function that it reduces the weight of the charge, for the reason that its combustion is practically complete. This is due to the fact that the burning surface is greater than that of the cylindrical grain of the same length and the same diameter. This greater burning surface gives an increased rate of burning, with the result that where formerly there was a relatively large amount of unconsumed powder left after the charge had been fired, with the use of this type of grain the slivers of unburned powder are practically eliminated. Slivers are small triangular prisms of powder remaining after the burning has progressed through the smallest dimension of the grain. The sliverless grain dries also quite as well, if not better, than the cylindrical grain and shows no tendency to split at the reentrant angles.

MANUFACTURE.

The different processes incident to the manufacture of *smokeless powder* may be summarized under the following heads:

First. Purification and mechanical preparation of the raw cotton. This includes the picking and drying processes.

Second. Nitration of the cotton. This is accomplished by treating the cotton with a mixture of nitric and sulphuric acid, thus producing a cellulose nitrate or "pyrocotton."

Third. The purification of the pyrocotton from all traces of free acids and lower nitrates.

Fourth. The mixing of the pyrocotton with ether-alcohol and pressing to form a colloid.

Fifth. The granulating of the powder by pressing the colloid through steel dies.

Sixth. The final processes of solvent recovery, drying, and blending.

The details of manufacture are as follows:

Purification of cotton.—The cotton used in the manufacture of smokeless powder consists mainly of two distinct grades, the one known as linters and the other as hull fibers, although other grades of cotton and even wood pulp are used. However, various mixtures of linters and fibers are generally employed. The charge of raw cotton is cooked in a digester for about six hours with a solution of approximately 2 per cent caustic soda. The digestion is carried out under a pressure of about 72 pounds per square inch, which corresponds to a temperature of 152° C. After removing the spent caustic liquors by washing, the cotton is treated with a solution of commercial bleaching powder of about $2\frac{1}{2}$ per cent strength. This bleaching is carried out at 36° C., and as short a time as is necessary to decolorize the fibers is employed. The excess bleach is destroyed by the addition of a small quantity of sulphuric acid. The charge is then washed free of bleaching agents and dried.

The object of the boiling with soda and the bleaching treatment is to reduce the content of vegetable oil, resinous material, and other extractible substances. It is very important that the alkaline treatment should not be excessive and that the cotton should not be overbleached, otherwise the contents of hydrocellulose and oxycellulose will be undesirably high, as indicated by the caustic potash test described in specifications for smokeless powder for cannon (Ordnance Department Specification No. 450) under "Cellulose."

If uniform nitration is to be obtained, it is essential that the cotton must be of a uniform low moisture content, of a uniform physical condition, and that it should be free from lumps or any extraneous material.

Picking of cotton.—To obtain this uniformity the cotton is put through a picking machine, of which there are various forms, e. g., the Cogswell Mill, the cyclone Superior, and the Davis & Furber picker. The last-mentioned machine is provided with a toothed

roller which engages the cotton as it is moved along the feeding table and carries it into such a position that it is caught and torn apart by rows of sharp hook-shaped teeth set along six evenly spaced elements of a skeleton cylinder revolving at the rate of 1,000 revolutions per minute. This operation reduces the cotton to a fluffy state in which it is caught and blown by air blast into a large flue leading into the drying room. At one portion of its journey through the flue the cotton passes through the C. O. B. machine, which comprises a system of W-shaped flues containing a set of baffles in the form of prongs which serve to fluff out the cotton and separate the fibers from the heavy dust. This dust settles to the bottom of the bends in the flues, whence it is removed.

From the C. O. B. machine the cotton is blown into the dry house.

Drying of cotton.—Two systems of drying are in use: One, the continuous drier in which the cotton is conveyed by a belt through a long chamber heated to about 100° C., the other by placing the cotton in a large chamber which is heated by hot-air blast. The former is a continuous operation and the cotton issuing from the drier is weighed directly into metal containers and transferred to the nitrating house. The entering cotton usually contains about 8 per cent moisture. The treatment reduces this to approximately 0.5 per cent.

The chamber system is the more expensive of the two and the least desirable from the standpoint of time. These chambers are of such a size as to hold approximately 2,500 pounds of cotton. After the chamber has been filled, it is closed tightly and the heat is gradually raised until the temperature reaches 105° C., where it is held for 24 hours. After a laboratory test of the cotton has shown less than 1 per cent of moisture, the dried cotton is weighed in lots of 32 pounds in closed fiber containers which are transferred to the nitrating house by means of a telpherage system.

Nitrating.—In the nitration of cellulose there are two reactions to be considered from the manufacturing standpoint. Although these reactions occur simultaneously, for the sake of clearness in description they are to be considered separately—first, the formation of the nitric acid ester of cellulose, and the subsequent removal of the water formed in the reaction by sulphuric acid.

There are three kinds of acid used in nitrating, namely, fortifying, fuming sulphuric, and spent acid. The spent acid is that which is recovered from the nitrators after nitration has been completed. This acid is built up or fortified by use of a fortifying acid, having a strength of approximately 50 to 55 per cent nitric and 50 to 45 per cent sulphuric. This acid supplies all of the nitric acid necessary for the new nitration and a portion of the sulphuric acid. The rest of the sulphuric acid is supplied by adding fuming acid of

104 per cent H_2SO_4 . The main function of the sulphuric acid is to combine with the water formed during the reaction, and in this manner to prevent the dilution of the nitric acid. At the present time the mixing of mixed nitrating acids is generally accomplished by agitation with iron paddles rather than by the use of compressed air.

Four different systems of nitration have been used in this country, viz: The Du Pont mechanical dipper process, the centrifugal process, the Thompson displacement system, and the pot process. The relative proportions of the nitric acid, sulphuric acid, and water vary

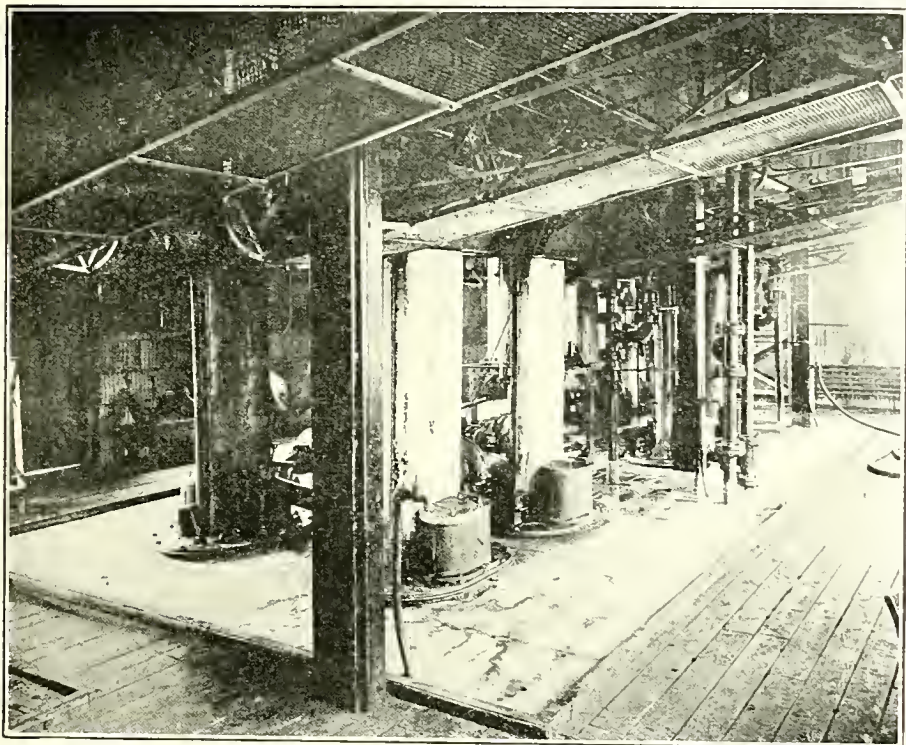


PLATE I.—DU PONT MECHANICAL DIPPER PROCESS, NITRATING FLOOR, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

not only with the different processes, but also with a change in weather conditions, more particularly of temperature. The sulphuric acid content is maintained very nearly constant, but the variation in nitric acid is nearly 1 per cent, and is largely accounted for by the fact that a certain amount of denitration of nitro cotton takes place during warm weather. Unless the nitric is increased to take care of this phenomenon, the resulting nitrocotton will be below specifications.

1. *Du Pont mechanical dipper process.*—The entire cycle of operation in this process is not more than 35 minutes. Under ordinary working conditions the fumes are negligible, whereas in all of the

other nitrating systems the fumes are always in evidence, so that from the standpoint of the health of the operatives the Du Pont system is much to be preferred, provided that the proper care is always exercised in the manipulation of the machinery.

A nitrating unit in this system consists of four iron pots so situated that they can all be handled from a center point. In each nitrator there are two vertical revolving paddles operated in opposite directions from each other, the motion being from without inward. These paddles consist of a series of horizontal arms so placed upon the post that when set in motion the cotton is quickly drawn beneath

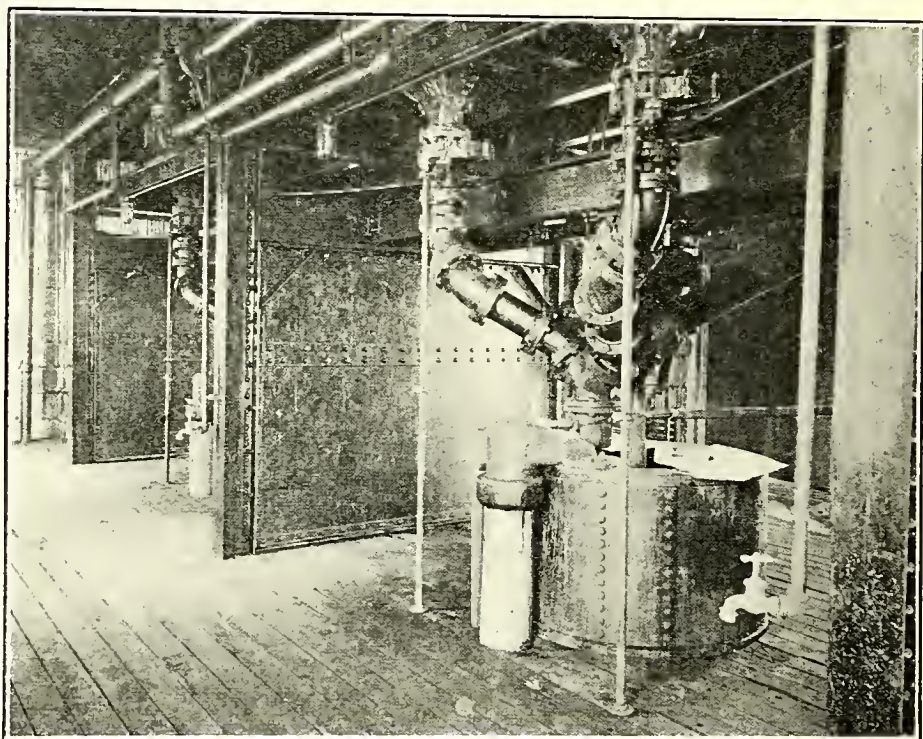


PLATE 2.—DU PONT MECHANICAL DIPPER PROCESS, WRINGING CENTRIFUGAL FLOOR, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

the surface of the acid. A charge of approximately 1,500 pounds of acid, having a temperature of 30° C., is used in each nitrator of which the following is a fair average composition: HNO_3 , 21 per cent; H_2SO_4 , 63 per cent; N_2O_4 , 0.5 per cent; H_2O 15.5 per cent.

When the acid has been run in, the paddles are set in motion and 32 pounds of cotton added. The speed of these paddles is approximately 60 revolutions per minute. Nitration is continued for 24 minutes, after which the bottom discharge pipe is then opened and the cotton and acid allowed to run down into a centrifugal wringer. This centrifugal wringer rotates slowly at first at about 300 revolution per minute until the whole charge is in the centrifuge. The

speed of the wringer is then increased to about 1,100 revolutions per minute and held at this rate for $3\frac{1}{2}$ minutes. The spent acid is run by gravity from the outer jacket of the wringer into catch tanks where small amounts of nitrocellulose settle out. The spent acid runs from these catch tanks to a blow case, and is either blown into mixing tanks, or any surplus spent acid set aside for denitration or other means of disposal.

The nitrated cotton obtained is forked through a bottom discharge of the centrifuge into an immersion basin below. As fast as the nitrated cotton falls into the basin it is submerged by a heavy stream

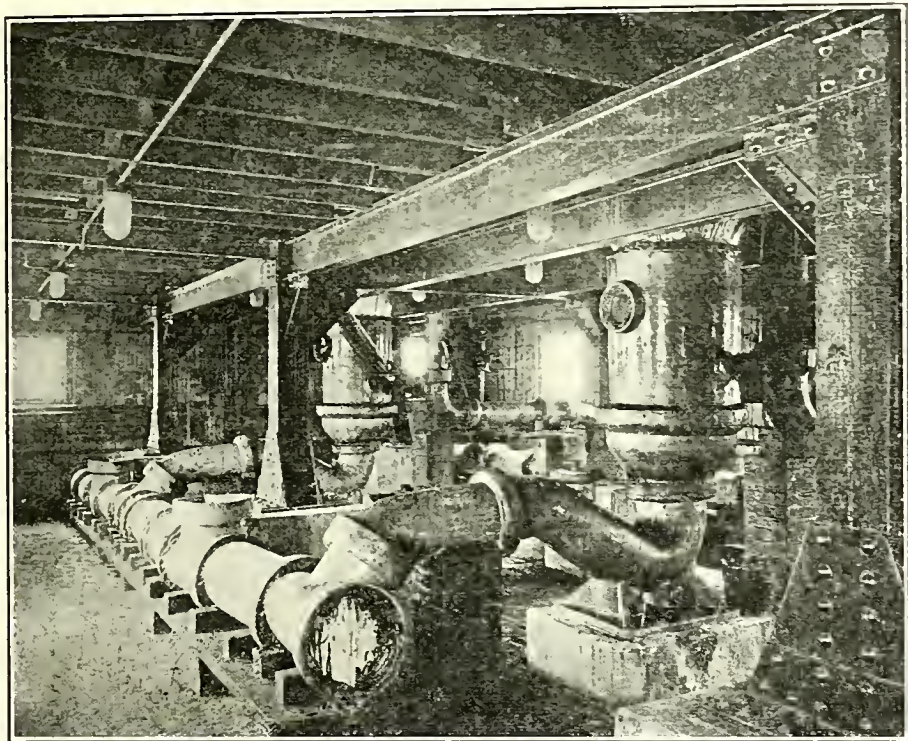


PLATE 3.—DU PONT MECHANICAL DIPPER PROCESS. IMMERSING BASIN AND EXIT FLUME FLOOR, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

of water distributed by fishtail or other form which combines the greatest dispersion of water with the maximum force for submersion.

The pyrocotton, as it is now called, is next transferred by means of pumps or by gravity to the boiling tub house.

2. *Centrifugal process*.—In this system the nitrating and the separation of the spent acid from the nitrated cotton are both carried on in a large nitrating centrifugal. The latter is filled with a definite amount of the mixed acid, usually 50 times the weight of the cotton charge, at a temperature of about 32° C., the weighed charge of cotton (usually 30 pounds) immersed rapidly by means of an iron fork

and allowed to stand for about 20 minutes, with occasional turning over by means of the fork. The drain cock is then opened and the spent acid separated by centrifuging, after which the charge is forked out and drowned, as in the mechanical dipper process.

3. *Pot process.*—In the pot process the nitration is best carried out in iron pots. These are filled with the mixed acid, the cotton immersed and allowed to digest for 20 to 30 minutes, when the entire contents are dumped into a centrifugal wringer. The pots are moved and dumped by means of a suitable two-wheeled truck conveyer. The pot process employs considerably less acid than the centrifugal

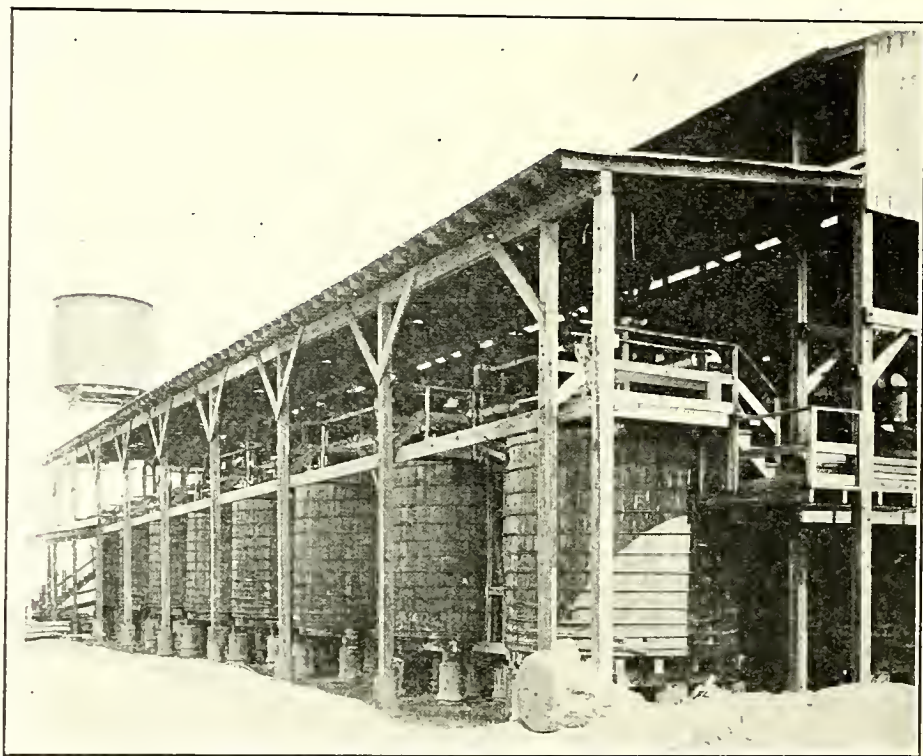


PLATE 4.—EXTERIOR OF BOILING TUB UNIT, OLD HICKORY SMOKELESS
POWDER PLANT, NASHVILLE, TENN.

process, about 35 parts of acid being sufficient to cover the cotton properly.

The charge of cotton used is generally about 4 pounds. Sometimes much smaller pots made of earthenware are used, holding a charge of only 2 pounds of cotton, several of these charges constituting a wringer charge. These small pots are usually emptied by hand.

The spent acid recovered from the centrifugals is transferred to storage tanks to be fortified, as has already been mentioned. Its average composition is approximately: HNO_3 , 18 per cent; H_2SO_4 , 65 per cent; N_2O_4 , 0.5 per cent; H_2O , 16.5 per cent.

The chemical reactions involved in the nitration are not understood definitely, for the reason that the exact molecular weight of cellulose is not known. The empirical formula of cellulose is assumed to be $(C_6H_{10}O_5)_x$, and is thus discussed by Marshall (Explosives, Arthur Marshall, Blakiston's, 1917, pp. 135-136) :

At first the simplest possible formula was assumed for cellulose, $C_6H_{10}O_5$, and guncotton of high nitrogen content and low solubility in ether-alcohol was supposed to be formed by the substitution of three NO_2 groups for hydrogen atoms, $C_6H_7O_5(NO_2)_3$, and was consequently called trinitro-cellulose. The less nitrated product soluble in ether-alcohol was similarly supposed to be the dinitro-cellulose $C_6H_8O_5(NO_2)_2$. Later workers obtaining evidence of intermediate stages of nitration proposed to increase the formula of cellulose; Eder doubled it, Vieille quadrupled it, and Mendeleeff octupled it, giving 48 atoms of carbon to each molecule, and hydrogen and oxygen in proportion. A nitro-cellulose having the composition of the above-mentioned trinitro-compound would contain 14.14 per cent nitrogen. Quite as much as this has never been found by the analysis of any product that has ever been obtained, but various investigators by nitrating with mixtures of nitric acid and phosphorus pentoxide, or with concentrated sulphuric and nitric acids and extracting the product with ether-alcohol have obtained percentages between 13.9 and 14.4. Lunge and Bebie found that with mixtures of sulphuric and nitric acids the highest percentage of nitrogen was attained, not with anhydrous acids, but with mixed acids containing 11 or 12 per cent of water: with a mixture in which the proportions $H_2SO_4:HNO_3:H_2O$ were 63.35:25.31:11.34 they produced a nitro cotton containing 13.92 per cent N, but this was not stable. After keeping in the wet state it was reanalyzed and found to contain then only 13.5 per cent N, and other nitro cottons nitrated almost as highly were found to decompose rapidly until the same composition was reached, even though the material was kept under water. This corresponds very closely with the formula $C_{24}H_{26}O_{20}(NO_2)_{11}$, endeka-nitro-cellulose. Hence the authors conclude that the molecule with 24 atoms of carbon fits the facts sufficiently well, but point out that this is only the lower limit of the possible size of the cellulose molecule, as to the real magnitude of which there is little or no evidence.

With the possible exception of this endeka-nitro-cellulose no definite stages of nitration can be recognized; nitro-celluloses with every percentage of nitrogen from 7 to 13.5 and more can be produced, and those of the same degree of nitration may be soluble to very different extents in ether-alcohol. To characterize a nitrocotton it is better to specify the percentage of nitrogen and the solubility rather than to state the number of NO_2 groups that it is supposed to contain in each molecule. The following table shows the percentage of nitrogen and the volume of gas evolved in the nitrometer by the different nitrocelluloses of the C_{24} series. The figures have been calculated, using the latest atomic weights.

Designation.	Formula.	c.c. NO per g.	Per cent N.
Dodeka-nitro-cellulose.....	$C_{24}H_{28}O_{20}(NO_2)_{12}$	225.6	14.14
Endeka-nitro-cellulose.....	$C_{24}H_{29}O_{20}(NO_2)_{11}$	215.0	13.48
Deka-nitro-cellulose.....	$C_{24}H_{30}O_{20}(NO_2)_{10}$	203.5	12.76
Ennea-nitro-cellulose.....	$C_{24}H_{31}O_{20}(NO_2)_{9}$	190.9	11.97
Okto-nitro-cellulose.....	$C_{24}H_{32}O_{20}(NO_2)_{8}$	177.3	11.12
Hepto-nitro-cellulose.....	$C_{24}H_{33}O_{20}(NO_2)_{7}$	162.4	10.18
Hexa-nitro-cellulose.....	$C_{24}H_{34}O_{20}(NO_2)_{6}$	146.0	9.15
Penta-nitro-cellulose.....	$C_{24}H_{35}O_{20}(NO_2)_{5}$	127.9	8.02
Tetra-nitro-cellulose.....	$C_{24}H_{36}O_{20}(NO_2)_{4}$	107.9	6.77

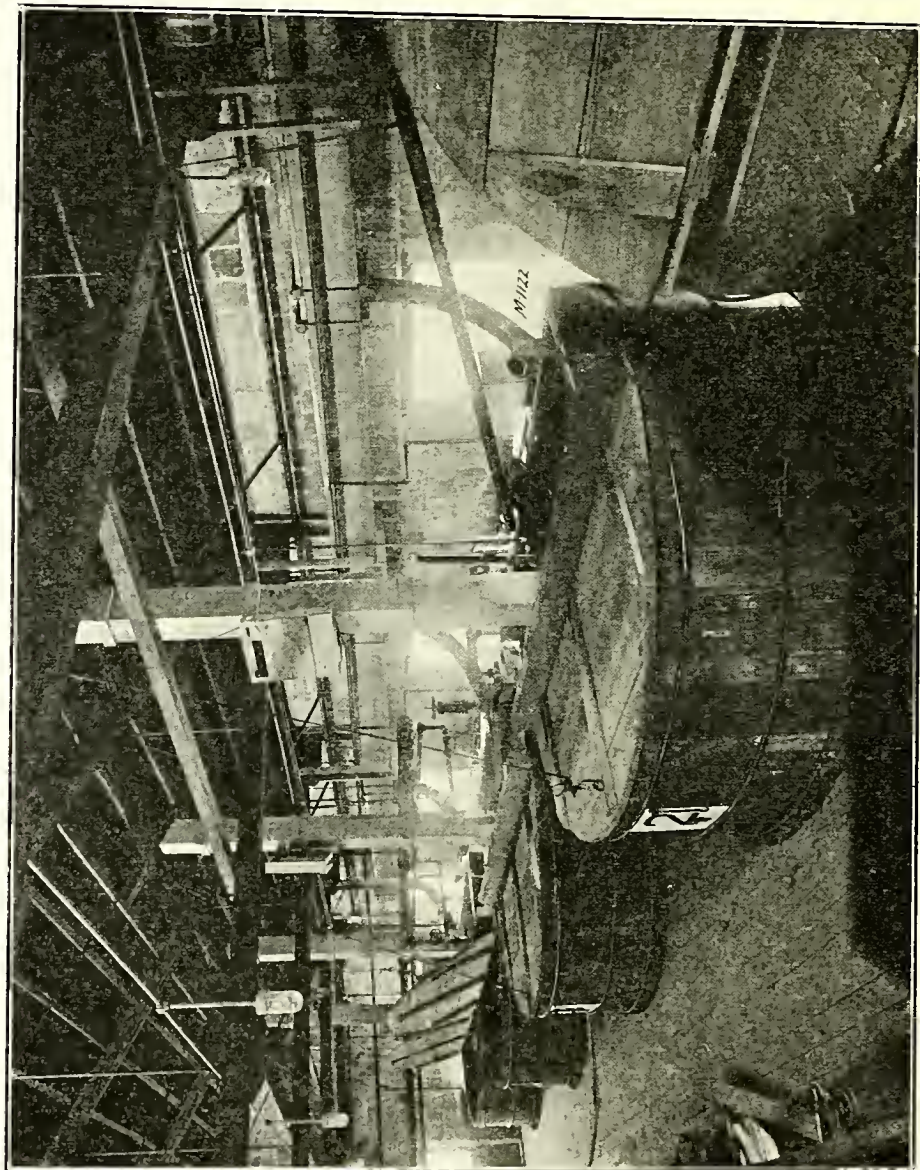


PLATE 5.—BOILING TUBS FOR PURIFICATION OF NITROCELLULOSE BEFORE PULPING, SMOKE-
LESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

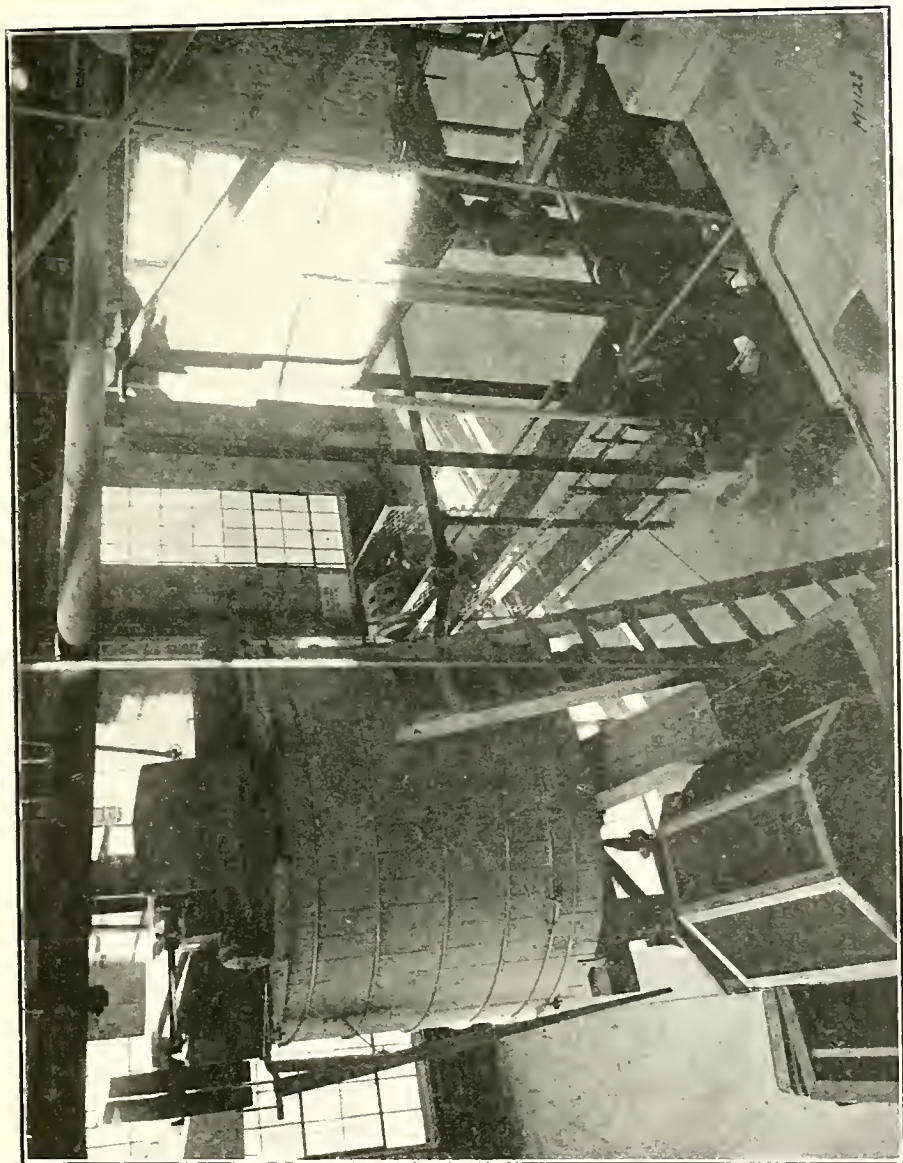


PLATE 6.—GENERAL ASSEMBLY OF APPARATUS FOR PULPING, NITROCELLULOSE, SHOWING
CONCENTRATING SIEVE, JORDAN ENGINE, AND FEED TANK, SMOKELESS POWDER FACTORY,
PICATINNY ARSENAL, N. J.

Escales (Die Explosivstoffe mit besondere berucksichtigung der Neuren Patente. Bearbeitet von, Dr. Richard Escales, Leipzig. von Veit. 1914) discusses the cellulose nitrate from a slightly different standpoint. as shown by the appended table.

Composition of cellulose (nitrated).

Parts nitrate.	Designation.	Formula.	e.e. NO per g.	Per cent N.
12	Dodeka-nitro-cellulose.....	$C_{24}H_{25}O_8(NO_3)_{12}$	226.27	14.14
11	Endeka-nitro-cellulose.....	$C_{24}H_{29}O_8(NO_3)_{11}$	215.17	13.47
10	Deka-nitro-cellulose.....	$C_{24}H_{30}O_{10}(NO_3)_{10}$	203.35	12.75
9	Ennea-nitro-cellulose.....	$C_{24}H_{31}O_{11}(NO_3)_9$	190.75	11.96
8	Okto-nitro-cellulose.....	$C_{24}H_{32}O_{12}(NO_3)_8$	177.19	11.11
7	Hepto-nitro-cellulose.....	$C_{24}H_{33}O_{13}(NO_3)_7$	162.36	10.18
6	Hexa-nitro-cellulose.....	$C_{24}H_{34}O_{14}(NO_3)_6$	145.96	9.15
5	Penta-nitro-cellulose.....	$C_{24}H_{35}O_{15}(NO_3)_5$	127.91	8.02
4	Tetra-nitro-cellulose.....	$C_{24}H_{36}O_{16}(NO_3)_4$	107.81	6.76

It should be definitely understood that nitrocellulose is not a true nitro body, but is a nitric acid ester, or nitrate of cellulose. Nitrates yield all their nitrogen as nitric oxide (NO) in the nitrometer; nitro bodies do not. Hence the term "nitrocellulose" is also a misnomer, but has become standard through long usage. The same remarks apply to nitroglycerin and nitrostarch.

In the nitration of the cotton there are two things to be accomplished: First, the formation of a product containing a high percentage of nitrogen; and second, the formation of a product which will be 95 per cent soluble in a mixture of two parts ether and one part alcohol. A correctly prepared pyro should contain 12.60 per cent $N \pm 0.1$ per cent. and corresponds very closely to the deka-nitrocellulose. The solubility requirement is very important for the reason that the nitrocotton is eventually converted into a dense colloid, the properties of which depend upon the solubility of the nitrocellulose. If this colloid is of low solubility the resulting granulation will lack in uniform consistency, due to the fact that there will be white particles of uncolloided cotton throughout the mass.

Purification.—Under the general term of purification is included the following sequence of processes: Preliminary boiling, pulping, poaching, screening, and wringing. It is impossible with our present limited knowledge of the cellulose molecule and of the intermediate reactions occurring during the nitration of the molecule, to control the reaction to such an extent that a nitrocellulose, consisting of but one nitro body, will result from a certain reaction accomplished under a set of standard conditions. The products of the reaction always include certain of the lower nitrocelluloses. These bodies influence the stability of the whole mass and must, therefore, be removed before the stability of the pyrocotton can be guaranteed. The object then of the purification treatment given to the pyro is to

insure a uniform stability by eliminating, through hydrolysis or other means, these unstable lower nitro bodies. This is accomplished most easily by prolonged boiling in acid water, which in the preliminary treatment has an acidity varying from 0.1 to 0.3 per cent calculated as H_2SO_4 .

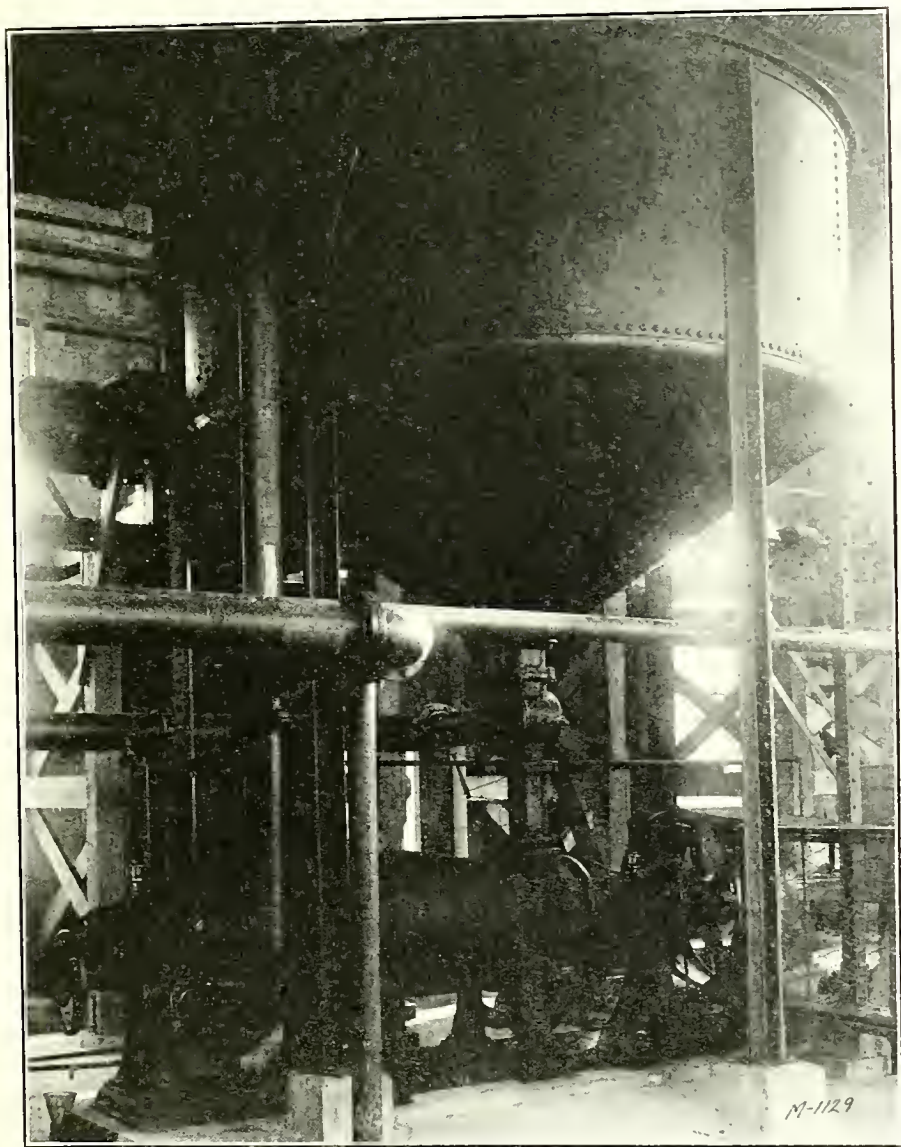


PLATE 7.—DETAIL OF PULPING EQUIPMENT SHOWING JORDAN ENGINE, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

The preliminary boiling process is carried out in large wooden tubs, constructed preferably of cypress and having a false bottom. In the center of the tub is a square wooden duct resting on a false bottom. This duct serves as a heating chamber for the water, by carrying a centrally located steam pipe. The water boils in this duct,

risers to the top, flows over a false top, and is distributed through perforations onto the charge of pyrocotton. The actual boiling time must be 16 hours. The steam is then turned off, the tub refilled, and boiled again for 8 hours. This is repeated until each tub has had a

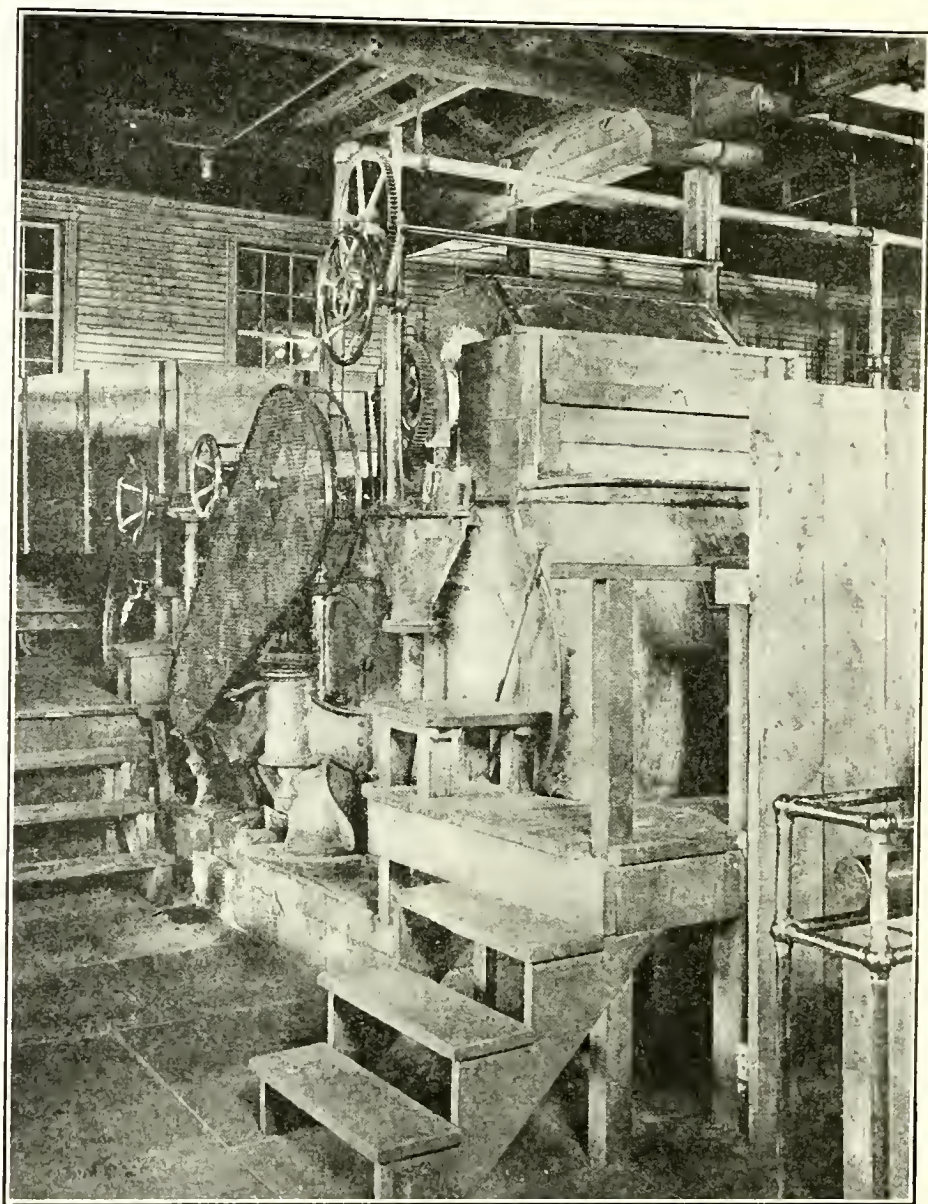


PLATE 8.—MILLER-DUPLEX TYPE BEATER, SMOKELESS POWDER FACTORY,
PICATINNY ARSENAL, N. J.

40-hour boil, with not less than four changes of water. Careful attention to the details in the boiling-tub house insures to the finished pyrocotton a more satisfactory stability than one in which these details have been disregarded.

Pulping.—The next process, that of pulping, has for its object the reduction of the pyrocotton fibers to a uniform state of division in order to remove the last traces of acidity occluded by the fibers. The degree of fineness is determined by laboratory test and has been the subject of a great deal of discussion. It has been maintained by some manufacturers that a finely cut pyro produces a powder inferior in toughness to that made from a coarser cut pyro, but since the colloidizing operation tends to destroy the fibrous structure, it does not appear to be altogether reasonable to assume that the degree of fineness of pyro has an appreciable effect upon the toughness of the


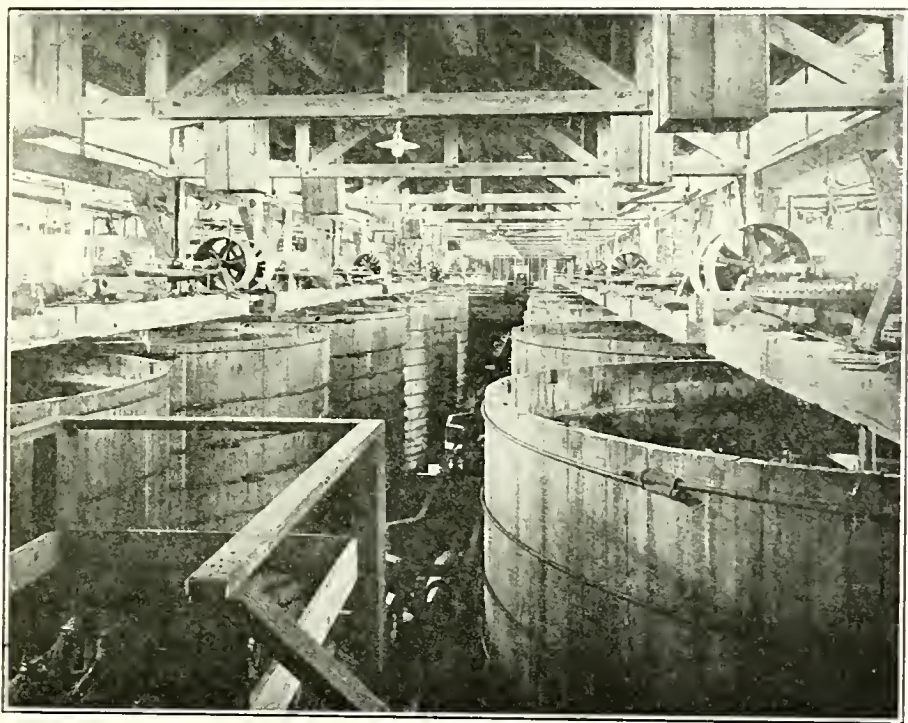


PLATE 9.—INTERIOR OF POACHING HOUSE, OLD HICKORY SMOKELESS POWDER PLANT, NASHVILLE, TENN.

finished powder. The pulping operation is accomplished by machines similar to those used in the paper industry.

The most efficient means for pulping pyrocotton is provided by the Jordan engine. This is operated on the centrifugal principle, by means of which the entering pyrocotton is thrown from the small tapered end to the large end of the beater, and from thence to a storage tank over the machine.

Another type of machine used for this purpose is the Miller duplex beater. The essential features of this pulping machine consist of a fixed set of knives at the bottom of a tub over which revolves a roller which is mounted in adjustable bearings and carries a remov-

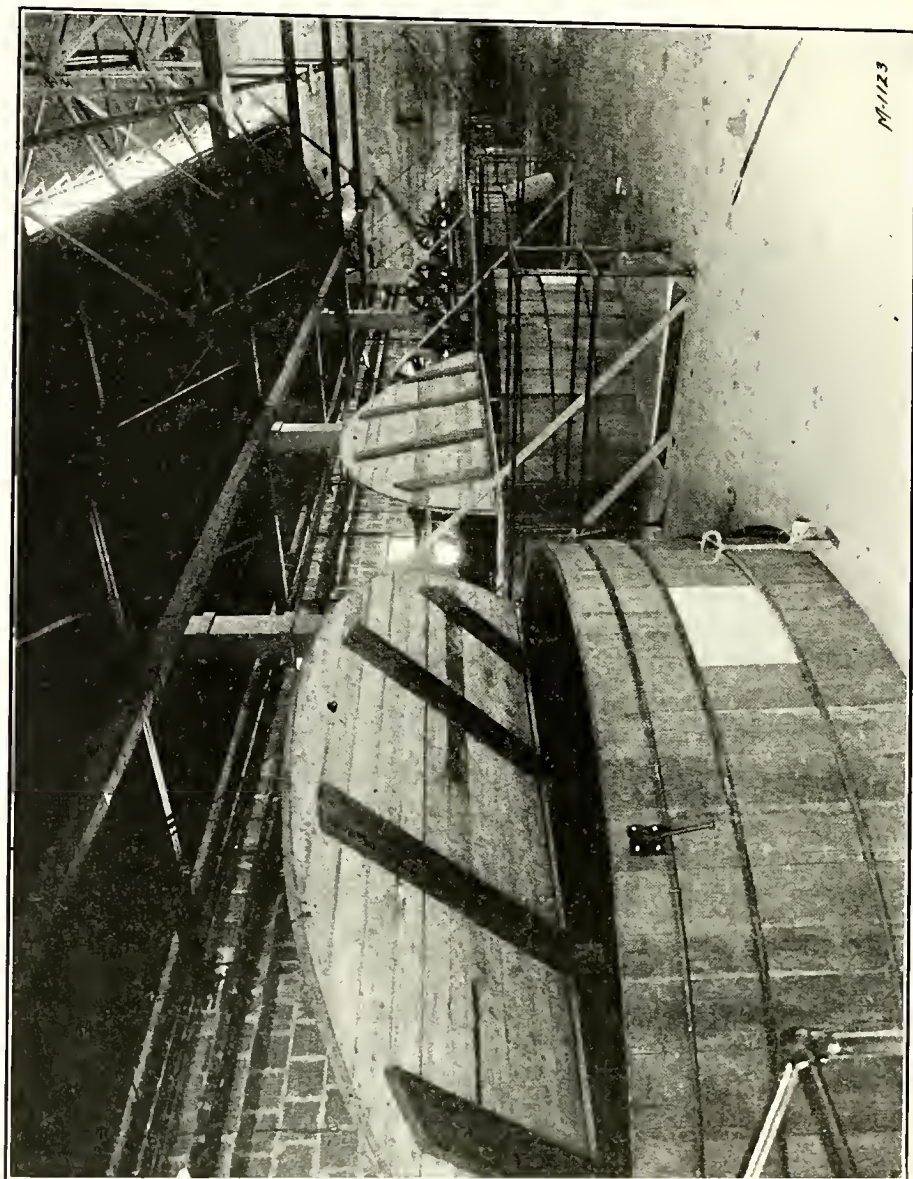

M-1123

PLATE 10.—POACHING TUBS FOR PURIFICATION OF PULPED NITROCELLULOSE, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

able set of knives. The pulping is accomplished by the rolls repeatedly drawing the pyrocotton between the two sets of knives and thus reducing the material to any desired degree of fineness. A weak sodium carbonate solution is used during this process for the purpose of neutralizing the acid retained within the fibers of the cotton and which is set free mechanically when these fibers are macerated.

With the Miller duplex beater the hull fiber is cut in a much shorter time than the linters, the variation being between six and eight hours per beater lot. During the first stage of the pulping treatment a washer, consisting of a large octagonal box covered with very fine wire screen, is lowered into the pulp to remove a part of the sour water, fresh water being added at the same time. The water thus removed passes to settling basins, where any pulp carried off mechanically is recovered. When the desired degree of fineness has been obtained, the material is ready for the next purifying process.

Poaching.—It has already been pointed out that in the pulping operation the fibers of the pyrocotton are broken down mechanically so that the original physical texture of the cotton is destroyed. The preliminary boiling tub treatment reduced the acidity of the fibers and of the interstitial material, but the pulping process, by macerating these fibers, has set free an additional amount of acid. It is, therefore, necessary to repurify the pyrocotton by boiling. This operation is carried on in the poacher house in a manner somewhat similar to that described in the boiling tub house, but with the notable difference that the first boiling treatment is carried out in an alkaline solution. For this purpose there is dissolved 1 pound of sodium carbonate (soda ash) to a gallon of water, and for every 3,000 pounds of dry nitrocellulose there may be added 7.5 gallons of this solution. It is necessary to repeat the boiling operation five times, but the soda is only added during the first boiling. All the other treatments are made in a neutral solution. During all of these treatments a thorough agitation of the pyrocotton is essential so that it is necessary to employ mechanical stirrers driven by gears and shafting. At this stage of the operation it is necessary for the chemical laboratory to determine: (*a*) The stability of the pyrocotton by K. I. test and 135° test. (*b*) the percentage of nitrogen in the pyrocotton. (*c*) the solubility of the pyrocotton in the ether-alcohol mixture. (*d*) the degree of fineness, and (*e*) the ash. The details of performing these tests are described in another chapter.

After purifying the pyrocotton, as described above, it is necessary to separate mechanically any foreign material or any portions of the product which may not have been properly macerated in the beater house. This is accomplished by means of the Packer screen. This

piece of machinery consists of a large box, the bottom of which is fitted with a brass plate having slits one one-hundredth inch in width. The pulp is drawn through these slits by suction underneath the screen and any particles which are too coarse to pass through are returned to the beater house for additional treatment. From the Packer screen the pulp is pumped into one of the large blending tubs where it is stored until needed in the next operation.

*SCHEMATIC SKETCH OF
PACKER PULP SCREEN.*

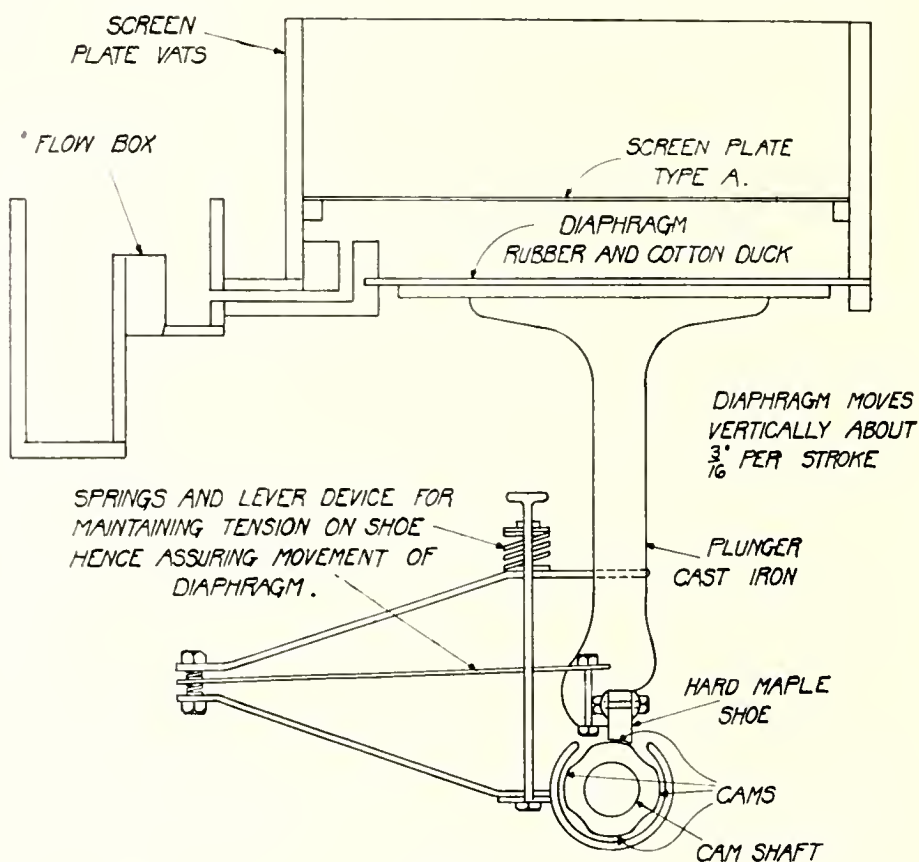


PLATE 11.

Wringing.—The transference of the pyrocotton from the time of nitration up to this stage of manufacture is accomplished by having it suspended in water. It is the function of the wringers to remove water from the pulp so that the subsequent operation of dehydrating by means of alcohol will be done with the minimum amount of water present. This wringing operation consists merely in forcing the water out of the pyrocotton by means of centrifugal action.

The wringer consists of a perforated brass basket lined with a 24-mesh copper screen. This basket is connected by means of a

shaft to a motor, and is so geared that the basket revolves at a speed of 800 revolutions per minute. This centrifugal action forces the water out of the pyrocotton through the basket and so on down the drain pipe. The time of wringing is about 7 minutes. At the end of this operation another sample is sent to the laboratory for the purpose of determining the amount of moisture remaining in the product. This moisture content averages between 28 and 30 per cent.

If the wringers are operated at a uniform rate of speed for the same length of time the moisture content will not vary more than 2 per cent. This operation concludes the manufacture of pyrocotton.

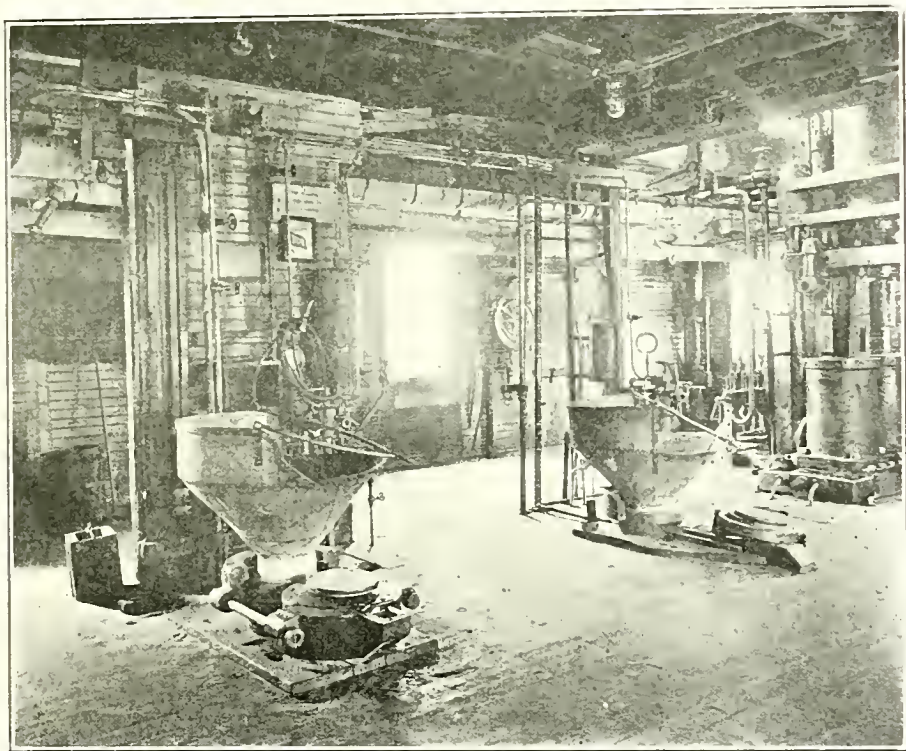


PLATE 12—OPERATING FLOOR, DEHYDRATING PRESS HOUSE, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

Dehydration.—The pyro from the wringers, containing approximately 30 per cent moisture, is transferred to storage and placed in warehouses to prevent freezing in winter time until it is required for dehydration. The object of the dehydration is to remove all of the water from the pyro and to add in its place the quantity of alcohol necessary to form the colloid with the ether which is added later. This amount varies within relatively small limits and is dependent upon the solubility of the pyro being used, as shown by laboratory tests, and also, to a certain extent, upon the size of granulation of the final powder. It is customary to add $1\frac{1}{4}$ pounds of alcohol for every pound, dry weight, of pyrocotton.

The amount of solvent (ether-alcohol) necessary to form the colloid is determined from previous experience of manufacture and is

*SCHEMATIC SKETCH OF
DEHYDRATING SYSTEM.*

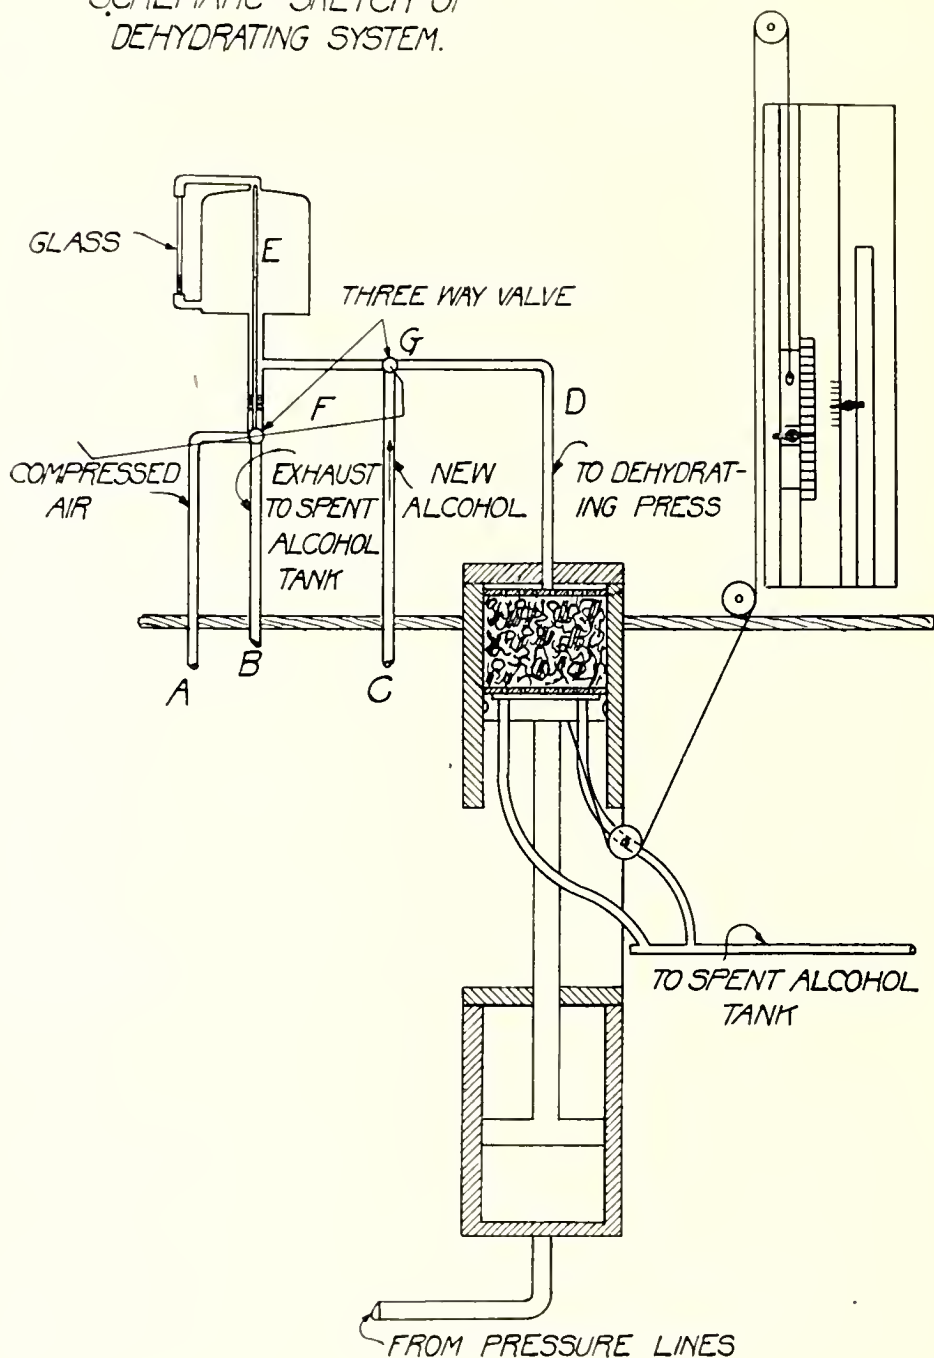


PLATE 13.

correlated with ballistic data obtained from the proving ground. The general practice is to vary the amount of solvent according to

the web thickness of the powder; thus approximately 105 per cent solvent is used in the manufacture of .30 caliber powder, 100 per cent solvent for cannon powder whose web thickness is approximately 0.025 inch, and about 85 per cent for powder having a web

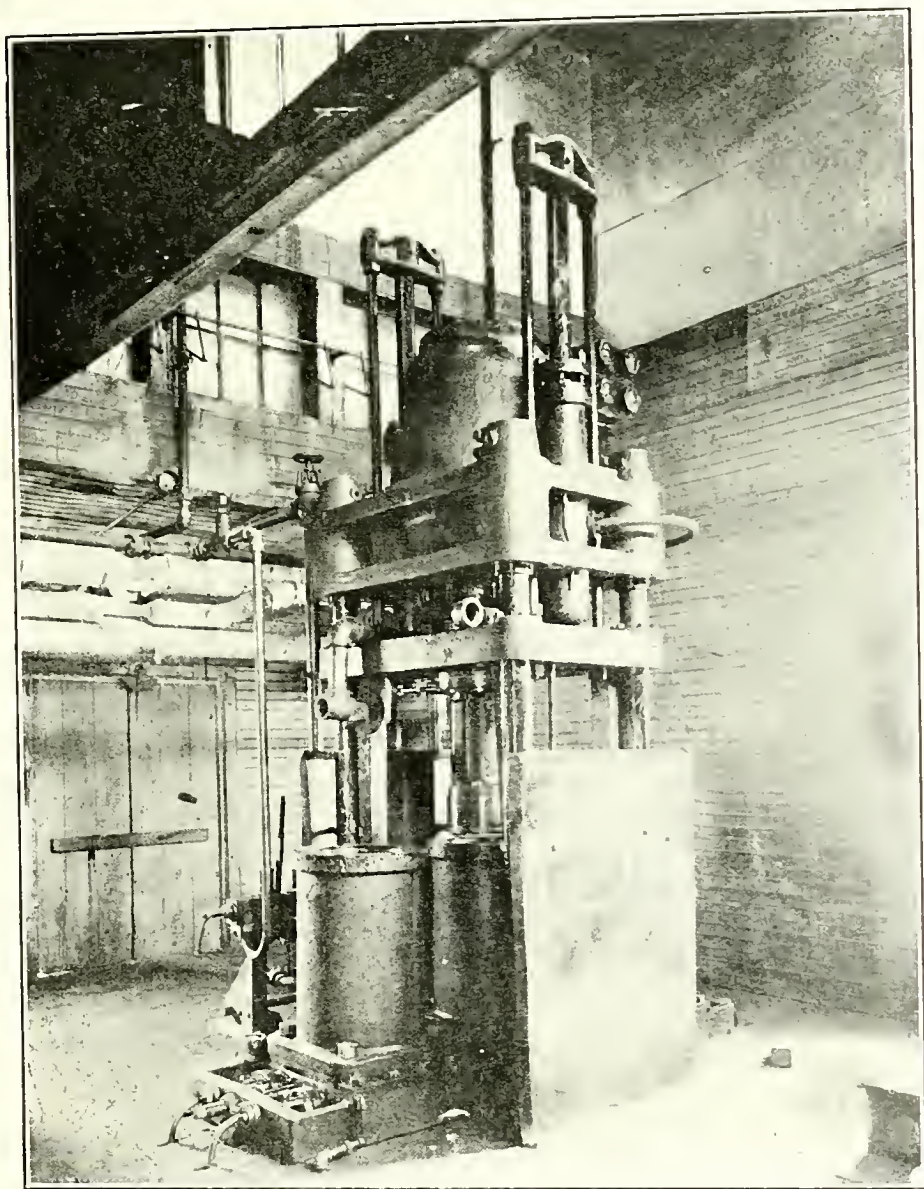


PLATE 14.—LARGE DEHYDRATING PRESS, SMOKELESS POWDER FACTORY,
PICATINNY ARSENAL, N. J.

thickness of 0.185 inch. In the event that 100 per cent of solvent is to be used, or 1 pound of solvent (1 part alcohol: 2 parts ether) for every pound of pyrocotton, it is necessary that the usual dehydrating press charge of 25 pounds dry weight of pyrocotton should

produce a block weighing 33 pounds 4 ounces (25 pounds pyrocotton and 8 pounds 4 ounces alcohol).

The dehydrating operation is conducted somewhat as follows: The press consists of a cylinder and movable piston operated by hydraulic pressure, as indicated on the attached sketch. The press is charged with pyrocotton and "low pressure" (about 250 pounds per square inch) is applied for a few moments, thus squeezing out a portion of the excess water. The predetermined amount of alcohol is then forced into the press by use of a pump, and the pressure increased to about 4,000 pounds per square inch. The alcohol functions first as an agent for displacing the water in the block and finally as a dehydrating agent. Its initial entrance into the block forces out a small portion of the remaining water; later, however, it combines with the residual water and produces a block of pyro nearly free of water. The first portion of this alcohol contains relatively large amounts of water and is forced out of the press into the spent alcohol tank. The remaining amount, however, is about 90 per cent alcohol. The spent alcohol resulting from this process is pumped back into the storage tank and eventually rectified, with the addition of caustic soda to decompose dissolved or suspended nitrocellulose. It is then used again either in the dehydrating process or in the manufacture of ether.

The dehydrated blocks must be first thoroughly broken up before the next operation of mixing is commenced. For this purpose they are transferred into a rotating drum or block breaker, equipped on the inside with a wire screen and iron prongs. This barrel upon revolving throws the block against the prongs, thus breaking it into small lumps which lend themselves more readily to the mixing operation and which in turn insures a more even colloid.

From this point up to the time the powder is put into the solvent recovery the product is kept in closed containers as much as possible between the various steps in the manufacturing process in order to prevent excessive losses in solvent, which is an important point, not only from the economical but also from the manufacturing standpoint, since excessive loss of solvent would entail difficulty or irregularity in the subsequent screening and graining operations.

Mixing.—The mixing operation is the next step in the formation of the colloid. As has been pointed out above, unless care is exercised during the dehydrating process in producing a block of uniform dehydration, it will be impossible to secure a good colloid. It is no less important that the ether be added to the mass in such a manner that the evaporating losses are minimized by incorporating the ether throughout the mass as quickly as possible. This is accomplished by the use of a mixing machine. It consists of a covered

water-cooled tank in which two shafts bearing curved agitator blades rotate in opposite directions, giving a kneading motion to the material in the mixer. During this agitation the ether is poured in rapidly in order to minimize loss of solvent by evaporation. In the case of the small arms powders and of the one-pounder single perforated grains, graphite is added to the mixer charge before the ether is run in.

It is also at this stage of the process that the so-called stabilizer is incorporated into the colloid. The material used for this purpose is diphenylamine, and there is dissolved in the ether enough

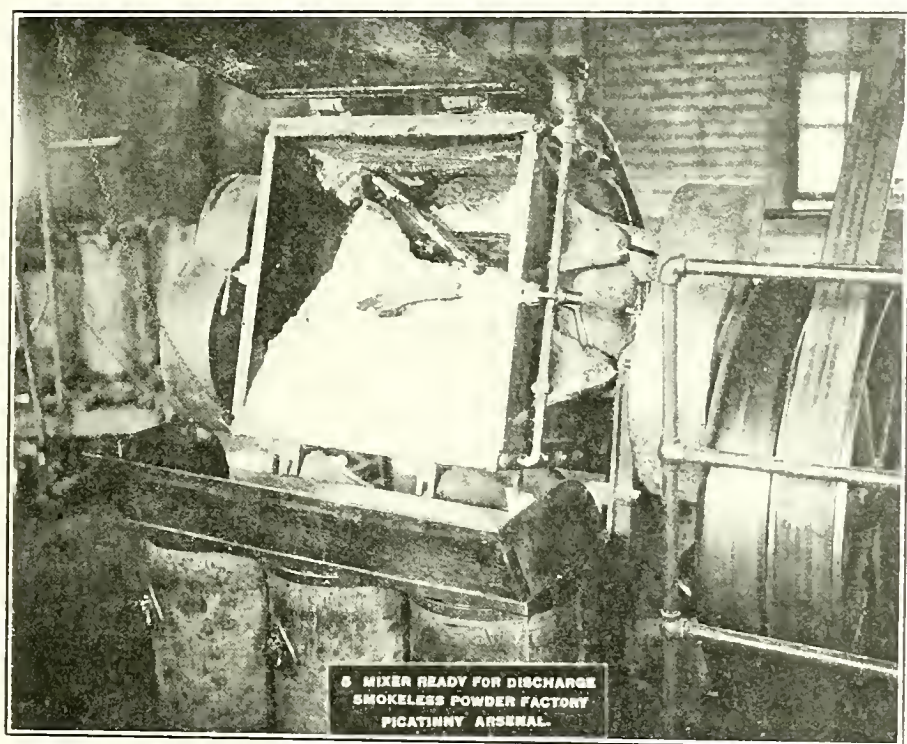


PLATE 15.

of this substance so that the finished powder will contain between 0.40 and 0.50 per cent diphenylamine.

The object of adding diphenylamine at this stage is to incorporate it thoroughly throughout the colloid so that on long-continued storage any nitrous fumes which may be evolved from the powder will be absorbed by this so-called stabilizer. The many factors entering into the use of this material are more properly discussed in a later chapter on surveillance and stability.

Pressing.—The colloid is next subjected in sequence to the action of a preliminary blocking press, a macaroni press, and a final blocking press.

The incorporation of ingredients as accomplished in the mixing is really but a preparatory stage for the final formation of the colloid, this last step being completed by the action of the presses.

The preliminary blocking press consists merely of a cylinder and piston similar in action to the dehydrating press. It forms the

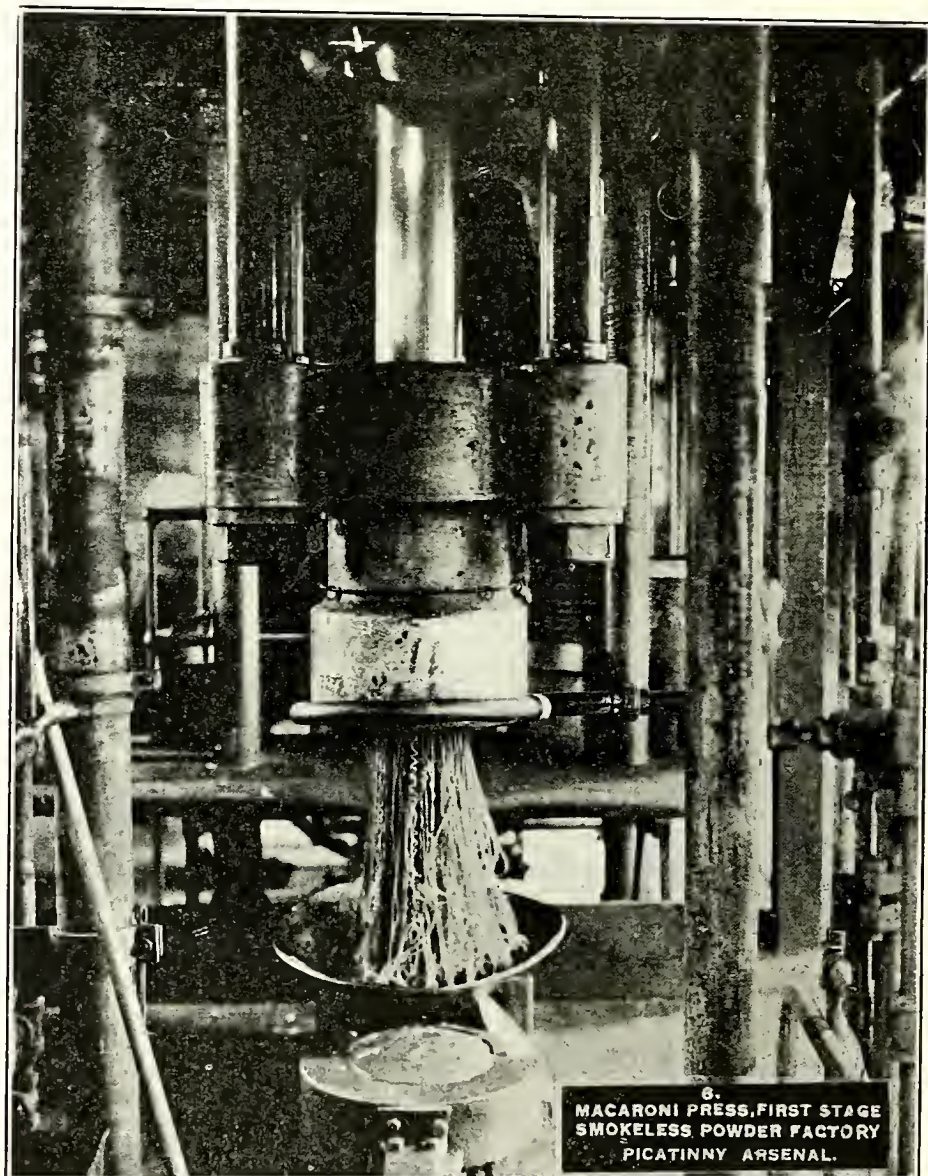


PLATE 16.

colloid into a dense cylindrical mass by subjecting it to a compression of 3,500 to 4,000 pounds per square inch. This "preliminary block," so called, is then transferred to the macaroni press. The operation here consists in straining the solid block of colloided matter through a heavy brass perforated plate on which are placed one 12-

mesh steel plate, two sheets of 24 and one sheet of 40 mesh steel wire screens, and at a pressure of 3,000 to 3,500 pounds per square inch, in such a manner that the material as it is ejected is similar in appearance and size to macaroni. As it leaves this press it falls by gravity into the cylinder of the final blocking press. This is similar in

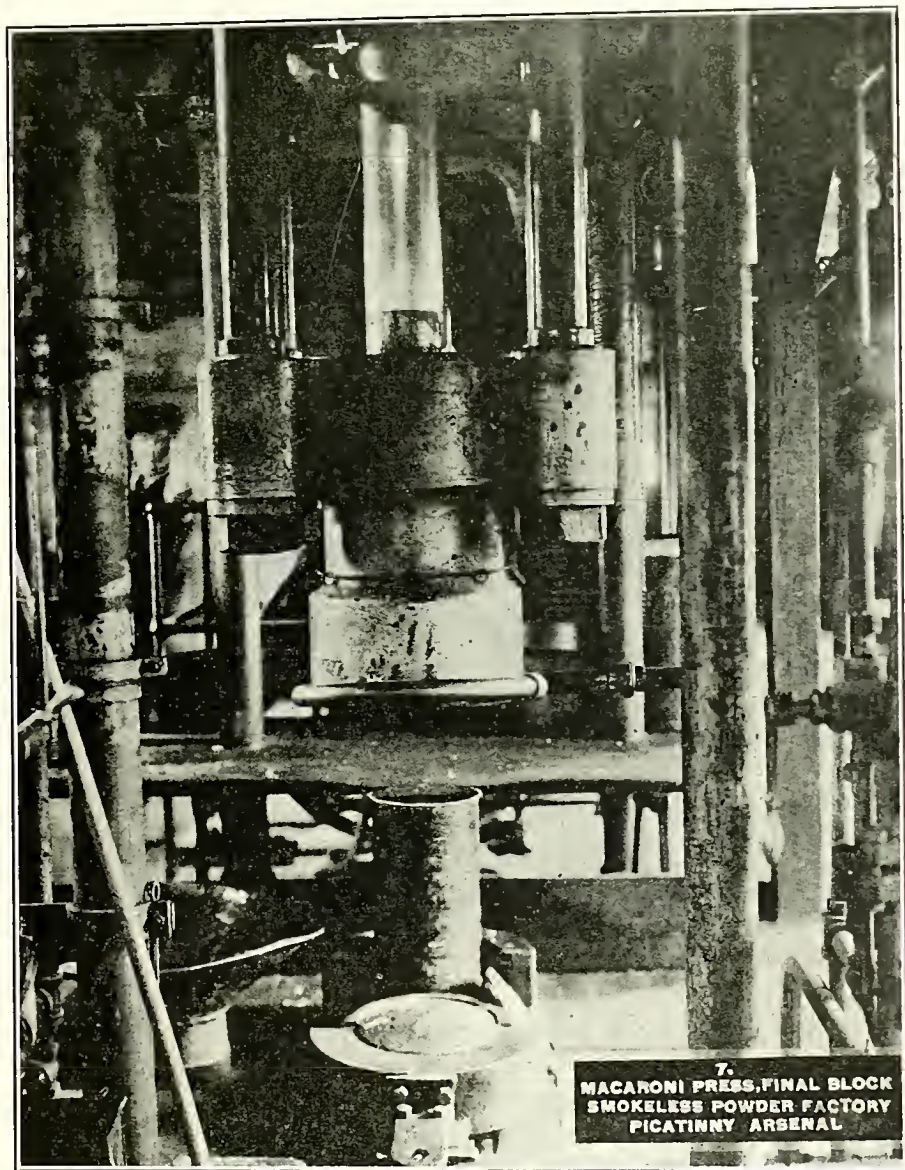


PLATE 17.

every respect to the preliminary blocking press and forms the colloid into the final shape before it is taken to the graining press. The block is here subjected again to heavy pressure (3,500 to 4,000 pounds per square inch) for one to two minutes, thus completing the colloid of the pyrocotton. The colloid now is entirely different

in appearance from the material as drawn from the mixers, for it has been changed from a mass resembling light brown sugar to a dense, elastic, translucent brown substance. These operations of pressing insure, to the greatest possible degree, a uniformly thorough action of the solvent upon the pyro. and very nearly eliminate the possibility of having uncolloided cotton in the finished powder.

Graining and cutting.—The final operation from the standpoint of the granulation of the powder occurs in the graining press room. These presses may be set either horizontally or vertically. Their action is to force the colloid through a steel die, in such a manner

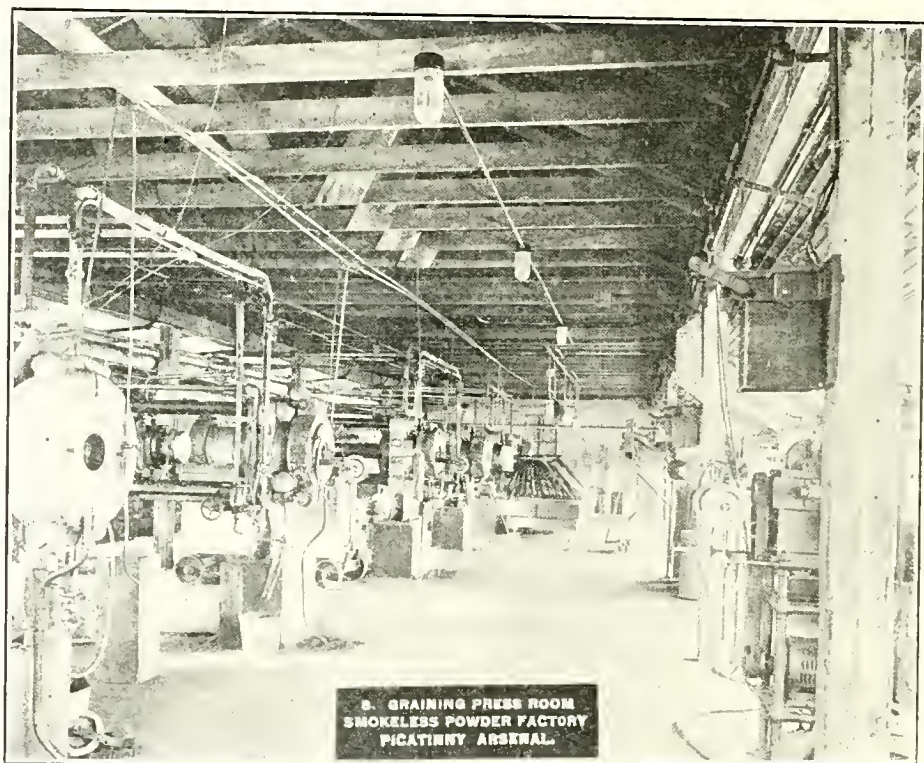


PLATE 18.

that the expressed material, which takes the form of a string, will be delivered at a uniform rate of speed under the control of the operator at the press. The power which is necessary to force this colloid through the die is very great and is supplied by means of a hydraulic ram, under a pressure of 2,500 to 3,800 pounds per square inch. The press head may be equipped with one or more barrels, depending upon the rate of production of the colloid from the other departments and also upon the capacity of the graining presses themselves. When small arms powder is being grained there may be 36 strings issuing simultaneously from the head. With a large caliber powder, however, such as 16-inch gun, it is customary to use but one

barrel. The "powder" issues from the press head in the form of a flexible rope which is led over pulleys to a cutting machine. This cutting machine is capable of very fine adjustment and is so manipulated that the ratio of the diameter of a grain to its length always remains constant.

The factors affecting the size of the grain and its relation to the type of gun for which it is designed are discussed in a subsequent chapter.

Solvent recovery.—Having prepared the powder in a definite form of granulation the next step is that of recovery of the ether

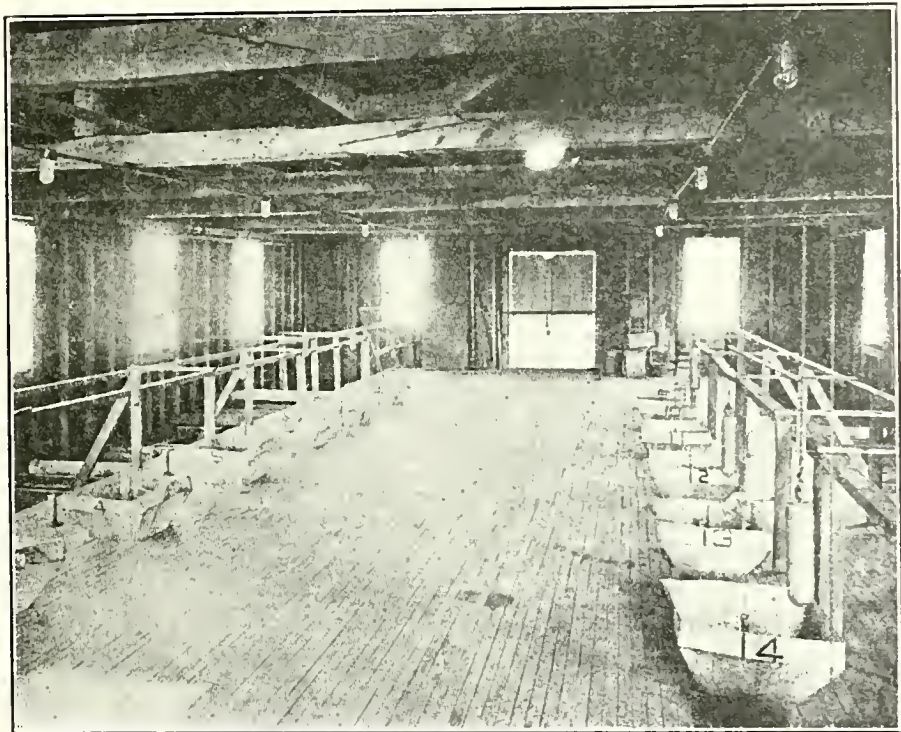


PLATE 19.—CHARGING FLOOR, CAN TYPE, SOLVENT RECOVERY HOUSE, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

and alcohol which is given off during the process of drying. The unit which is concerned in the recovery of this solvent is termed the solvent recovery, and may consist of any one of three types: First, the chamber type of solvent recovery, in which the powder is transferred from a car to a box lined with zinc and provided with a water-sealed lid; second, the car type of solvent recovery, in which the car itself containing the powder grains becomes the chamber; and third, the can type of solvent recovery. In all of these the governing principle is the same.

Warm air is circulated through the powder and is then forced over cold coils. This change in temperature causes a precipitation of the

solvent upon the coils and produces, in effect, a miniature fog. The saturated air after passing over these cold coils loses its surplus solvent, is reheated and then is again forced through the powder in continuous cycle, in this manner completing the closed system of air circulation. The length of treatment depends upon the size of the powder, the larger calibers, of course, requiring a greater length of time than the smaller ones. Definite rules are laid down governing the length of time necessary for powder to remain in the solvent recovery building—rules which are the result of experiments and

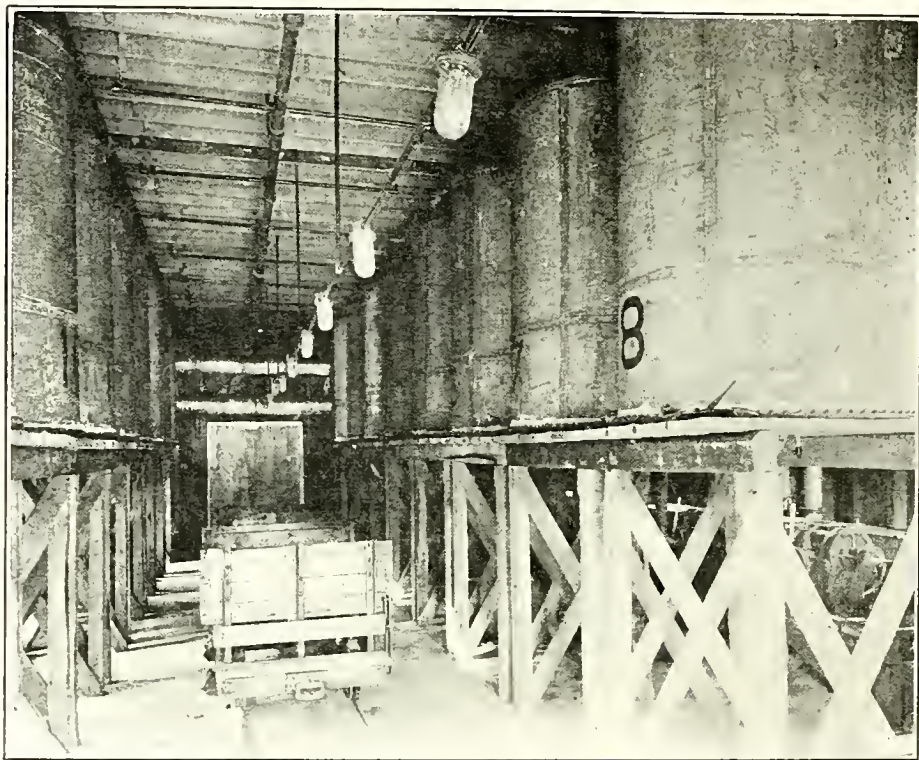


PLATE 20.—CAN AND DISCHARGE FLOOR, CAN TYPE, SOLVENT RECOVERY HOUSE, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

which combine the maximum of efficiency with the best results from the standpoint of drying.

The temperature and times of heating in the solvent recovery processes are approximately as follows:

Propellant powders having web thickness up to 0.095 inch:

Raise to 30° and hold for 24 hours.

Raise to 35° and hold for 24 hours.

Raise to 43° and hold until total time of treatment has been 7 days.

For powder of heavier web than 0.095 inch:

No heat for 48 hours.

Raise to 25° C. and hold for 24 hours.

Raise to 30° C. and hold for 24 hours.

Raise to 35° C. and hold for 24 hours.

Raise to 40° C. and hold for 24 hours.

Raise to 43° C. and hold until total time of drying of solvent recovery treatment has been 8 days.

Drying.—There are three separate types of drying operations: The first and most satisfactory except from the standpoint of time,

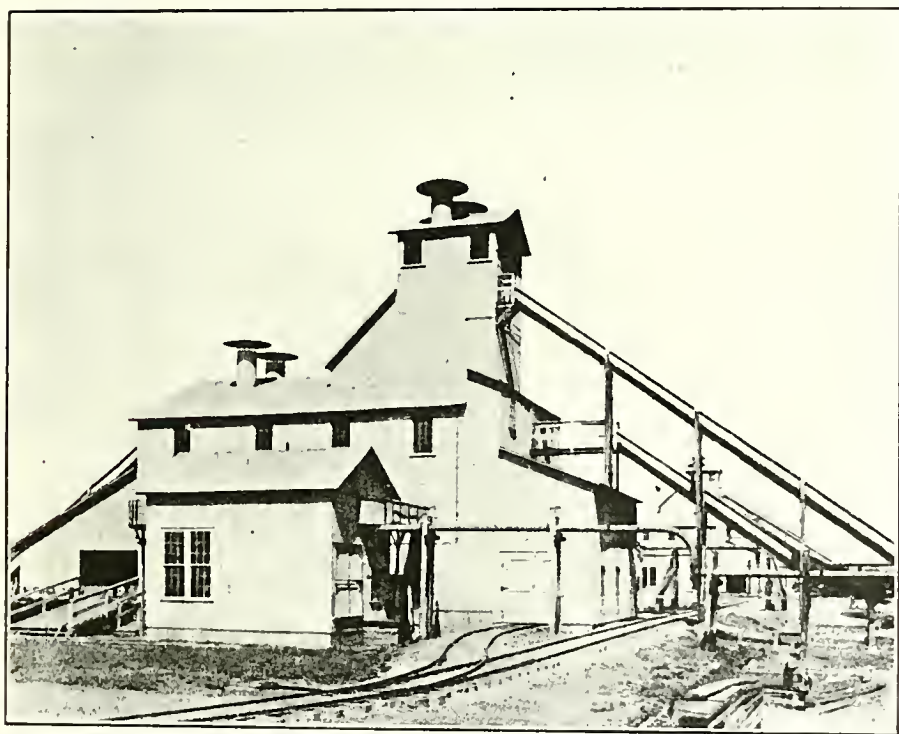


PLATE 21.—EXTERIOR OF "CONTINUOUS" PROCESS DRY HOUSE, OLD HICKORY POWDER PLANT, NASHVILLE, TENN.

is the air dry. A second method, known as the water dry system, has a great advantage as to time saving, and up to the present time there is little reason to believe that the resulting powder is not as satisfactory as that dried by the air method. Finally, a new process, termed the "Nash alcohol dry system," is being investigated.

Air dry treatment.—In this treatment the powder is transferred directly from the solvent recovery house to the dry house and placed in bulk in narrow bins. The time of drying varies with the granulation of the powder. For all granulations, however, there is a heating period of 30 days at 43° C. Temperature is then raised

to 50° and the time required to drive off the volatile matter until the desired total volatile content has been secured varies from about 30 days for the 75 mm. powder to 90 or more days for 16 inch powder. In the case of powder having web thickness of more than 0.095 inch,

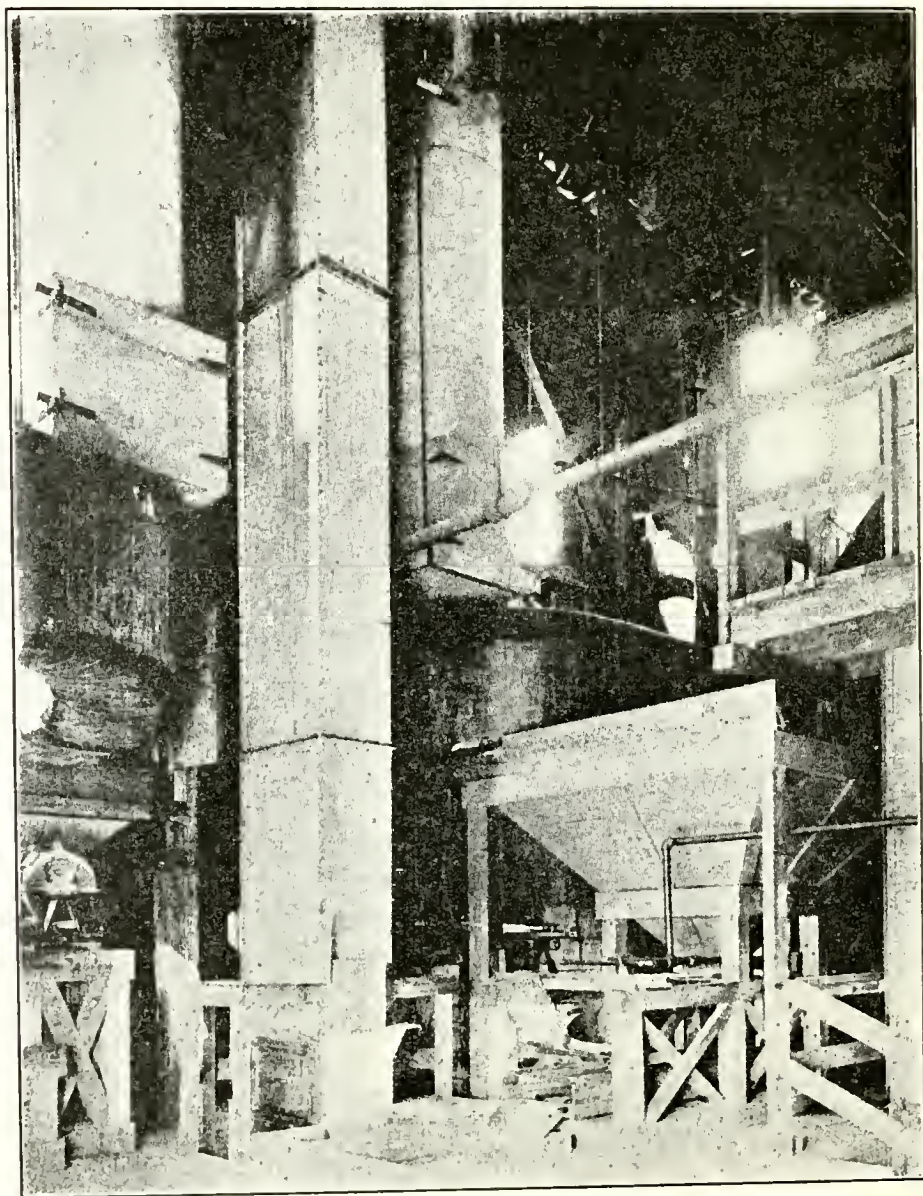


PLATE 22.—INTERIOR OF "CONTINUOUS" PROCESS DRY HOUSE. OLD HICKORY SMOKELESS POWDER PLANT, NASHVILLE, TENN.

a period of at least two weeks in the dry house without heating must precede any heating treatment.

From time to time the laboratory analyzes a sample of the powder to determine if the required moisture and volatile content has been

reached. This moisture and volatile content, or total volatiles, as it is usually called, is very important from the standpoint of ballistics.

Smokeless powder is, to a certain extent, hygroscopic. Extensive experiments have been performed for many years to determine definitely the amount of total volatiles necessary in a given size powder

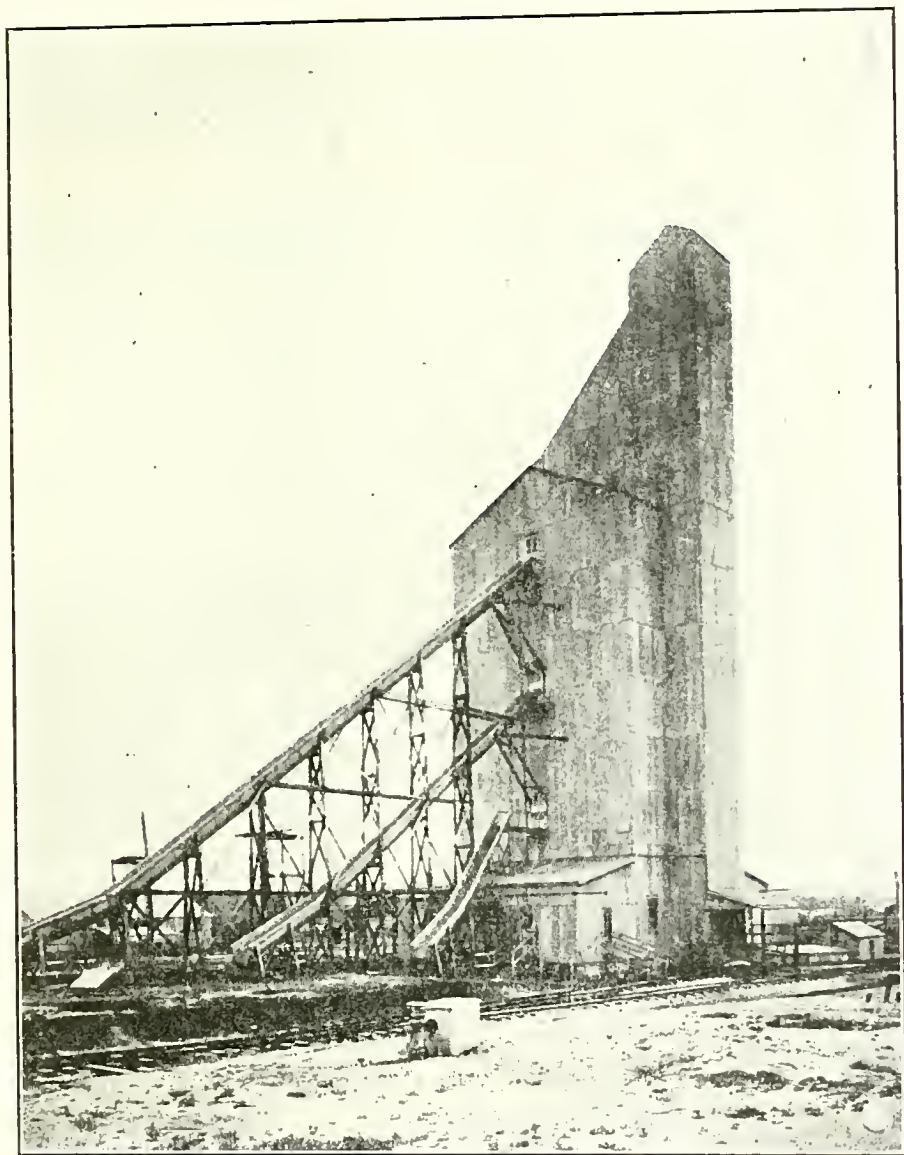


PLATE 23.—CANNON POWDER BLENDER, OLD HICKORY SMOKELESS POWDER PLANT, NASHVILLE, TENN.

to give the best results. If the powder is permitted to become too dry, a small weight of charge with correspondingly large air space will be encountered in the test firings in the gun, resulting in excessive pressure at service muzzle velocity, owing to too rapid combustion. If, on the other hand, it is not dry enough a relatively high

weight of charge with correspondingly small air space will result in excessive pressure at service muzzle velocity. It is, then, very necessary that the drying operation be carefully watched from the stand-points of chemical control and of technical manipulation of the house.

Water-dry treatment.—The main difference between the air-dry process and the water-dry process is the difference in the surrounding medium. In the first case it is warm air, and in the second warm water, but the object desired is the same in either case. Water is kept circulating throughout the powder at temperatures which vary by 10° increments from 25° to 55° C., for approximately four days

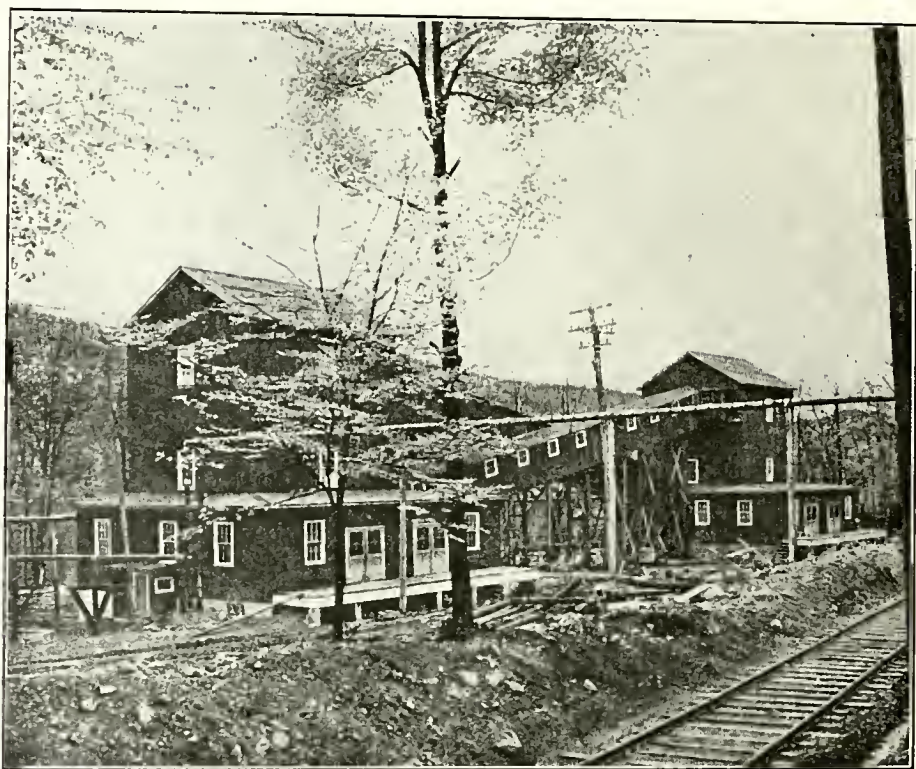


PLATE 24.—CANNON POWDER BLENDER, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

for powders having a web thickness of approximately 0.020 inch. Later the powder is removed and air dried for about 48 hours, this latter treatment requiring much less time to finish than when the powder has only the air-dry treatment.

A later development in this water-dry process is the so-called continuous drier. This differs from the ordinary dry-house treatment in that the drying of the powder is accomplished in between 4 and 5 hours, depending upon the size of the granulation. The powder enters the dry house from the water-dry system, is hoisted to a hopper and then slides by gravity into a shaking screen. This screen re-

moves foreign material, and drops the powder to a bucket conveyor of the ordinary type. The powder is then hoisted to the top of the building, where it is thrown into a drying chute. This chute is approximately 6 inches in thickness, 5 feet in width, and about 10 feet in length, and is equipped with baffles running crosswise in the direction of its smallest dimensions. A series of screens on the side wall provide the means for the passage of warm air through the powder; and a temperature of 50° C. is maintained by this means at the bottom of the chute. A shaking device near the floor is capable of such regulation that the rate of discharge from the drier,

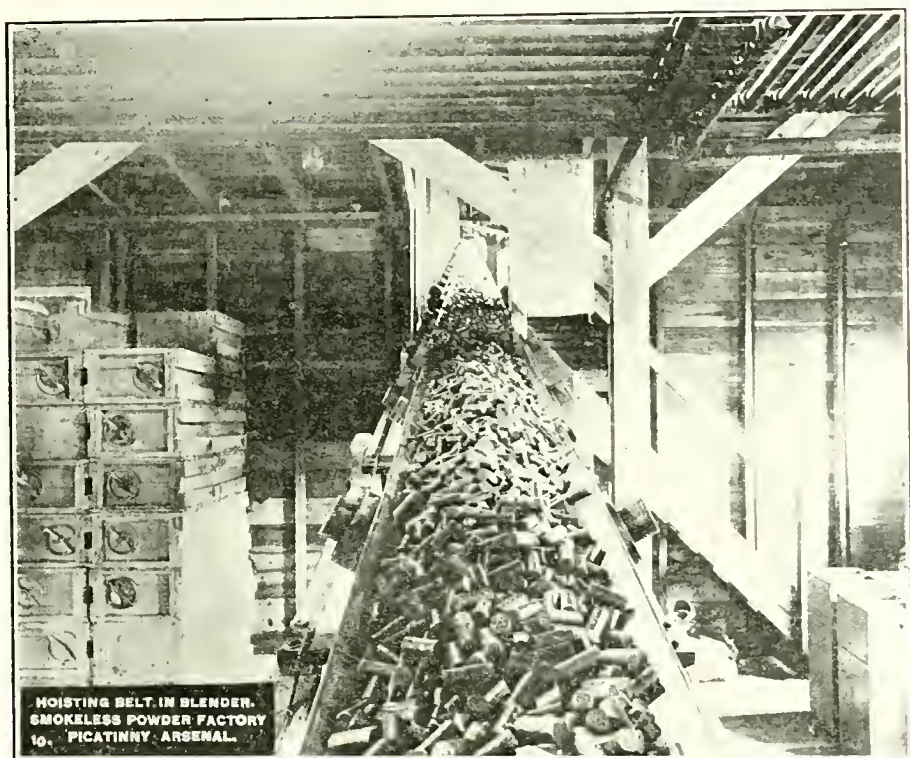


PLATE 25.

and consequently the volatile content of the powder, is controlled by the speed at which this shaker is operated and by the amount of clearance between the shaker and the bottom of the chute. In one of the largest war plants one continuous drier was capable of drying, to the correct moisture and volatile content, 100,000 pounds of 75 mm. powder in 24 hours.

Alcohol-dry treatment.—In the Nash alcohol-dry system the drying medium is a mixture of water and alcohol. The relative percentage of the two liquids varies according to the caliber of the powders, and experimental work is still being carried out to determine the best working conditions. If too strong an alcohol is used, it results in a

brittle powder, a powder in which the external moisture is reduced to a very small amount, and one in which the shrinkage alters to a considerable extent the web dimensions. This naturally gives excessive pressure in the gun. If too weak an alcohol is used, the time of drying is proportionately lengthened. This alcohol-dry system has the advantage that none of the ether is lost and but a very small part of the alcohol. It also does away with the solvent recovery treatment and it is only necessary to put the powder in the air-dry house for a short space of time to obtain a correct percentage of total volatiles, or to finish with a water-dry treatment and final drying in the continuous drier.

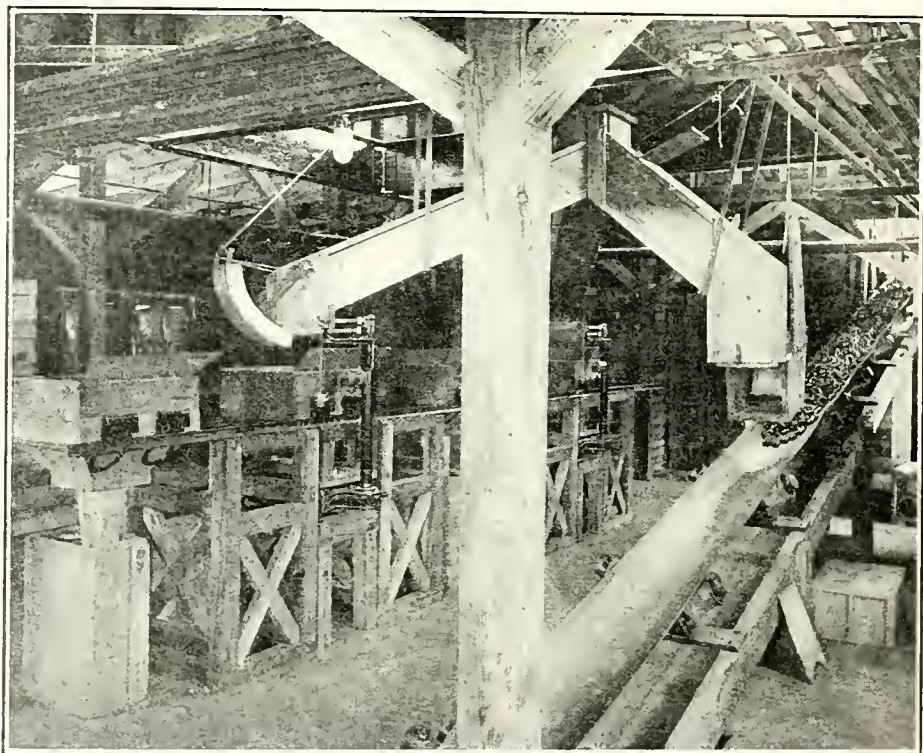


PLATE 26.—BOX FILLING AND WEIGHING FLOOR, CANNON POWDER BLENDER, SMOKELESS POWDER FACTORY, PICATINNY ARSENAL, N. J.

Blending.—The next step and perhaps the most important one from the standpoint of uniformity of firing is the proper mixing or blending of a certain arbitrary amount of powder. For the larger caliber guns it is customary to blend or mix a complete lot of 100,000 pounds of powder, but for the smaller caliber powders, particularly for the small arms powders, lots ranging from 15,000 to 50,000 pounds are more usual. The blending operation consists merely in the transference of the powder by means of gravity from one bin to another bin, this transference resulting in a thorough mixing of all of the lot. These bins are so constructed that when full of a lot of

powder the powder assumes the shape of a double cone with one apex pointed down toward the discharge pipe and the other apex pointed up toward the top of the bin. The proper construction of these bins from the standpoint of the correctness of the angles at the sides of the bin is very important. If the sides of the bin are too steep the powder will slide down toward the apex of the lower cone. If, on the other hand, the sides are built on too gradual a slope the powder will not flow freely from the bin and it would be necessary to use a raking device in order to empty the bin toward the end of the lot. It is essential, therefore, that a point midway between these two be

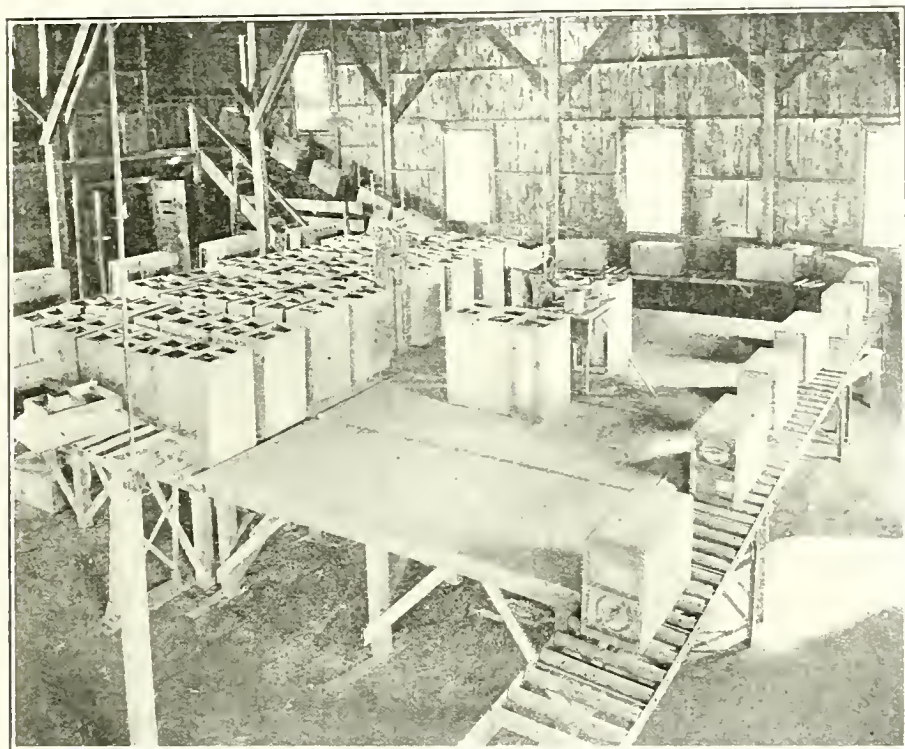


PLATE 27.—POWDER BOX TESTING HOUSE, SMOKELESS POWDER FACTORY,
PICATINNY ARSENAL, N. J.

found, a point so selected that the powder will not slide down the side of the bin, yet at the same time will insure a complete emptying and mixing of the lot. These angles have been determined and when the principles are observed no difficulty results from lack of proper blending. After two or three cycles from one bin to the other have been completed, the powder is weighed and boxed.

A new type of blender has been worked out at Picatinny Arsenal, which apparently is a considerable improvement over the old "tower blender." In the place of two bins set one upon the other as in the old type, an awkward arrangement which necessitated a

building at least 100 feet high, two separate buildings were constructed about 100 feet apart. The bottom of the one bin is connected with the top of the other by an endless belt. There are, then, two belts operated independently of each other for the transference of the powder from the bottom of one bin to the top of the other. The arrangement at the bottom of each bin is such that the powder may be boxed in either building. When it is desired to empty one bin and transfer to the other for the purpose of blending, it is merely necessary to put the belt in motion and open the chute.

The speed of the belt is such that 100,000 pounds are hoisted in about 75 minutes, a speed not possible with the older type of blender. The powder is charged into a hopper at the base of one tower from bags, if coming from the dry house, or from boxes if the powder is being reblended, onto a conveyer belt, carried to the top of the second tower, and dropped into the bin until the entire lot has been transferred to this bin. The conveyer belt at the base of this second tower is then started, the powder carried to the top of the first tower, and thence into the bin, thus completing the cycle. The blending comprises four complete cycles.

After the blending is completed the lot of powder is boxed and stored. The powder container used for storage is merely an air-tight zinc box about which is built a wooden box completely covering and protecting the metal inside. It is of such a size as to hold from 110 to 140 pounds of smokeless powder, depending upon the type of box. These boxes are tested for air leaks to insure the powder retaining the same moisture and volatile content as when withdrawn from the dry house.

CHAPTER II.

GRANULATION OF SMOKELESS POWDER.

GENERAL.

The propellant used as a charge for the gun possesses a certain force or latent power which upon combustion becomes a kinetic or moving force and which drives the shot to the muzzle of the gun. What actually occurs when powder is ignited is as follows: In the first place, the powder is converted by change of state, i. e., from solid to gas, into a volume greater than that originally occupied by the powder; in the second place, the heat generated by the explosion expands the volume of this gas and increases its pressure, and finally sets the projectile in motion.

The rapid development of the gas pressure within the gun should be of such a progressive nature that the force exerted should not attain its maximum at the time of the ignition (as would be the case if a high explosive were used as a propellant), but rather should attain it by a relatively gradual rise. The control of this pressure lies in the form of granulation of the individual powder grains, and also in the composition. The granulation determines the area of the burning surface of the grain, which in turn controls rate of combustion, and through that, the pressure.

A brief consideration of the factors influencing and determining the proper granulation of the powder will involve a discussion, first, of the best form of the powder grains, and second, the factors which determine the size of the grains.

The best form of granulation from a ballistic point of view is, first, that which with the smallest given weight of charge will impart to the projectile the highest muzzle velocity within the prescribed limits of maximum pressure; second, that which will cause the minimum erosion to the bore, and third, that which shows maximum regularity in ballistics. The grains should burn uniformly from the surface and the rate of burning should vary directly with the pressure; the greater the burning surface, the higher the pressure, other things being equal. It is evident, therefore, that the shape of the grain is a direct factor in determining the amount of burning surface.

Shape of granulation.—When the powder is ignited its rate of burning is dependent upon the area of the burning surface. It was formerly supposed that the powder grains should be so designed

that this area should remain nearly constant, in an attempt to maintain the original pressure developed upon ignition throughout the period of combustion.


Powder was made in the form of tubes, broad tapes, and thin flakes as the result of efforts to realize this condition. This theory, however, is not in accord with the practice in this country, and it has been demonstrated that instead of maintaining a constant pressure during the combustion of the charge, the pressure should be gradually increased until the maximum is reached, in the case of the ideal gun, at the time that the projectile is about to leave the muzzle. Our guns are designed to withstand a pressure increasing to the maximum at a point in the bore just ahead of the powder chamber. If this object is to be attained there must be an actual progressive increase in the area of the burning surface. This larger area has been secured by perforating the grain longitudinally, with holes so spaced that the progressive burning of the grain increases the area exposed to ignition. This multiperforated grain has been manufactured in three shapes, namely, the cylindrical grain, the square grain, and, lastly, the "sliverless" or Walsh grain. Of these three, however, the cylindrical form has been the most used. The cylindrical or multiperforated grain for cannon powder has seven circular longitudinal perforations, one central and the other six equally distributed midway between the center of the grain and its circumference. A uniform distance between the center of the central perforation, the center of the outside perforation, and the outside circumference of the grain itself is the object sought, since it has been found that this facilitates the complete combustion of the charge. The length of the dry grain is between 2.1 and 2.5 times the outside diameter. For the smaller type of gun the multiperforated grain finds no use, and in its place the single perforated grain has been adopted. The types of gun for which the single perforated grain is used are the .30 caliber rifle, 37-mm. gun, 2.95-inch sub-caliber, 2.95-inch mountain gun, and 3-inch mountain howitzer. Unlike the multiperforated grain, it burns with practically a constant burning surface.

The square form of grain is made with four longitudinal ridges on each side and nine square perforations. Contrary to expectations, this grain has not proved satisfactory, first, because of the difficulties in cutting the die, and, second, because of the difficulties in maintaining the square shape of the grain due to the soft, pliable nature of the colloid.

The "sliverless" or Walsh grain was invented by Col. J. E. Walsh in 1912, at Picatinny Arsenal. The following diagram shows a comparison of the burning surface of the cylindrical and "sliverless" grains. When the cylindrical grain burns it is apparent that the

last portions to be consumed will be six inner and six outer pieces of powder of triangular cross section, called "slivers." The Walsh or "sliverless" grain partially eliminates this defect. This more complete combustion of each grain of powder has a direct economic effect in that it reduces the weight of the charge, and also considerably accelerates the rate of ignition by increasing the surface per unit of mass.

Size of granulation.—In designing the granulation of the powder, the chemical composition of the colloid does not need to be considered, as it does not alter for the various types of guns. The factors which affect the size of the grain are, first, the type of gun for which the powder is to be used: second, the weight of charge: third, the weight of the projectile; fourth, the effect of the per cent solvent upon the shrinkage of the powder: fifth, the effect of the moisture and

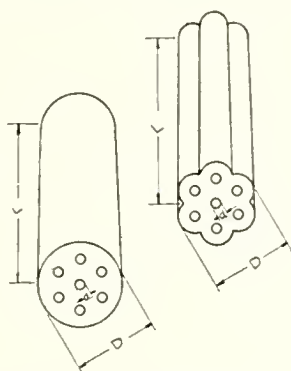

volatile content of the powder: and lastly, the effects of the different methods of drying.

Artillery is divided into three general classes: Guns, howitzers, and mortars. Tschappat (Ordnance and Gunnery, J. Wiley & Sons, New York, 1917) describes the following types of artillery:

Seacoast guns, field guns, mountain guns, antiaircraft guns, and subcaliber tubes.

The howitzers are classed as mountain howitzers and field howitzers.

The mortars are seacoast mortars and trench mortars.

In comparing the three types of cannon as to length, the gun is the longest, its length ranging from 40 to 60 times the bore of the gun: howitzers are medium in length, and mortars the shortest. Therefore, the mortar type would require a powder with a larger burning surface than either a gun or a howitzer of the same caliber. The gun, however, as a class gives the highest degree of accuracy, permits the longest travel of the projectile, and imparts the highest muzzle velocity.

The calibers of seacoast guns range from 2.24 to 16 inches and are permanently mounted in fortifications. Field guns, or mobile artillery, are designed to accompany or follow an army in the field, and are smaller in caliber, except in some of the railroad mounts. Depending upon the type of the gun, however, the granulation of the powder must be so designed that the functions of the different guns are best served.

Howitzers are used only in mobile artillery. "For each caliber of gun there is designed a corresponding howitzer of an equal degree of mobility, and the caliber of each howitzer is the same as that of the gun of the next lower degree of mobility; that is, the howitzer corresponding in mobility to one of the guns is of the same caliber as the next heavier gun and uses the same projectile."—(*Tschappat, idem.*)

The seacoast mortars are short guns and in firing them there is always a large amount of unburned powder slivers thrown from the muzzle, except when the "sliverless" or Walsh grain is used. This grain, as has been pointed out before, by providing a larger burning surface, burns more quickly and thus practically eliminates this undesirable feature.

Since each type of gun has its specified size of powder chamber, it is necessary to ascertain this capacity before designing the granulation of the powder. Other factors being equal, the greater the capacity of the powder chamber, the greater the size of the powder grains. If, for instance, the capacity of the powder chamber for the 12-inch mortar, model of 1890, is 2.674 cubic inches, and 12-inch mortar, model of 1912, 3.770 cubic inches, using the same weight of projectile (617 pounds) and approximately the same weight of charge, the "average web" for model of 1890 is 0.0642 inch (Lot P. A. 199-1916) and for model of 1912, 0.0768 inch (Lot P. A. 198-1916).

Effect of weight of charge.—When the weight of the charge is reduced there is a corresponding decrease in both the velocity and pressure developed on combustion. Within certain limits, however, this lowered weight of charge can be effected, without sacrificing the pressure, by altering the granulation of the powder. The dimension most to be considered in this connection is the "average web." By this term is meant the mean distance which constitutes the least burning thickness from the edge of one surface to the edge of the next surface in the diametric direction. A full discussion of the dimensions of the powder grain will be found under section "green dimensions, die dimensions, dry dimensions, and web measurements." To decrease the weight of charge the average web must be decreased, but this decrease invariably causes increase in pressure with service muzzle velocity; consequently there are limitations. From an eco-

nomical standpoint the greatest efficiency is obtained when the desired muzzle velocity, with the maximum allowable pressure developed just as the projectile starts moving, is produced by the least weight of charge. From a technical standpoint the greatest efficiency, that is, the highest muzzle velocity with the same pressure, is obtained when the pressure increases as the projectile travels along the bore of the gun, until reaching a maximum at the muzzle: but in this case the powder efficiency is lowest.

Effect of weight of projectile.—The following general classification of projectiles is indicative of the various types which have been or are in service (of these the high-explosive shell, shrapnel shell, and gas shell have been used most extensively):

Solid shot, cored shot, high-explosive shell, shrapnel, canister, and gas shell.

An increased weight of projectile will result in an increased maximum pressure in the gun if the same muzzle velocity is to be maintained with the same powder, size of powder chamber, and length of travel. The maximum pressure for any gun being fixed, the use of a heavier projectile will usually require the use of a slower powder, and if the increase in weight is very great it will require an increase in the size of the powder chamber, or in the length of the gun, or in both dimensions.—(Tschappat, p. 518.)

Of two projectiles fired with the same initial velocity and elevation, the projectile with the greater sectional density will therefore lose its velocity more slowly and will attain a greater range. For any given range it will be subjected for a less time to the action of gravity and other deviating causes and will therefore have a flatter trajectory and greater accuracy.

The advantages of increased sectional density are therefore increased range, greater accuracy, and a flatter trajectory.—(Tschappat, *idem*, p. 517.)

Effect of solvent on shrinkage of powder.—It has been stated that a mixture of ether-alcohol is used as a colloidizing agent or solvent for the nitrocellulose. The excess solvent which is always present is eventually dried out during the solvent recovery and the dry-house processes and used again for the manufacture of ether. Depending upon manufacturing conditions and the type of powder to be manufactured, the amount of solvent, in terms of dry weight of nitrocellulose, may vary from 80 to 105 per cent. For .30 caliber powder usually 105 per cent solvent is used; for reworked powders, 90 per cent; and for cannon powders, 100 per cent. An excess of solvent enables the powder to pass through the press more easily, but on account of the softness of the grains they will dry unevenly and often blister and split. On the other hand, too little solvent not only delays the incorporation but is likely to interfere with the perfect homogeneity of the powder.

The per cent solvent used is nearly of as much importance from the ballistic standpoint as are the dimensions of the powder grains; in fact, this percentage influences, to a great extent, these measure-

ments, for the greater the amount of solvent, the greater will be the shrinkage of the drying powder.

Effect of moisture and volatiles.—After graining, the bulk of the solvent is dried out, but 2 per cent to 8.5 per cent may remain in the powder as moisture and volatiles, or total volatiles, the amount depending upon the size of the grain. No better description of the effect of moisture and volatiles can be given than the following from Tschappat's Ordnance and Gunnery, page 115:

The alcohol used in the solvent contains 5 per cent water, which generally remains in the powder after drying. Additional water may be absorbed from the air during the process of manufacturing and handling. Recent lots of powder also contain 0.4 to 0.8 per cent of a stabilizer, and .30 caliber rifle powders contain, in addition, 1 per cent of graphite.

Smokeless powder may, therefore, be considered to be a mixture of nitrocellulose, alcohol, water, and sometimes a stabilizer and graphite. Most of the ether used is evaporated out during the drying process.

From calculations it is found that the energy per pound of pure nitrocellulose of 12.60 per cent nitrogen is 1,422,000 foot-pounds per pound. If now, an inert material, that is, one that takes no part in the reaction at combustion, is mixed with the nitrocellulose, the energy per pound of the resulting material will be less than that of pure nitrocellulose. For instance, if 0.99 pounds of pure nitrocellulose of 12.60 per cent N is mixed with 0.01 pound of inert material, the inert material will be 1 per cent of the total weight and the energy per pound of the resulting material will evidently be $1,422,000 \times 0.99 = 1,427,580$ foot-pounds per pound.

Now, of the materials entering powder as given above, water is considered as having the same effect as the same percentage of inert matter. Alcohol has a greater effect than inert matter for the reason that the carbon contained in it combines with the CO_2 resulting from the combustion of the nitrocellulose, thus forming a larger quantity of CO and a smaller quantity of CO_2 , than in the combustion of pure nitrocellulose. Theoretical considerations and practical tests indicate that the effect of 1 per cent alcohol in reducing the energy per pound of nitrocellulose is equal to the effect of 2.5 per cent inert matter.

In the same way the effect of 1 per cent stabilizer, which is higher in carbon content than alcohol, is shown to be equal to the effect of 4 per cent inert matter. Graphite, though entirely carbon, does not readily take part in the reaction and, therefore, the effect of 1 per cent graphite in reducing the energy per pound of nitrocellulose is considered equal to that of 2.5 per cent inert matter.

Consequently, the granulation of the powder must be so calculated that it will counteract the reduction of the energy of the powder by the solvent remaining after drying. In order to give more energy, the burning surface should be increased by diminishing the average web measurements or the size of the grain, or by changing the form of the grain.

Effect of methods of drying.—The methods of drying which have been previously described in the process of manufacture affect both the ballistics and the stability of a powder.

In the discussion of the alcohol dry system, mention was made of the fact that the strength of the alcohol used influences, to a marked degree, the shrinkage of the powder. This shrinkage, however, can be regulated by varying the relative percentages of alcohol and water used in the process. While there is a tendency toward a greater shrinkage with alcohol-dried powder than with water-dried powder, the experiments at the present time seem to indicate that this factor will be easily controlled, since air-dried powders show the least amount of shrinkage. It is obvious that a larger allowance in measurements should be made for the powder which has the greatest shrinkage and, therefore, the die dimensions of the air-dried powders should be correspondingly smaller than those for the "water-dry" or "alcohol-dry" powders.

In considering the length of the powder grain in reference to its diameter it is known that if the green length is more than 1.875 times the green diameter, the grain will warp excessively and dry unevenly.

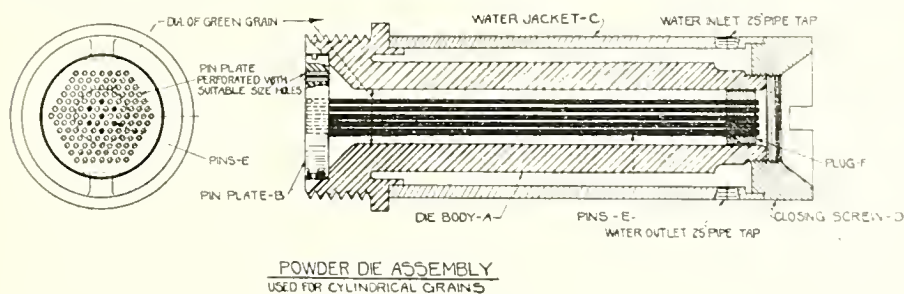


PLATE 28.

On this account and in order that the grain may serve for convenient building into charges, as well as other factors, its length is limited. The requirement of prompt ignition throughout the length of the grain also limits this dimension, and by allowing 8 per cent shrinkage in length, and 30 per cent shrinkage in diameter, this will make the length of the dry grain a little less than two and one-half times the diameter. The per cent increase allowed should increase two-thirds per cent for every per cent increase in solvent.

Before designing the dimensions of the multiperforated, single perforated and sliverless grains, it will be necessary to understand the following terms: Green dimensions, die dimensions, dry dimensions, and web measurements.

As the powder comes from the graining press it contains from 40 per cent to 50 per cent solvent and is called "green" because the solvent has not been extracted by the drying processes. The "green" powder has about the same dimensions as the steel die through which it has just been pressed. The die body A consists of a steel

block designed to hold the pin plate B, the water jacket C (having an inlet and outlet for water used for cooling the die while running the powder) and a closing screw D for the water jacket. The pin plate consists of a perforated plate, to which are attached the wires or pins E, which form the perforations in the grain, and the plug F, which holds the pins in place when the die is not in use. The dimensions for both the die body and pin plate are called die dimensions.

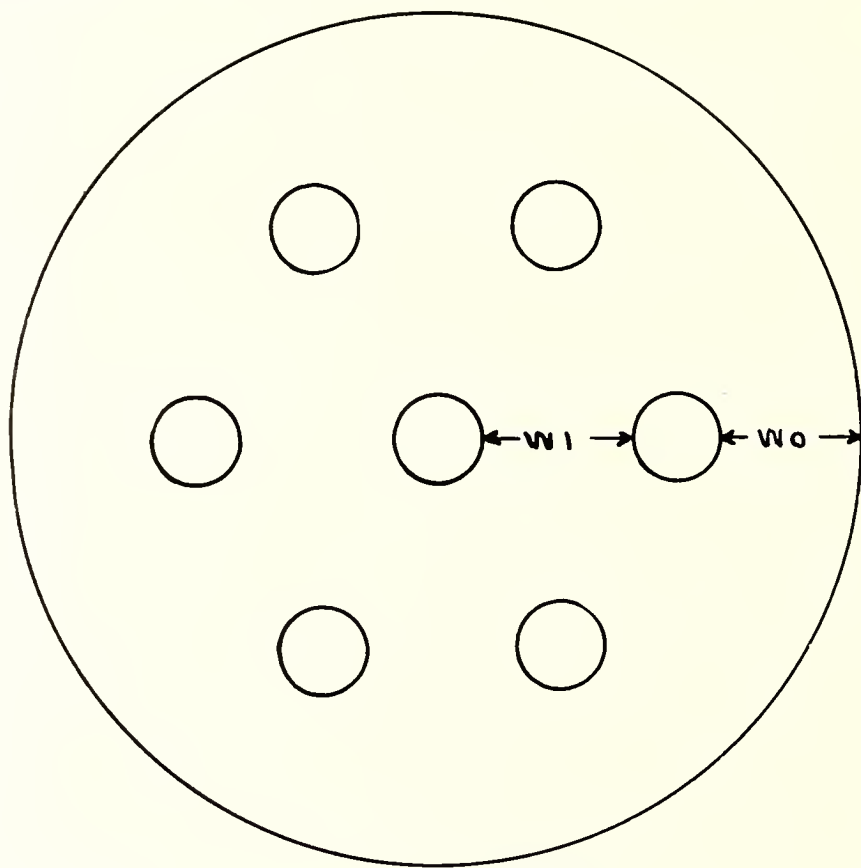


PLATE 29.— $W_a = \frac{W_i + W_o}{2}$.

It is necessary to calculate the dimensions of the die very accurately, as there are many factors which cause the measurements of the green powder to differ from those of the die. Among these factors is the spring of the pins (or needle wire) by which action the pins are drawn together as the powder is being pressed through the die, and which has the effect of decreasing the "inner web." Another factor is the consistency of the powder as it is being grained. The softer the powder, the more it will contract as it goes through the die, thus causing the green dimensions to be less than the die dimensions.

Dry dimensions.—Before the powder can be used, the solvent must be dried out so as to leave not over 8.5 per cent for the largest granulations and not over 2.5 per cent for the smallest granulations. The percentage of solvent is first reduced by the solvent recovery process and finally by placing the powder in dry houses for a period of from 15 days for .30 caliber powder to three months or more for 16-inch powder. The powder is then blended and samples are taken for measurements and other tests. The measurements taken from the dry finished grain are called dry dimensions.

Web.—By the web of a powder grain is meant the minimum burning thickness, or the distance from the edge of one surface to the next surface in the diametric direction. There are three of these measurements: "Outer web," "inner web," and "average web." The outer web is the distance from the circumference of the grain to the nearest edge of the outer perforation. The inner web, found only in multiperforated grains, is the distance between the inner edge of the perforation midway between the center and the circumference, and the nearest edge of the central perforation. The average web is found by adding two inner webs, two outer webs, and dividing by four. The symbol used for outer web is W_o , for inner web W_i , and for average web W_a . The average web is given as a basis for all other computations, and the purpose of the following calculations is to indicate the procedure used in computing the measurements for a die, from a standard average web measurement.


To calculate an entirely new average web for the powder of a new gun requires a knowledge of interior ballistics and explosive theories, which is not within the scope of this book. An excellent and detailed explanation for calculating a new powder is given in Tschappat's *Ordnance and Gunnery*, Chapter IV.

The calculation of the average web, which will be discussed, involves merely the change of the die measurements which may be made in order to conform to the different processes of manufacture, and to create better ballistic results for a new lot of powder.

Perforation.—The perforation or pinhole of a powder grain is the hole in both single and multiperforated powders made by the needle wire of the pin plate. The diameter is always the required measurement of the perforation and is expressed by the symbol "d."

Diameter.—The capital D signifies the outside diameter of the grain, passing through its center and terminating in its circumference. In the multiperforated grain it includes three perforations and is calculated mathematically as the sum of two outer webs, two inner webs, and three times the diameter of the perforation or $D=2W_o+2W_i+3d$.

Needle wire.—Needle wire consists of steel rods, set in the pin plate as shown in the diagram, and which form the perforations in

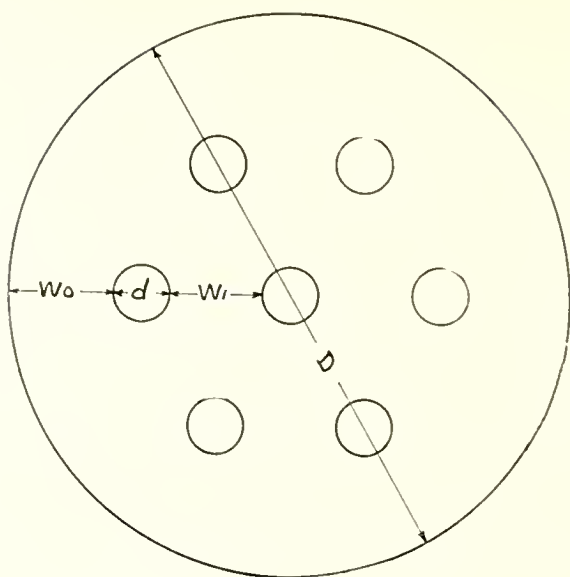


CYLINDRICAL GRAINS 7 PERFORATIONS

Dry Dimensions (Approx.)

$$D = 10d$$

$$W_o = W_i + 5\% W_i$$

$$W_a = \frac{W_o + W_i}{2}$$

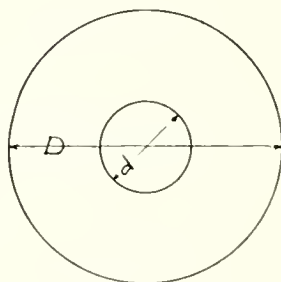 D = outside diameter d = diameter of perforation W_o = outer web W_i = inner web

CYLINDRICAL GRAIN SINGLE PERFORATION

Dry Dimension, $D = 3d$ D = outside diameter d = diameter of perforation

the powder as it issues from the die head. There are standard sizes of needle wire usually kept in stock at the factories, and the calculations of the die can be made to conform to the standard needle wire.

Pin circle.—The pin circle is formed by drawing a circle through the center of the six outer perforations. The diameter of the pin circle is calculated as the sum of the two inner webs and the two diameters of the perforation. This equals $2W_i + 2d$. The pin plates are classified according to the diameters of the pin circles.

Slope of cone.—The powder is pressed through the die at a given angle and it depends on the consistency of the colloid whether the powder should be fed to the press slowly or quickly; for cannon

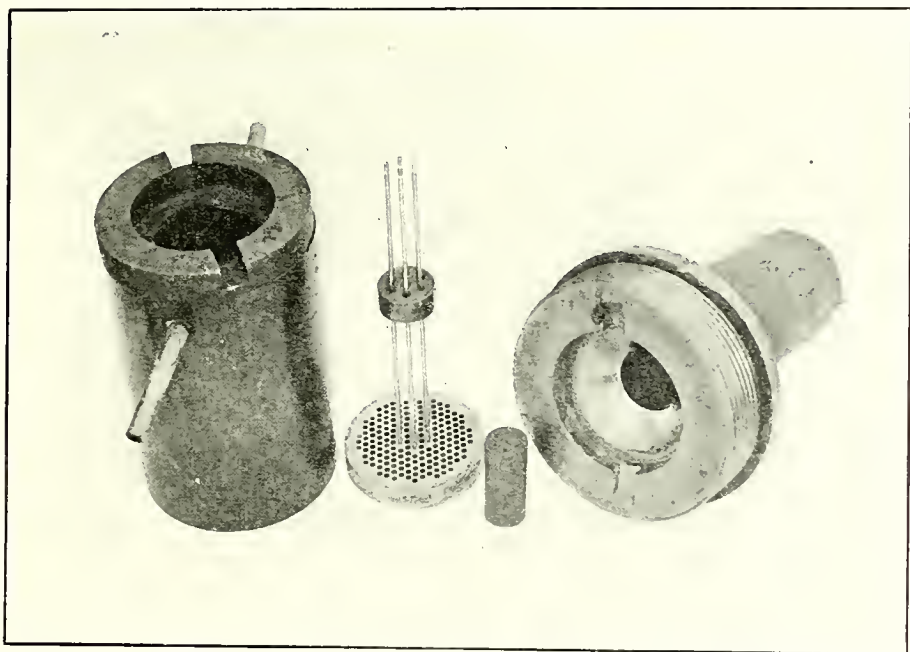


PLATE 31.—DIE BODY, PIN PLATE, PLUG, WATER JACKET, WATER-JACKET HEAD, AND SMOKELESS POWDER GRAIN FOR 12-INCH GUN.

powder the angle at which the colloid enters the die should be about 45° and for small arms about 30° .

Quick powder—Slow powder.—Wise (Gunnery, J. C. Wise, Johnson Publishing Co., Richmond, Va., 1912) gives the following definitions of quick and slow powders: "A powder with greater initial surface than the standard powder—that is, a powder of smaller granulation, will produce a greater maximum pressure and therefore will be a quick powder for the gun, and a powder of larger granulation will be a slow powder." Another factor to be considered in this connection is the percentage of "total volatiles." The higher this per cent the slower the powder, and the lower the pressure for a given density of loading; and conversely, the lower the

per cent. the quicker the powder, and the higher the pressure for a given density of loading.

Calculation of average dry web.—The basis for all calculations of powder dimensions is the average web of the dry powder. As has been pointed out, the factors affecting this dimension include the percentage of solvent and the method of drying the powder. There are relatively wide variations in practice by the different manufacturing companies—variations which are necessitated by the differences in manufacturing technique, as well as by climatic conditions. Although the maximum temperatures of air drying and water drying are specified, the contractor is given enough leeway to insure a maximum speed of drying without injury to the grain. In other words, as long as the finished powder meets the required specifications, the minute details involved in the manufacturing process are of little consequence. Each company issues a description sheet which indicates both the die and dry measurements. For determining the best average dry web, it is necessary to take the dimensions of the powders which have given the best ballistic results. This information is obtained from an examination of the firing records, charge, velocity, and pressure curves, and if these are not available, the average dry web of any accepted powder can be taken as a basis. It is the average web of the die that is difficult to calculate because that measurement takes into consideration all the processes of manufacture, such as per cent solvent used, method of drying, moisture, and volatiles, etc.

Calculation of required dry dimensions.—When the average web has been determined and complies with the standard dimensions, the next step is to determine, theoretically, the other dimensions of the dry powder—that is, the outer web, the inner web, the diameter of perforation, the outside diameter, and the length. The outer web is calculated as 5 per cent larger than the inner web. This is found by dividing the average web by 0.975 to obtain the outer web, and by dividing the average web by 1.025 to obtain the inner web measurements.

The diameter of the small perforation (d) is determined from the following formula:

$$d = \frac{4Wa}{7}$$

Theoretically, the outside diameter (D) equals ten times the diameter of the small diameter, or $D=10d$. In order to check this, another formula is used:

$$D=2Wo+2Wi+3d.$$

The length of the dry grain is calculated as two and three-eighths to two and one-half times the outside diameter (D).

The dry dimensions for a single-perforated grain are calculated differently. As there is only one web measurement, the outer web is the same as the average web and also the same as the diameter of the perforation (d). This would make the outside diameter (D) equal three times the average web, or

$$D=3d.$$

The dry-length of the single-perforated grain is equal to three times the outside diameter, or

$$L=3D.$$

Calculation of per cent shrinkage.—When all the above required dry measurements have been calculated and before the dimensions of the die can be determined, it is necessary to find the per cent of shrinkage for the average web measurement. This is very difficult to determine accurately because so many factors influence the amount of shrinkage. It has been stated that the greater the amount of solvent used the greater the shrinkage. An increase of two-thirds per cent shrinkage is allowed for every per cent increase in solvent. Air-dried powders have a smaller per cent of shrinkage than either water or alcohol dried powders. The per cent shrinkage of the multiperforated grain varies from 25 to 35 per cent. This shrinkage can also be determined by reference to the shrinkage of powder of other manufacturers, as noted on the description sheets, but care must be taken to consider the processes employed (such as solvent, drying, etc.), which also affect the shrinkage.

CHAPTER III.

STABILITY OF SMOKELESS POWDER.

The subject of stability of smokeless powder involves both safety in storage and uniformity in ballistics. In the discussion upon the purification of nitrocellulose, it was pointed out that the processes of boiling are made necessary from the fact that a pure product, or more properly, one definite nitrate, can not be prepared. The present knowledge of the cellulose molecule and of the intermediate reactions occurring during the nitration of the molecule, limits any attempt at the preparation of a single nitrate, and while the complete hydrolysis of the lower nitrates is sought in the boiling processes, there is no assurance that this reaction is the only one concerned, nor is it proven that there are not other factors influencing the speed and the completeness of the reaction. In spite of the elaborate process of purification followed out to insure the stability of the finished powder, this program is extended by incorporating in the colloid four-tenths per cent dry weight of diphenylamine.

STABILITY TESTS.

The powder is said to be stable or is said to have good stability when it passes the KI test, the 135° test, and the test in the surveillance chamber, which is maintained at a temperature of 65.5° C.

There is no test, however, of the stability of smokeless powder which is infallible, or which indicates in more than a general way the safety of the powder from the storage standpoint. The idiosyncrasies and the unreliability of the KI test are too well known to require more than passing mention. The 135° test serves as a criterion for the incomplete hydrolysis of the lower nitrates and for the presence of sulphuric esters (cellulose sulphates). Any of these are capable of giving a low test for "salmon pink." There is a good deal of discussion, however, upon the points involved, and research work projected along physico-chemical lines would throw much needed light upon this subject.

The surveillance tests of smokeless powder are unsatisfactory from the standpoint of uniformity of results and also from the standpoint of elapsed time necessary to obtain any data.

CAUSES OF INSTABILITY.

Worden points out (Nitrocellulose Industry, Worden, D. Van Nostrand Co., New York, 1911) that the stability of cellulose nitrate may be influenced by any or all of the following factors:

First. The formation during the process of nitration of sulphuric esters, which are not entirely eliminated in the subsequent purification processes.

Second. The presence of hydro- and oxy-cellulose in the cellulose before it is nitrated. This point has already been emphasized in the discussion on nitration, where it was pointed out that the over-bleaching of the raw material yielded a product relatively high in soluble cellulose.

Third. Traces of free acid.

Fourth. Traces of organic impurities, such as waxes and resins.

Fifth. The presence of fungi or other microorganisms.


Sixth. The presence of such vaguely characterized bodies as nitro-saccharoses or pectins.

STABILIZERS.

Prior to 1908 little was done from the manufacturing standpoint to standardize the methods of purification then in practice. In fact, the importance of the whole subject of stability of explosives was not recognized to the same extent as at present and consequently had not received the same consideration. In the mixing of the colloid, it was the practice to incorporate a small amount of an organic dye which served the purpose of an indicator rather than a stabilizer.

The indicator which found the widest application was rosaniline, and its adoption was due to the fact that upon the development of any marked acidity produced from the decomposition of the smokeless powder, the red color of the dye in the powder grains faded to a yellow, which fact serves to indicate the instability of the powder.

The use of diphenylamine was not general until the latter part of 1908, and its function was different from that of rosaniline, for it has the property of combining with free NO_2 . Upon the development of those free oxides of nitrogen in smokeless powder, the diphenylamine undergoes progressive nitration (Buisson, "Problems. Des Poudres," P. Juillard, Bul. Soc. Chem. 33, 1905, p. 1172), as indicated in the following series of reactions:

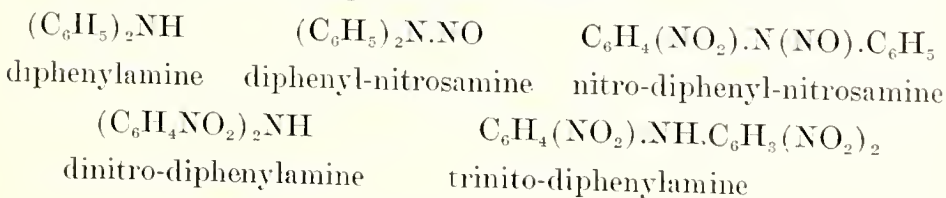

These separate substances may be detected by various quantitative and qualitative reactions, and it was formerly thought that when any of the tests applied to the powder were positive, they indicated an impaired stability. However, more recent work has indicated that nitrosodiphenylamine itself is an excellent stabilizer, so that the presence of nitrosodiphenylamine does not necessarily indicate impaired stability.

REWORKED POWDER.

The reworking of smokeless powder, which is in effect a salvaging of unstable powder, is a relatively new development in the manufacture of this propellant and is therefore experimental from many

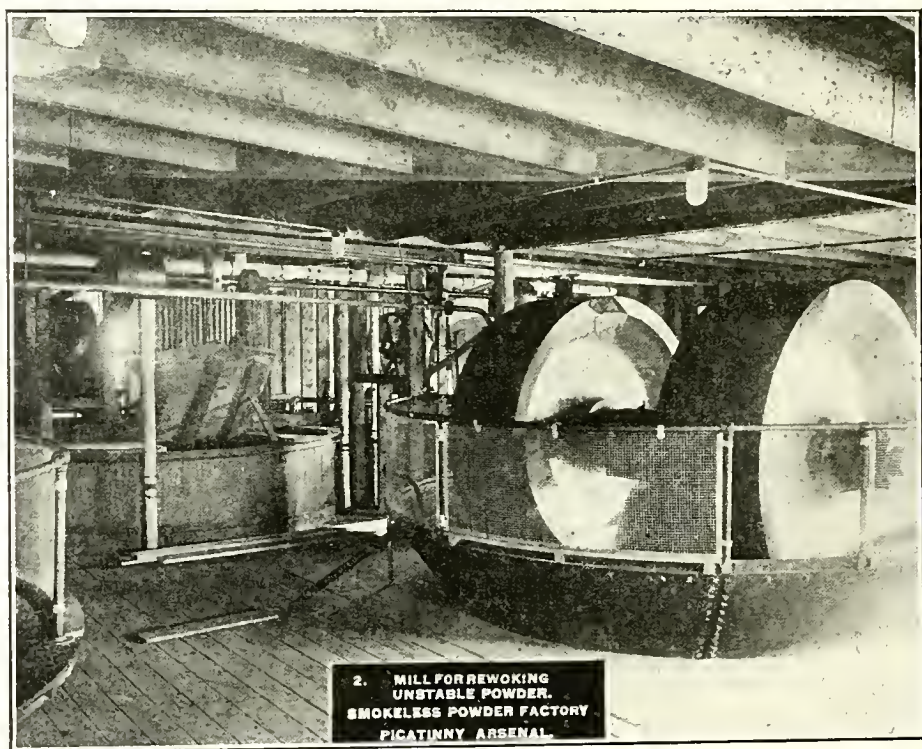


PLATE 32.

standpoints. The subject of stability is one of very prime importance when large amounts of explosive are being stored. In fact, the whole storage problem is so intimately related to stability that a consideration of the one necessarily involves the other.

When storage tests and surveillance results give warning of an approaching impaired stability of a quantity of smokeless powder, the particular lot so affected is withdrawn from general magazine storage, each powder container opened and the contents flooded with water. In the event that the lot in question is a nitroglycerin powder or a coated powder such as a graphited powder, the lot is

destroyed at the burning ground. This procedure is made necessary for the reason that it is impracticable from the standpoints of both economy and safety to rework such powders. If, however, the powder showing impaired stability is a so-called "straight nitro-cellulose" powder, the reworking can be accomplished economically and efficiently. It is necessary, however, to determine the nitrogen content in the unstable powder, for a powder whose instability has progressed to such a degree that the loss of nitrogen brings the percentage of the total nitrogen below 12.10 per cent can not be reworked to advantage. A powder failing to show at least this percentage is burned as in the case of the nitroglycerin and coated powders.

The fabrication of reworked powder differs from that of straight powder in that there are no nitrating, boiling tub, or pulping processes involved. Instead of this the powder grains are pulverized under water by a heavy steel wheel mill, weighing 5 tons, until the particles of powder are so finely comminuted that they float on the surface of the water. Powder grains may also be crushed between heavy steel rolls, or pulverized by some of the standard pulverizing and grinding equipment. In all cases, however, the powder must be wet. A discharge pipe from the mill conveys the material to a screen having a mesh of twenty-six hundredths of an inch, where the coarser particles of powder are separated out and returned to the mill for further grinding. The grinding operation is therefore of a continuous nature and more old powder is added from time to time, depending upon the hardness of the grains being worked and the speed of the mill.

After this preliminary screening the material is repurified in a manner similar to that employed in the poaching treatment of the regular pyro. The reworked pyro at this stage is very dissimilar to the regular pyro and presents many obstacles from the manufacturing standpoint. It is yellowish in color, does not respond readily to the purification treatment, is difficult of manipulation in the wringers on account of the dense cake it forms on the screen, and offers many problems in chemical analysis, especially when determining the percentage of nitrogen. In the dehydrating presses the utmost care must be exercised, for on different occasions the careless manipulation of the pressure valves has resulted in the blowing up of the press, with its attendant fire and loss of life. The dehydrated block, unlike the regular pyro, is more friable and is in fact so lacking in cohesiveness that it can not be put in the block breaker prior to the mixing operation.

Its photomicrograph also shows certain definite differences, one of the most striking being the reduction in the number and size of the fibers, thus indicating the action of the previous colloidizing operation.

It is largely due to this fact that reworked pyro granulated for 6-inch gun, model 1900, 1903, and 1905, and 75-mm. gun, model 1897, requires only 90 per cent solvent as against 100 per cent in regular pyro.

After the colloid has been formed, however, the treatment in both the factory and dry house does not differ materially from that given the regular colloid.

STORAGE OF SMOKELESS POWDER.

It has already been pointed out that the moisture and volatile content of smokeless powder is an important factor in determining the weight of charge and the pressure to be expected for the required muzzle velocity. In order that this percentage will remain constant it is necessary that the powder be stored in air-tight containers so constructed that they may be easily filled, tested, piled, and emptied. With small arms powder it is customary to line the inside of the container with a muslin bag, the object being to keep the powder entirely free from dust, chips, or other extraneous material.

The powder container consists of a wooden box, zinc lined, about 26 by 16 by 11 inches. There are two types, the so-called export type, having a capacity of 140 pounds of smokeless powder, and the other, the Picatinny Arsenal type, having a capacity of 110 pounds of smokeless powder. The cover is provided with an outside ring, locking ring, and rubber gasket, assembled in such a way that when a lever is forced down on the top of the box, tension is put upon the lug in such a manner that there is no possibility of air leaks. Each box is tested before being filled by having a small hole drilled in the cover, applying compressed air, and noting the reading on the pressure gauge attached to the air line.

The magazines for the storage of smokeless powder should be kept dry, and should be so situated that there is a minimum variation in temperature. This latter point is an important one from the standpoint of maintaining the standard moisture and volatile content. In those instances where a wide range in temperature obtains there is always the added risk of the powder containers tending to develop leaks, due to the difference in the atmospheric pressure inside and outside of the zinc boxes. The most satisfactory storage conditions are those which insure a free circulation of cool, dry air. The ventilation, therefore, of the magazine is a very important point and should be so controlled that air will not be admitted when conditions on the inside of the magazine are such that condensation of moisture within the magazine would follow. The containers should be handled the least possible number of times, and whenever such handling is necessary it should be done with the greatest of care, the ob-

ject being to obviate any possibility of air leaks being produced in the containers.

In piling, the boxes are placed on their broad side. They should not be piled closely together for the reason that such a procedure defeats a proper ventilation. When properly placed, however, they may be piled 12 high, provided the magazine space permits. The important preliminary detail of cleanliness of the magazine floor should not be overlooked, for the accumulation of dirt, rubbish, and nails, aside from being unsightly, constitutes a menace. Scrapers should be placed at the door of the magazine so that mud, cinders, gravel, or other material will be removed from the shoes before the powder is stored. Under ordinary conditions it is not necessary to wear powder shoes in the magazine, except in the case of repacking, when it is advisable that this precaution be observed.

The magazines must be so located that good drainage of the land is possible at all times. This is of special importance where large quantities of smokeless powder are being stored. In spite of the precaution observed for the elimination of leaky powder cans, the fact remains that there are many instances where the leaks are not discovered. This results, of course, in the powder in such cans absorbing moisture from the damp atmosphere in which it is stored, a condition very undesirable from the ballistic standpoint. The fire risk is not of serious consideration if the necessary precautions are observed. The danger of grass fire is practically nil if brush and undergrowth are removed from a distance of 50 feet around the building. The carrying of matches or flash-producing devices of any kind should be strictly prohibited. This rule may be enforced by having those employees associated with the storage depot searched for matches in their clothes at irregular intervals. Smoking, of course, should be absolutely forbidden at all times where explosives are manufactured, tested, or stored. Oil-burning lamps, lanterns, candles, etc., should be prohibited, and in those cases where artificial light is required special storage-battery lamps only should be used, or for short inspection the ordinary dry-battery flashlight.

When it is necessary to renail boxes, nonsparking tools should be used. These consist of copper hammers, wooden mallets, copper nails, etc. The use of metal hooks for the moving of packages of high explosives or ammunition should not be permitted. When circumstances are such that it is impossible to get explosives under cover, a tarpaulin should be thrown over the exposed material, but in the event that an explosive becomes damp from inclement weather, it should be piled separately from the other explosives and a special chemical examination be made of the wet material.

Each magazine should be provided with a minimum and maximum thermometer, and careful record should be kept at all times of the

variation in temperature. Except when material is being checked in or out of the magazine, or during inventory, the building should be kept securely locked. Under no circumstances should packages of explosives or ammunition be opened within the magazine. If it is necessary to examine the material, it should be done outside of the building and far enough away so that in the event of accident the building itself would not be endangered.

Damaged packages should in every case be removed from the magazine and taken to a special repacking house before any attempt to salvage the material is made. If the damage is slight and a repacking house is not available, any repair or recoopering may be done outside at a distance not less than 100 feet from any magazine.

The transportation of explosives should be governed primarily by the rules of the Interstate Commerce Commission. These provide for the safety in transit of certain so-called acceptable explosives, provided that they comply in every way with the rules for packing and marking. Where shipment is in carload lots, each tier of boxes or containers must be carefully cleated and braced to provide against any possible misplacement through jar or shaking of the car.

CHAPTER IV.

INSPECTION OF SMOKELESS POWDER.

The foregoing consideration of the manufacture of smokeless powder emphasizes the prime importance of careful chemical supervision throughout the factory and demonstrates that standard methods of analysis are necessary if comparative results from different factories are to be of value. The purchase of the raw materials, such as cotton, acids, alcohol, and diphenylamine, is governed by specifications so designed that a uniform quality of material will be obtained. As these specifications are, necessarily, of a chemical nature, it is essential that they prescribe in detail the methods to be used in carrying out the various tests and determinations. The methods of testing described in this publication are, in general, those prescribed in the latest Ordnance Department specifications for the materials in question. In view, however, of the fact that the specifications are revised from time to time, reference should be made to the last revision of the specifications in order to obtain exact data as to approved methods.

A. TESTING OF RAW MATERIALS.

METHODS FOR ANALYSIS OF CELLULOSE.

Moisture.—Approximately 5 grams of the cellulose is weighed in a large weighing dish with ground glass stopper. The sample is heated for one and one-half hours at 105° C., cooled in a desiccator, and weighed. Loss in weight is calculated as moisture on sample taken. The dried sample is saved for determination of extractive matter.

Extractive matter.—The dried sample from the above moisture determination is placed in a Wiley or Soxhlet extractor and sufficient redistilled ethyl ether for the extraction is added. After the sample has been extracted on the steam bath for three hours the ether is transferred to a weighed beaker or evaporating dish and evaporated to dryness on a steam bath. The residue is heated for 30 minutes in an oven at 100° C., cooled in a desiccator, and weighed. From this the per cent of extractible matter, based on the dry cotton, is calculated.

Ash.—A known weight of approximately 1.5 grams of cellulose is weighed out into a tared platinum or silica crucible. The cotton

is moistened with strong nitric acid, and the crucible heated over a Bunsen burner until acid fumes disappear, finally raising to a red heat until all carbonaceous matter has been consumed. The crucible is cooled in a desiccator and weighed, and the weight of the residue calculated as percentage on the dry weight of the sample taken.

Test for overbleach.—A known sample of approximately 5 to 10 grams of the cellulose is boiled in distilled water. After filtering and concentrating the filtrate, portions of the latter are tested for chlorides, sulphates, and calcium. Barium chloride is used to detect sulphates, and silver nitrate to detect chlorides. Calcium is detected by adding oxalic acid and making alkaline with ammonia.

The material soluble in potassium hydroxide solution will be determined by heating 2 grams of cotton, previously dried at 102–105° C., in a 250 c. c. glass or porcelain beaker with 100 c. c. of the caustic potash solution (10.0 ± 0.1 per cent) for three hours at 100° C., or an equivalent strength of sodium hydroxide solution (7.14 ± 0.1 per cent). Care must be taken to avoid concentration of the solution or undue oxidation of the cotton, due to the exposure of the alkali-soaked cotton to the air. After the heating is completed the cotton and solution are poured into a beaker containing 1 liter of distilled water, the alkali is neutralized with decided excess of acetic acid. The undissolved cotton is then filtered onto a weighed Gooch crucible having an asbestos mat, and thoroughly washed successively with hot water, alcohol, and ether. It is then rapidly dried to constant weight at 102–105° C. The loss in weight is then calculated as per cent.

METHOD FOR ANALYSIS OF DIPHENYLAMINE.

Total diphenylamine.—Bromination in acetic acid solution. From 2 to 3 grams of sample is weighed into a beaker and dissolved in 25 c. c. glacial acetic acid. A solution of bromine in acetic acid (1:2) is then added a drop at a time until a distinct yellow color persists after stirring. The beaker is covered and set aside for 15 minutes at room temperature, during which time a distinct yellow color should remain. The beaker is then placed on a steam bath and heated for five minutes, at the end of which time there should be a yellow color. The beaker is set aside to cool and 150 c. c. water added. The beaker is placed on steam bath and heated till the hand can barely stand the heat and the precipitate is then filtered off and washed five or six times with hot water, and dried to constant weight. The weight of precipitate multiplied by 0.3487, divided by the weight of sample, and multiplied by 100 gives per cent of diphenylamine in original sample.

Solidification point.—A sample of about 80 to 100 grams is heated in a beaker on a steam bath until it is liquified, when about 20 grams of granular calcium chloride is added. The mixture is stirred for about 15 minutes at a temperature of 80° C. and then allowed to cool gradually to 55° C., when the liquid is poured off into the inner tube of the solidification point apparatus. The diphenylamine is remelted by placing the tube in an oven at about 90° C., and the tube then placed in the apparatus, the standard thermometer (graduated in $1/10^{\circ}$ C.) adjusted so that its bulb is approximately in the center of the molten diphenylamine. The auxiliary thermometer used for determining the amount of the stem correction is adjusted so that its bulb remains close to the standard thermometer and approximately halfway between the surface of the melted diphenylamine and the top of the mercury thread in the standard thermometer when the final temperature is reached. Stirring is continued vigorously by means of either mechanical or hand stirrer as the temperature falls, and the thermometer watched very carefully from the point where the temperature begins to rise as the heat of crystalization is liberated. The temperature should be recorded every 15 seconds until the maximum temperature is reached. This maximum, corrected for emergent mercury column and for the calibration of the thermometer itself, is taken as the solidification point.

Solubility in ether-alcohol.—A known weight of approximately 10 grams of the diphenylamine is dissolved in 200 c. c. of an ether-alcohol mixture comprising 2 parts of ethyl ether to 1 part of ethyl alcohol. The solution is filtered through a weighed Gooch crucible and the residue is washed with 5 portions of 20 c. c. each of the ether-alcohol mixture. The crucible is dried for 1 hour at 100° C., cooled for 20 minutes in a desiccator, and weighed.

Aniline hydrochloride.—A known weight, approximately 10 grams, of diphenylamine is boiled with 50 c. c. of water for about ten minutes. After cooling until the diphenylamine solidifies, the water is filtered into a beaker and the diphenylamine washed with approximately 50 c. c. of water at a temperature of about 50° C. The filtrate is evaporated to a volume less than 10 c. c. and transferred to an ordinary test tube which has been marked at the points where it contains 10 and 10.5 c. c. The solution is slightly acidified with nitric acid, diluted with water to a volume of from 10 to 10.5 c. c., and 0.5 c. c. of a 10 per cent solution of silver nitrate added. A greater degree of turbidity should not develop than is obtained when 0.3 c. c. of N/10 HCl is added to 10 c. c. of water slightly

acidified with nitric acid and silver nitrate solution added as above described. This indicates a content of 0.02 per cent aniline hydrochloride. All reagents and water must be free from chlorides.

Aniline.—Approximately 1 gram of finely ground diphenylamine is stirred for 10 minutes in 20 c. c. of a filtered cold saturated solution of calcium hypochlorite. A violet coloration is evidence of the presence of aniline.

Reaction.—A known weight of approximately 10 grams of the sample is melted and shaken with 100 c. c. of neutral boiled water at approximately 80° C. and allowed to cool. The water is poured off and the sample is treated a second time in the same manner with 50 c. c. of water. The total water extract is cooled and tested with a standard neutral litmus paper. The litmus paper must not be turned red. If the color remains unchanged, indicating neutrality of the sample, no further test is necessary, but if the water is found to be alkaline the sample should be titrated against N/50 hydrochloric acid, using methyl red as an indicator. The sensitiveness of the litmus paper is considered to be sufficiently delicate if it shows a definite reddish coloration on being immersed in 100 c. c. distilled water containing 1 c. c. N/1000 HCl or H₂SO₄.

METHOD FOR ANALYSIS OF MIXED ACIDS.

The analysis of mixed acids involves the following operations:

1. Titration with N/10 NaOH for total acidity.
2. Determination of total HNO₃ by nitrometer.
3. Evaporation of HNO₃ and titration of the residue for total H₂SO₄.
4. Titration with N/10 KMnO₄ for oxides of nitrogen.
5. Specific gravity.

By calculation the values obtained in the above operations are reported as:

1. Total H₂SO₄.
2. Available HNO₃.
3. Total N₂O₄.
4. H₂O.

The details of the operations and calculation are described below:

1. *Total acidity.*—A sample of approximately 1 gram is run from a Lange acid pipette into a 500 c. c. beaker containing 150 to 175 c. c. of standard N/10 NaOH. 3 to 4 drops of methyl orange indicator are added and the titration completed with the standard alkali.

Correction for burette reading: 0.01 c. c. is added for each 35 c. c. of NaOH used for each degree centigrade below the temperature at which the solution was standardized, and subtracted for each degree centigrade above this temperature.

The total acidity is calculated as per cent H_2SO_4 . For this calculation is used the formula—

$$\text{Per cent } \text{H}_2\text{SO}_4 = \frac{n \times f}{S}$$

in which

n = number of c. c. (corrected) of N/10 NaOH used to titrate.

f = factor to convert standard N/10 NaOH to H_2SO_4 .

S = weight of sample taken.

2. *Total HNO_3* .—The Du Pont nitrometer is used for this determination. The weight of sample used should be about 2 grams for spent acid, 1.2 grams for mixed acid, and 0.8 to 0.9 grams for fortifying acid. The nitrometer reading divided by the weight of sample taken multiplied by 4.49807 ($\text{Log.} = 0.65303$) gives per cent HNO_3 .

3. *Total H_2SO_4* .—The total HNO_3 found by the nitrometer is converted to H_2SO_4 by multiplying by 0.77814 ($\text{Log.} = 0.89106$). This is subtracted from the total acidity as H_2SO_4 . The remainder is total H_2SO_4 . As a check on this figure the following determination should be made:

A sample of about 2 grams of mixed acid is run from a Lunge pipette into a porcelain or silica evaporating dish. The dish is placed on the small hole of the steam bath and is allowed to evaporate for one hour with good pressure of steam. One c. c. of water is then added, drop by drop, carefully avoiding any spurting. The dish is tilted from side to side to cause a flow of the liquid over the whole surface, and the evaporation continued for one-half hour. Another 1 c. c. of water is then added and the operation is repeated. This treatment serves to break up the nitrosulphuric acid present, liberating the oxides which evaporate with the water.

The contents of the dish are carefully transferred to a 400 c. c. beaker containing 150 to 175 c. c. of N/10 NaOH and titrated exactly as described under total acidity. The acidity is calculated as H_2SO_4 by the formula given above.

4. *Oxides of nitrogen*.—About 200 c. c. of distilled water is placed in a 400 c. c. beaker and colored slightly with a small drop of N/5 KMnO_4 . About 10 grams of acid are run into the water from a Lunge pipette, using a short piece of glass tubing connected to the tip of the pipette by a very short piece of rubber tubing and dipping below the surface of the water. When the sample has been added the additional tubing should be disconnected and dropped into the beaker. The solution is titrated with N/5 KMnO_4 until a pink color persists for 10 minutes. The bulk of the KMnO_4 solution may be added at once and gradual additions are then made as the color fades. A point will finally be reached when the color fades very rapidly, having just before this time persisted for several minutes with the addition of 1 or 2 drops of solution. Beyond this point

about one-tenth of the total amount used is required to complete the titration. It is unnecessary to make corrections for slight errors in the burette readings or for temperature, as a considerable error is necessary to affect results.

The percentage of N_2O_4 is calculated from the volume of $KMnO_4$ used and converted to its equivalent in HNO_3 . This equivalent in HNO_3 is subtracted from the total HNO_3 obtained in paragraph 2. The difference is actual HNO_3 .

The actual HNO_3 plus one-half the N_2O_4 calculated as HNO_3 is available HNO_3 .

Formula for calculations:

$$\text{Per cent } N_2O_4 = \frac{n \times f}{S}$$

in which

n =number of c. c. of $N/5$ $KMnO_4$ used to titrate.

f =factor for converting to N_2O_4

S =weight of sample taken.

To convert N_2O_4 to its equivalent in HNO_3 , the amount of N_2O_4 is multiplied by 1.36966 ($\text{Log.}=0.13661$).

5. *Water*.—This is calculated by difference. The sum of the percentages of H_2SO_4 , HNO_3 , and N_2O_4 subtracted from 100 per cent is taken as water.

Standardization of solutions.— $NaOH$: This is made approximately tenth normal. A large carboy is filled with distilled water which has previously been boiled to remove CO_2 and cooled in running water. To a portion of this water is added a nearly saturated solution of very pure sodium hydroxide in such an amount that approximately four grams of sodium hydroxide will be present in each liter of the final solution. This nearly saturated solution of sodium hydroxide is prepared by taking equal weights of fused sticks of C. P. sodium hydroxide and distilled water and allowing the solution to stand for several days. By this means practically all the sodium carbonate which was present in the original sticks of sodium hydroxide will fall to the bottom of the solution. Sodium carbonate is quite insoluble in a nearly saturated solution of sodium hydroxide. The solution of sodium hydroxide thus freed from sodium carbonate is added in the proper quantity to make a 1/10 normal solution with the water in the carboy. The solution is mixed by blowing air through it which has been freed from CO_2 by passing it through a wash bottle of strong caustic solution. The mixing should be continued for about two hours. If the container is not too large, it may be mixed by shaking by hand. When thoroughly mixed, the container is set in its place and connected with a wash bottle containing strong $NaOH$ solution to protect it from the CO_2 of the air.

The solution so prepared should be standardized carefully at least once a week against $N/10$ H_2SO_4 and HCl . A standard H_2SO_4 of about 90 per cent strength may be kept in a double-sealed bottle in a desiccator and the standard alkali titrated once a month against a weighed sample of this acid.

The values for the standard acid solutions should be based on gravimetric results. The standard $N/10$ H_2SO_4 and HCl should be standardized by the following methods:

For $N/10$ H_2SO_4 : The standardization should be carried out at $25^\circ C.$ or corrections made of 0.01 c. c. per $^\circ C.$ for each 35 c. c. above or below $25^\circ C.$ Duplicate determinations are made, using 50 c. c. for each determination. The sample is diluted to 200 c. c. and a few drops of dilute HCl are added. After heating to boiling 7 to 8 c. c. of 10 per cent $BaCl_2$ solution are added slowly with stirring. The boiling is continued a few minutes. The beaker is placed on a steam bath until the precipitate becomes granular and settles to the bottom, leaving a clear solution. It is filtered while hot through a Gooch crucible containing a mat of acid-treated and ignited asbestos. The crucible is washed with hot water, dried, and ignited for one-half hour at a good red heat, then cooled in a desiccator and weighed. The weight of the precipitate of $BaSO_4$ is calculated to H_2SO_4 per liter of solution. The normality factor of the solution is found by dividing this weight by 49.045 and expressing the result to 4 places of decimals.

For $N/10$ HCl : The standardization is conducted at $25^\circ C.$ or corrections are made as for H_2SO_4 . Duplicate determinations are made, using 30 c. c. for each determination; 20 c. c. of water and a few drops of HNO_3 are added, and 6 c. c. of a fresh 10 per cent $AgNO_3$ solution are then added drop by drop with constant stirring. After precipitation is complete the sides of the beaker are washed down with a thin stream of water from a wash bottle. The beaker is heated to about $70^\circ C.$, with constant stirring, and set away in a dark place over night. On the following day the mixture is filtered through a "white-ribbon" S. & S. filter paper and washed with warm water slightly acidified with HNO_3 until all trace of $AgNO_3$ is removed. The filter and precipitate are dried at $100^\circ C.$, the precipitate transferred to a glazed paper, and the filter paper ignited in a weighed porcelain crucible. After the carbon has been burned off, a drop or two of HNO_3 and HCl are added, evaporated to dryness, the precipitate transferred to a crucible, heated to incipient fusion, cooled in a desiccator and weighed. The weight of $AgCl$ is calculated to HCl per liter of solution. The normality factor of the solution is found by dividing this weight by 36.47 and expressing the result to 4 places of decimals.

If it is desired, a Gooch crucible with an asbestos mat may be substituted for the filter paper if the mat is thick and compact, and the operator can check results by this method with those by the method described above.

METHOD FOR TESTING ETHYL ALCOHOL.

Ethyl alcohol content (by specific gravity).—The specific gravity of ethyl alcohol is determined at 20° C. by means of a Westphal balance or a U. S. Standard hydrometer, calibrated to read the density at 20° C. in terms of the density at 40° C. The percentage of absolute ethyl alcohol by weight is then found by reference to the tables given in "Official and Tentative Methods of Analysis of the Association of Official Agricultural Chemists" (pp. 345–358), or in Circular No. 19 of the Bureau of Standards (Table No. 2).

Acidity.—Fifty c. c. of the sample of ethyl alcohol is measured by means of a graduated cylinder into an Erlenmeyer flask, and 3 to 4 drops of phenolphthalein added. The acidity is determined by titrating with approximately N/10 NaOH (or KOH).

$$\left. \begin{array}{l} \% \text{ acidity as } \\ \text{acetic acid} \end{array} \right\} = \frac{\text{c. c. NaOH soln.} \times \text{Normality factor} \times 0.006 \times 100}{50 \times \text{specific gravity of sample.}}$$

Residue on evaporation.—One hundred c. c. of the sample of ethyl alcohol is measured by means of a graduated cylinder into a weighed evaporating dish. The dish is placed on the steam bath until the alcohol has evaporated to dryness, then dried at 100° C. to constant weight. The increase in the weight of the dish gives the amount of residue per 100 c. c.

$$\% \text{ residue} = \frac{\text{wt. of residue}}{\text{Specific gravity of sample.}}$$

Aldehyde.—The following solutions are required for this test:

9 grams AgNO₃ dissolved and diluted to 100 c. c.

9 grams NaOH dissolved and diluted to 100 c. c.

NH₄OH of specific gravity 0.90.

All of these reagents should be of the quality known as Merck's Blue Label, J. T. Baker's Analyzed, or equivalent. The silver nitrate solution should be stored in a dark bottle and in a dark place.

The test is carried out by adding 1 c. c. of the NaOH solution to 1 c. c. of the AgNO₃ in a small graduated cylinder. One c. c. of the NH₄OH is added, or rather just enough to dissolve the precipitate completely. Ten c. c. of the sample of ethyl alcohol is placed in a clean clear glass-stoppered bottle to which is added 10 c. c. of distilled water and 1 c. c. of the mixture prepared in the small graduate. The bottle is shaken and allowed to stand in a dark

place for one hour. The solution is filtered and the clear filtrate tested for unreacted silver by adding 1 c. c. of a 10 per cent solution of sodium chloride. If any precipitate, as judged by the cloudiness of the liquid, is found the alcohol is considered as containing less than the allowable amount of aldehyde.

METHOD OF TESTING ETHER.

Specific gravity.—The specific gravity is determined by the Westphal balance.

Acidity.—Fifty c. c. of alcohol is measured into an Erlenmeyer flask, three drops phenolphthalein solution added and N/100 KOH added drop by drop, with stirring, until a faint pink color persists. Then 50 c. c. of ether is added and the mixture titrated again to faint pink. The acidity is calculated as acetic acid by the formula:


$$\left. \begin{array}{l} \text{Per cent acidity as} \\ \text{acetic acid} \end{array} \right\} = \frac{\text{c. c. KOH} \times \text{normality factor} \times 0.006 \times 100}{50 \times \text{specific gravity of sample}}$$

DU PONT NITROMETER.

Theoretical.—The Du Pont nitrometer is a modification of the Lunge nitrometer and is devised to avoid the necessity of making the usual correction for temperature and barometric pressure which must be calculated with every gas measurement. The principle of the apparatus is to inclose a known volume of air at such a pressure that it takes up exactly the volume which it would occupy at 20° C. and 760 mm. pressure. If the same pressure and temperature are then applied to another volume of gas this will also take up the volume which it would occupy at 20° C. and 760 mm. pressure. The volume of air is kept in a "compensating tube" which is in connection with the reading tube of the nitrometer. When it is desired to read the volume of a given quantity of NO gas at 20° C. and 760 mm. pressure, the level of the mercury in the "compensating tube" is brought to the mark at which the air within the tube occupies the space it would occupy at 20° C. and 760 mm. pressure, the level of the mercury in the reading tube is brought on a level with this same mark and the reading made. The reading tube on the Du Pont nitrometer is graduated to read directly to per cent of nitrogen when a 1 gram sample is used.

To set up a Du Pont nitrometer.—The various tubes are arranged on the nitrometer rack in order shown in the accompanying sketch: 25 c. c. of 95 to 96 per cent H₂SO₄ is then placed in No. 2 and a quantity of air drawn in through the stopcock. The stopcock is then closed and the bulb shaken vigorously to dry the air. The shaking is repeated several times at intervals of from 10 to 15 min-

ntes. When the air is judged to be thoroughly dry, 2 and 4 are connected and the dry air run into 4 until, with the stopcock of 3 open and the mercury in 3, 4, and 5, on the same level, the reading in 3 is about 12.50. No. 4 is then sealed with a small blowpipe flame. Another portion of air is then desiccated in 2 and transferred to 3 until, with the mercury in 3, 4, and 5 on the same level, the reading in 3 is about 12.50. It is not necessary that these gas volumes be

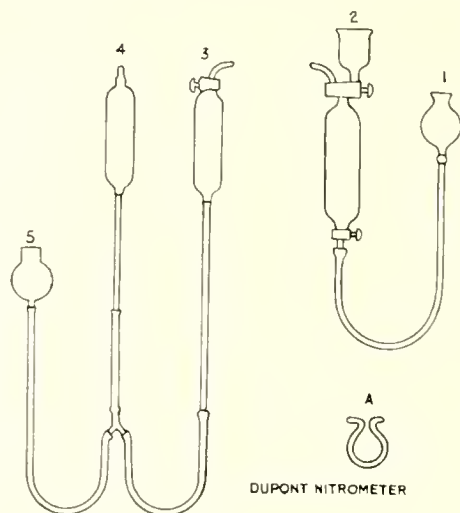

exact or equal. The small manometer, A, is then filled with H_2SO_4 and attached to 3. The apparatus is then left to come to constant temperature. The mercury in 3, 4, and 5 is then adjusted so that the air in 3 is under atmospheric pressure as shown by the acid in A. The reading is taken on the graduated scale on 3. The temperature and barometric pressure are noted at the same time. From these readings the volume of air in 3 is calculated at 20°C . and 760 mm. pressure by the gas laws which are expressed by the equation:

$$\begin{aligned} V:V' &= P':P \\ V:V' &= T:T' \end{aligned}$$

in which

V = volume at 20°C . and 760 mm.

V' = volume at the observed temperature T' and pressure P' .

From these is derived the equation:

$$V = V' \frac{p' \times 293}{760 \times (273 + T')} \times \frac{1 - (0.00018t')}{1 - (0.00018 \times 20)}$$

The last term of the equation represents the correction to be applied for the coefficient of expansion of mercury in the barometer where t' equals temperature of the barometer. When V has been calculated, the mercury in 3, 4, and 5 is adjusted so that, with the

mercury in 3 and 4 on a level, the mercury in 3 marks the calculated volume of air. The height of the mercury in 4 is then marked by a strip of paper pasted on the tube. This is taken as the standard volume with which every volume of gas to be measured is compared.

Standardization with C. P. KNO_3 .—A sample of C. P. KNO_3 which has been recrystallized three times from alcohol, is finely ground and dried for one and one-half to three hours at 150°C . Exactly 1 gram is weighed out into a small weighing bottle and transferred to the nitrometer (for details see "Determination of nitrogen"). dissolving the KNO_3 in the nitrometer cup with 20 c. c. 95 per cent plus or minus 0.3 per cent H_2SO_4 . With the lower stopcock of the generating bulb open and the mercury bulb low enough to give a reduced pressure in 2, the generating bulb is gently shaken until the larger portion of gas has been generated. The generating bulb is then raised until the mercury drops nearly to the lower shoulder, the lower stopcock closed and the bulb is shaken vigorously for three minutes. After replacing on the rack, the lower cock is opened and the bulb allowed to stand for several minutes. The shaking is then repeated for an additional three minutes, adjusting the mercury as before. Finally the gas is transferred to 3, the positions of 3, 4, and 5 so adjusted that the level of mercury in 3 and 4 is about the same and the apparatus allowed to stand 20 minutes. The mercury levels are then carefully adjusted with a leveling device and the reading in 3 taken. This should be 13.85 per cent.

Standardization by a test blend.—This standardization is run in a way similar to the above except that a blend of nitrocellulose which has been carefully tested on a standardized nitrometer is used. This method is somewhat more convenient than the method with KNO_3 because the nitrocellulose is more easily broken up in the nitrometer than KNO_3 . Whenever a doubt exists, however, the standardization must be carried out with KNO_3 .

B. TESTING OF NITROCELLULOSE.

Ether-alcohol-insoluble material.—The percentage of ether-alcohol-insoluble material in nitrocellulose may be determined as follows: One gram of the dry sample is soaked for two hours in 50 c. c. of 95 per cent alcohol in an Erlenmeyer flask. After adding 100 c. c. of ethyl ether, the mixture is shaken and allowed to stand overnight. On the following morning the mixture is shaken thoroughly and transferred with washing by 80-100 c. c. of fresh ether-alcohol mixture (2:1) to a specially constructed solubility tube of the following dimensions: Total length, 21 inches; inside diameter, 1.35 inches; the lower end constricted for a distance of 2 inches to an inside diameter of 0.3 inch and graduated in one-tenth

c. c. to 10 c. c. The constricted portion should be tapered gradually from the large part of the tube and the graduations should extend to the top of the shoulder thus formed. After standing for seven hours in the solubility tube the volume occupied by the insoluble and semisoluble matter is read in c. c. from the scale on the tube. This number (of c. c.) multiplied by 0.5 is the percentage of ether-alcohol-insoluble matter as noted in the specifications for smokeless powder.

The official temperature for this determination shall be 15.5° C. and in case of doubt or for greater accuracy the complete determination shall be made at this temperature, the solvents being brought to this temperature before their addition to the sample. The insoluble material should not exceed 5 per cent.

Heat test 65.5° C. with potassium-iodide starch paper.—The sample shall be pressed in a clean cloth or wrung in a wringer if it contains a large excess of water. The cake shall be rubbed up in a cloth until fine, taking care that it does not come in contact with the hands, spread out on clean paper trays and dried in an air bath at 35° to 43° C. just a sufficient length of time to reduce the moisture to that amount which will give a minimum heat test, this amount being from 1.5 to 2 per cent.

During this time the tray is taken out several times and the nitrocellulose is "rubbed up" with a piece of tissue paper spread over the back of the fingers. When the nitrocellulose begins to stick to the tissue paper, due to static electricity which is developed when dry nitrocellulose is rubbed, take a sample of 1.3 grams and put in KI starch test tube, shaking it down to occupy about $1\frac{1}{2}$ inches in the tube. These tubes for this test are standard $5\frac{1}{2}$ inches long, one-half inch internal diameter, and five-eighths inch external diameter, closed by a clean cork stopper fitting tightly, through which passes a tight fitting glass rod with platinum holder for the paper. The drying and rubbing are continued, taking samples at appropriate intervals of two to five minutes until the sample on the tray is completely dry and five samples have been collected. This series of samples is called the "moisture series" and is taken in order that samples may be run containing varying percentages of moisture.

If, as sometimes happens in dry weather, the moisture has been reduced to less than 1.5 per cent, the sample shall be placed in a moist atmosphere for a time not exceeding two hours until the required moisture percentage is obtained. The whole time of drying and making the test shall not exceed eight hours.

When these five samples have been collected they are prepared for the test as follows: A clean, fresh cork stopper is selected which just fits the tube. A perforation is made, through which is introduced a short length of closed glass tube into the lower end of which

a small piece of platinum wire has been fused. The platinum wire is cleaned by holding in a flame. A strip of KI starch paper 1 inch in length, three-eighths inch wide, is fastened to the wire. This should not be touched with the fingers. The upper portion of the test paper is then moistened by touching it with a glass rod which has been dipped into a solution composed of one part pure glycerin and one part distilled water. The stoppers so prepared are fitted into the test tubes containing the samples to be tested. The five tubes are immersed in the specially prepared heating bath, which is kept at a temperature of $65.5^{\circ}\text{C.} \pm 1^{\circ}\text{C.}$ The appearance of the first faint yellow line at the lower edge of the moistened portion of the test paper is carefully noted. This discoloration is to be greater than that obtained at the same time by a blank test. The tube giving this color first is taken as the test for the lot. This time shall be not less than 35 minutes.

Standard test papers will be used and will be furnished by the department to manufacturers.

The standard water bath holds 10 tubes and is made long and narrow to reduce to a minimum the upper portions of the tubes. These tubes are immersed in the bath to a standard depth of 2.25 inches.

Test at 135°C. —A sample of nitrocellulose is laid out in paper trays and dried for four or five hours at 42°C. , or is dried overnight at room temperature and then further dried one-half hour at 42°C. , after which 2.5 grams are pressed into the lower 2 inches of each of two tubes of heavy glass, about 290 mm. long, 18 mm. outside diameter, and 15 mm. inside diameter, closed with a cork stopper through which a hole 4 mm. in diameter has been bored. A piece of standard normal methyl violet paper, 70 mm. long and 20 mm. wide, is placed in each tube, its lower edge 25 mm. above the cotton. When the constant temperature bath has been carefully regulated at 134.5°C. , plus or minus 0.5°C. , these tubes are placed in the bath so that not more than 6 or 7 mm. of length projects from bath. Examination of the tube is made each five minutes after 20 minutes have elapsed by withdrawing about one-half its length and replacing quickly. When salmon pink is obtained between examinations, after 25 minutes and before 30 minutes, a 30-minute record shall be allowed the sample. The methyl violet test paper in either tube shall not be completely turned to standard salmon pink in less than 30 minutes.

The test is continued for five hours and no explosion should occur in that time.

The bath must be placed in a good light with a suitable background.

There shall be no failure of either of the tubes.

The standard normal methyl violet papers will be furnished by the department.

Determination of nitrogen.—A sample of approximately 1 gram is taken. This is weighed in a small weighing bottle, dried one and one-half hours at 100° C., cooled in a desiccator, reweighed and transferred to the cup of the nitrometer. Twenty c. c. of 95 per cent plus or minus 0.3 per cent H_2SO_4 are measured out. A portion of it is poured into the cup and the nitrocellulose washed into the generating bulb. The weighing bottle is rinsed with successive portions of acid, pouring the acid into the nitrometer cup each time and running it into the bulb. If the nitrocellulose is very dusty, it is best to dissolve it in the weighing bottle before transferring. Each successive portion of acid poured into the cup should be directed by means of a small stirring rod so that it rinses down the sides of the cup. When all is in the bulb, the NO gas is generated just as described under standardization. The gas is transferred to the measuring tube and the reading taken after standing 10 or 15 minutes. The reading is corrected for the sample, above or below 1 gram, the result being the percentage of nitrogen in the sample. If exactly 1 gram of sample is employed no correction is necessary.

Ash.—Approximately 1 gram of sample is weighed in a tared crucible, moistened with a small quantity of concentrated nitric acid, and digested for two or three hours on the steam bath. The crucible is then placed on a triangle and heated with a Bunsen burner, very cautiously at first to avoid loss. The crucible is finally placed in an inclined position, partly covered with lid and heated strongly over the blue flame of a Bunsen burner until all carbonaceous matter has disappeared. After cooling in a desiccator the crucible is weighed.

Acetone insoluble material.—This (heretofore-called "organic residue") is obtained by dissolving 1 gram of nitrocellulose in 100 c. c. of pure acetone in an Erlenmeyer flask and then transferring to a "solubility tube" which is described in paragraph headed "Ether-alcohol-insoluble material" and continuing as prescribed in that paragraph.

C. TESTING OF SMOKELESS POWDER.

Ten normal grains will be taken and both ends cut off at right angles to the length until—

$$\frac{\text{diameter}}{\text{length}} = 1.$$

These pieces are accurately measured for length and then slowly compressed between parallel surfaces until the first crack appears. The pressure is then removed and the grain again measured. The decrease in length necessary to crack the grain is calculated to per

cent of original length. The average compression must not be below 35 per cent. In case of failure in this test 20 more grains are tested, and if the average compression of the total 30 grains is below 35 per cent the powder will be rejected. Grains accidentally abnormal in shape or containing obvious flaws will not be used for this test.

Gravimetric density.—The amount of powder required to fill a box exactly 1 foot in every dimension, inside measurements, is weighed accurately. The weight is reported as pounds and decimal fraction of pound.

Specific gravity.—For 3-inch field gun and smaller calibers, specific gravity is determined by the following method: An accurately weighed sample of 15 to 20 grams, consisting of whole grains, is placed in a standardized specific gravity bottle, covered with boiled distilled water and held under a vacuum not less than 500 mm. until all air is displaced or approximately 20 minutes. The bottle is filled with boiled distilled water at 15.5° C. and weighed. The weight of the bottle plus powder is subtracted from the weight of the bottle plus powder plus water. This gives the weight of water in the bottle. The difference between this weight and the weight of water in the bottle when it was first weighed with the sample of powder represents the weight of water displaced by the powder.

Measurements.—Thirty grains will be selected at random and measured for length, diameter, perforation, and (inner and outer thickness) webs.

For grains having seven perforations the outside diameter (D) of the grain shall be about 10 times the diameter (d) of the perforations, and the length (L) from 2.1 to 2.5 times the outside diameter. For grains having a single perforation the outside diameter (D) shall be about three times the diameter (d) of the perforation, and the length (L) about three times the outside diameter. The dimensions (L and D) of at least 30 grains specified must comply with the requirements for uniformity as per table.

Dimensions.	Mean variation of individual dimensions from mean dimensions, expressed in per cent of mean dimensions.	
	Permitted.	Desired less than—
L.....	5.0	1.0
D.....	2.5	0.5

For grains having seven perforations six measurements of the outside-web thickness (Wo) and of the inside-web thickness (Wi) will be made from the six outside holes for each of the 30 grains, and the

two sets of 180 measurement will be averaged to obtain the mean outside and inside webs. The powder shall have the inside-web thickness as nearly as practicable about 5 per cent less than the outside-web thickness. The outside-web thickness may exceed the inside-web thickness by 15 per cent and may be less than the inside-web thickness by 5 per cent. The percentages are calculated on the average web thickness.

For grains having a single perforation the greatest and least web measurements of each of the 30 grains are taken. Neither the average of the 30 least measurements nor the average of the 30 greatest measurements should differ more than 15 per cent from the average of the entire 60 measurements, which is the average web of the powder.

Approximately one-third the length of each powder grain is cut from each end of 30 grains. The remaining one-third of the grain or middle portion of the original grain is "faced" and the end surfaces made exactly parallel. Care must be taken to have clean perforations and edges. A microscope having a micrometer stage attachment is used for obtaining the measurements.

The grains are measured three times across for seven-perforation powder and once across for single-perforation grains.

The number of measurements taken on seven-perforated powder is therefore as follows:

Three measurements of diameter (D): six measurements of outside-web thickness (Wo): six measurements of inside-web thickness (Wi): three measurements of the center hole are taken on each of the 30 grains and six measurements of other perforations on the same number of grains.

Determination of moisture and volatiles.—At least 10 grains are selected and several thin shavings are chipped from each grain, discarding the end portion. If the powder is too small to chip conveniently, whole grains may be used. The chipping should be done as rapidly as possible and chips dropped quickly into a weighing bottle to avoid loss of volatiles from the freshly cut surfaces. Approximately 1 gram of these chips is quickly weighed into a low form 250 c. c. "volatile beaker" which has been thoroughly cleaned, desiccated, and weighed. This weight of the beaker is used in final calculations. Fifty c. c. of redistilled alcohol and 100 c. c. of redistilled ether are added and the beaker placed under a tight bell jar until solution is complete. This usually requires one to two days. The mixture should be stirred occasionally to hasten solution. More ether should be added if much of the ether has been evaporated and solution is not yet complete. Residue determinations should be made on the ether, alcohol, and water used in the process and corrections applied to the final weight of the precipitate.

When all lumps have disappeared, the beaker is placed on the steam bath and a portion of the ether evaporated. The amount of ether that is evaporated here is very important, since it determines the nature of the nitrocellulose which is precipitated in the next step. If too little is evaporated, a fine sandy precipitate is obtained and the contents of the beaker are likely to "bump" in drying. If too much is evaporated, a gummy precipitate is obtained which can not be dried completely. A gummy precipitate should be avoided. A fine flaky precipitate will give the best results. The amount to be evaporated can be learned only by practice. Approximately $1\frac{1}{2}$ to 2 inches of solution should be in the beaker when the nitrocellulose is precipitated.

When the proper point is reached, the beaker is taken off of the steam bath and 50 c. c. of distilled water added, which precipitates the nitrocellulose. A precipitate of the proper mixture may be obtained in the determination by adhering closely to the following procedure: While still warm, 5 c. c. of distilled water is added, with stirring, from a graduate containing 50 c. c. Stirring is continued until the precipitate has been disintegrated. About 5 c. c. more water is added and above operation repeated. If the precipitate appears to be thick and heavy, about 5 c. c. of ether at a time is added with stirring until the precipitate becomes light and flaky. The remainder of the 50 c. c. of water is added slowly with constant stirring.

After precipitation is complete the beaker is replaced on the steam bath and stirred carefully until the bulk of the ether has been evaporated and there is no longer danger of "bumping." In stirring, touching the sides and bottoms of the beaker should be avoided as much as possible. When there are no longer signs of foaming, the beaker is suspended in the bath by means of specially constructed wooden blocks and allowed to evaporate to dryness. The beaker is not allowed to remain on the bath any longer than is actually necessary for drying. On removal from the bath the precipitate should be white or grayish white. A yellow or greenish yellow color indicates that the precipitate has been on the bath too long. The outside of the beaker is wiped clean and the beaker placed in the 100° C. oven for $1\frac{1}{2}$ hours. It is then transferred to a good desiccator for about 30 minutes to cool to room temperature before weighing. Before the desiccator is opened, the weights on the scale pan are adjusted to balance the beaker as nearly as possible. If more than 10 seconds are required to get the weight of the beaker it will have absorbed enough moisture from the air to affect the results seriously and should be put back in the 100° C. bath for 30 minutes more and the weighing repeated. This second check weighing is advisable in all cases where accurate work is important.

The difference between the weight of the sample taken and the weight of the precipitated nitrocellulose, corrected for residue in the ether, alcohol, and water used, is calculated as moisture and volatiles. A correction of 0.10 per cent is deducted from this result to allow for the volatilization of diphenylamine in the powder. If the powder contains more or less than 0.4 per cent of diphenylamine, the proper correction is made assuming that 25 per cent of the diphenylamine volatilizes.

Diphenylamine in smokeless powder.—Five grams of powder is placed in a 250 c. c. beaker and 30 c. c. of concentrated HNO_3 poured over it. The beaker is covered with a watch glass and set on the steam bath until the powder is completely dissolved, the heating being continued for one-half to one hour after solution has taken place to insure complete decomposition of the nitrocellulose. The contents of this beaker are then cooled and poured into another beaker containing about 100 c. c. of cold distilled water, stirring constantly during addition. The beaker and watch glass are washed into the second beaker, stirred vigorously, and set on the steam bath until the precipitate collects in a flocculent form and the solution is a clear yellow color. The solution is cooled and filtered through a weighed Gooch crucible, dried at 100°C ., and weighed. The weighed crucible is extracted with acetone, and is then dried and weighed again. The loss equals the nitrodiphenylamine formed. This loss in weight is multiplied by the factor 0.40576 to convert it to diphenylamine.

This method is much more rapid than the bromination method and gives good results, which are somewhat higher than those obtained by the latter method.

Determination of alcohol in powder.—One hundred grams sliced powder (it is unnecessary to slice 3-inch or smaller) is weighed into a 1,000 c. c. distillation flask. The distillation flask is connected with a condenser and the neck tightly closed with a rubber stopper through which a wide-mouthed separatory funnel is inserted. 25 to 50 c. c. H_2O and 25 c. c. NaOH (30 to 40 per cent) are added and the mixture gently warmed. At this stage great caution is necessary. When violent decomposition has ceased, NaOH is added from time to time until total decomposition of the powder has been effected. When this stage is reached, the heat is increased and 150 to 175 c. c. of liquid distilled off, replenishing from time to time the water lost by distillation.

The distillate is neutralized or made slightly acid with H_2SO_4 and 100 c. c. redistilled. The temperature is brought to 20°C . and the refractive index is read at 20°C . with a Zeiss immersion refractometer. From the Zeiss reading the amount of alcohol may be found by reference to tables.

Test at 135° C.—This test is run on all powders. Large mixed grains are turned down on a lathe until they fit snugly into the regular 135° test tube.

The test will be made on five samples in exactly the same way as for nitrocellulose, the powder being as nearly in whole grains as is consistent with the standard weight of 2.5 grams. No sample shall turn the normal methyl violet paper to standard salmon pink in less than one hour, nor shall any sample explode in less than five hours. Examination of the tubes is made every five minutes. When the salmon pink is established between the observations at the end of 55 minutes and at the end of 60 minutes, a 60-minute test shall be allowed. The end point is established at the end of the five-minute period during which the salmon-pink color develops in the normal methyl violet paper.

Moisture.—To obtain the amount of moisture in water-dried powders, a sample of at least 5 whole grains of not less than 20 grams will be dried for six hours at 100° C. \pm 2° C. at atmospheric pressure, cooled in a desiccator, and the resultant loss of weight determined by weighing. This loss will be considered as moisture, and the difference between this figure and that of the total volatiles by precipitation will be considered as residual solvent.

CHAPTER V.

COMPOUND PROPELLANTS.

So far there has been considered only the so-called "straight nitrocellulose" powders, that is, those powders which do not contain either inorganic nitrates or high explosives. The smokeless propellants yet to be considered are those which are mixtures of nitrocellulose with nitroglycerin or with inorganic nitrates, such as barium nitrate and potassium nitrate.

SPORTING BALLISTITE AND INFALLIBLE POWDER.

These powders are used chiefly as the propelling charge for shotgun and Stokes trench mortar. Instead of being in the form of a cylinder, as is the case with .30-caliber rifle powder or cannon powder, they are cut in the form of square flakes or discs of approximately 0.005 inch in thickness.

Their manufacture involves primarily the proper solution and incorporation of soluble nitrocellulose in nitroglycerin in the proportion of 60 per cent of the former to 40 per cent of the latter. By mixing the soluble nitrocotton and nitroglycerin in hot water a partial colloid is formed which is similar in certain respects to the colloid obtained when nitrocellulose is dissolved in an ether-alcohol mixture. The water is then expressed from the mass by passing the colloid between rollers which are heated to about 40° C. This rolling operation is repeated until a uniform mixture of nitrocotton and nitroglycerin is obtained. The sheet thus formed is finally cut into square flakes, which are coated and blended in the usual manner.

The inspection of these powders consists only of stability tests:

(a) The finished powder shall give a potassium iodide starch paper test of 15 minutes at 82.2° C.

(b) 120° C. fume test: A sample of the powder which has been dried at ordinary laboratory temperature overnight shall be used for this test. Two and one-half grams of the sample is placed in each of the two tubes of heavy glass, which are about 290 mm. in length, 18 mm. outside diameter, and 15 mm. inside diameter. When the constant temperature bath has been regulated at 120° C., these tubes are placed in the bath so that not more than 6 or 7 mm. of the tubes project from the bath. Examination of the tubes is made by

withdrawing about one-half their length and replacing quickly every 5 minutes. The test is completed when the fumes fill the tubes. The powder shall give a fume test of not less than 15 minutes at 120° C.

The storage of these powders is maintained under the same conditions as nitrocellulose smokeless powder.

E. C. POWDER.

This propellant is generally used for the loading of blank cartridges and consists of semicolloided nitrocellulose granulated with inorganic nitrates. The main point observed in manufacture is the proper incorporation and mixing of all ingredients. This process is usually conducted by means of a wheel mill in a manner somewhat similar to that used for black powder and reworked powder. Nitrocellulose of approximately 12.9 per cent nitrogen is mixed with about 10 per cent of a mixture of potassium nitrate and barium nitrate, together with a small amount of diphenylamine and a pink coloring matter, and the product granulated by a mixture of water and a suitable solvent, in such manner that it forms small rounded grains. The nitrocellulose in these grains is only partially colloided, acting as a binding material and hardening the surface of the grains.

Granulation.—About 95 per cent shall stay on a 40-mesh screen, and not more than 2 per cent shall pass a 60-mesh screen. The powder shall be stable to the following heat tests:

Stability.—(a) KI starch paper test: A weight of 1.3 grams shall be taken and tested in the same way as .30-caliber powder. It shall give a test of not less than 35 minutes.

(b) Heat test at 135° C.: A weight of 2.5 grams shall be taken and tested in the same way as .30-caliber powder. It shall not turn normal methyl violet paper salmon pink in less than 25 minutes, nor explode in less than 4 hours.

Other small arms compound propellants used for military purposes will not be discussed in this publication, as their composition and methods of manufacture can not be described without disclosing information regarded by the manufacturers as confidential.

CHAPTER VI.

BLACK POWDER.

GENERAL.

European history contains references to black powder as early as 1250 A. D. Roger Bacon in 1264 performed the first recorded experiments with this material and shortly after this time it was introduced as a propelling charge for the fourteenth century bombard. Authorities differ upon the subject of the origin of black powder. It has been attributed severally to the Chinese, Arabs, and Hindus. It is certain that the alchemists of mediæval days were familiar, to a certain extent, with the properties of the mixture of saltpeter, sulphur, and charcoal. Certain authorities regard Berchtold Schwarz as the inventor. To him, at any rate, belongs the credit of being the first (1313 A. D.) recorded user of this material in the propelling of stones from a gun. Powder was first used in a meal state. Later camphor was added to prevent crumbling. Graining or granulating is first recorded in 1425, resulting in a stronger and more uniform powder. Classification of the grains by screening is reported by the French in 1525. Black powder gradually replaced all other devices as a propellant, until 1870 it was practically the only propellant used. Its present military use is practically confined to the following:

First. Ignition charges.

Second. Base charge or expelling charge for shrapnel shell.

Third. Manufacture of primers and fuses.

Fourth. Saluting and blank-fire charges.

Fifth. For time-train rings and combination fuses.

Sixth. For mixtures with other kinds of propellant powders for use in small-arms ammunition.

It is thus seen that in its former function as a propellant black powder has been superseded almost entirely, having been replaced by smokeless powder. Among some of the factors which may be mentioned as responsible for effecting this change are:

First. A large quantity of solid residue after the ignition of a charge.

Second. The volume of black smoke caused by the presence of a large quantity of noncombustible material.

Third. The relatively great speed of erosion of the gun barrel due to the high temperature of combustion.

Fourth. Rapid deterioration when exposed to atmospheric conditions due to its hygroscopic nature.

The manufacture of black powder is not technically complicated, but owing to its sensitiveness, unusual precautions must be observed in its manufacture.

MANUFACTURE.

Black powder is a mechanical or physical mixture of potassium nitrate, charcoal, and sulphur in the approximate proportions of 75, 15, and 10, varying percentages being used with varying effects. The saltpeter and sulphur should be of a very high grade commercial quality, should be practically free from chlorides and chlorates, and for practically all grades the percentage of perchlorate should not exceed 0.5 per cent. Charcoal should be obtained from burning of peeled willow and alder, excepting for saluting and blank-fire powders, for which charcoal made from hardwoods is used. Depending upon the use to which the particular grade is to be put the percentage composition of the finished material is altered as necessity demands. It has been found, for instance, that by increasing the percentage of saltpeter the rate of burning is increased; by increasing the percentage of charcoal the rate of burning is decreased. Extensive incorporation improves the quality and uniformity.

Purification of saltpeter is obtained by means of repeated recrystallization, the formation of large crystals being prevented by continuous agitation of the saltpeter liquor.

PROCESS.

The sulphur and charcoal in the proportions specified are pulverized at the same time in a ball mill, which consists of a revolving steel cylinder in which iron or steel balls do the crushing or grinding. This pulverized material is mixed either with pulverized saltpeter or stirred into a saturated solution of saltpeter, depending on the plant equipment.

There are three methods of mixing:

First. The French method, which is rarely used in this country. The pulverized saltpeter, charcoal, and sulphur are mixed and incorporated in a ball mill in which the revolving cylinder is of hardwood and part of the balls are lead composition and part lignum-vitæ.

Second. Dry mixing, in which the ingredients are blended by hand or by mechanical devices. In each of the above methods a small quantity of water is added.

Third. Wet mixing, in which the pulverized sulphur and charcoal are stirred into a saturated solution of saltpeter at a temperature of about 130° C. (265° F.). The mass is then spread on a floor to cool, after which it is ready for incorporation. The lumps formed in the cooling are easily broken.

After mixing by either of the above methods, the material is spread on the bed of the wheel mills in quantities of 300 pounds per wheel mill. The wheels, weighing 8 tons each, rotate on the material for 3 hours at 10 rotations per minute. Edge runners keep the material worked toward the center of the tread of the wheels. Wheel cake or clinker formed during this operation is crushed or broken before pressing.

In order to obtain uniform ballistic results, it is necessary that the powder be of uniform density before granulation. The horizontal hydraulic press has been found to be the best type for this operation. The press plates, usually of aluminum, are so placed as to give press cake approximating three-fourths inch in thickness and about 24 inches square. The effective pressure on the press cake is estimated at 1,150 pounds per square inch.

The press cake is cracked or granulated in the corning mill by feeding the cake between crusher rolls. Mechanically operated shaking screens separate the dust and coarse grains from the finished grain—the coarser lumps passing through successive crushing rolls—four sets of crushing rolls being the usual number per mill. The operation is considered as the most hazardous of the various operations in the manufacture of black powder. Many devices have been employed to reduce the loss of property and life in the corning mill to a minimum. Most of these efforts have been toward conserving material that is lost in the way of dust, and which during operation of the mill prevents the proper oversight of machinery or extraction of foreign substances in the powder and the use of labor-saving devices and mechanism so arranged that the mill can be operated from a place of safety.

FINISHING.

There are three accepted standard processes for finishing:

First. In which drying and polishing are separate processes.

Second. In which drying and polishing are one operation.

Third. In which drying and polishing are one operation in a heated cylinder.

The rounding or polishing of the grain is accomplished by tumbling in a revolving wooden cylinder. The drying may be done in the same cylinder by forcing a current of warm air through the cylinder while the powder is being polished, or the powder may be removed from the cylinder and dried in stationary wooden trays. When heated cylinders are used the cylindrical surface of the revolving cylinder is steam-jacketed, warm, dry air being forced through the cylinder as described above. The damage done by an explosion of a mill of this type leads to its abandonment. To glaze the polished grains a small quantity of pulverized graphite is added to the

powder while the powder is hot from the tumbling or polishing process and the process continued for about half an hour.

The drying and glazing process, when carried out on the single operation plan, requires 8 hours.

PACKING.

Before packing, the powder is rescreened and separated into grades according to specification requirements. Containers for black powder are made of soft steel and average about 9 inches in diameter by 11 inches high, capacity 25 pounds, painted black, stenciled to show grades, lot number, maker, and contract number.

INSPECTION.

The various grades of black powder specified by the Ordnance Department are classified according to their percentage composition, purity of material, size of granulation, and rate of burning. For example, a certain latitude is permitted in the lower grades of black powder in the purity of the saltpeter and the percentage used in the finished product. Similarly the use of those grades of charcoal which yield a larger percentage of dust is also permitted. With grade "C" black powder, however, where the uniform rate of burning is of utmost importance, the inspection details are governed by more rigid specifications.

The different sizes of granulation form the basis for a secondary classification, as is indicated by the following table:

Powder.	Passer screen.				Duster screen.			
	Mesh per inch.	Diameter of opening (inch).	Diameter of wire (inch)	Tolerances (per cent)	Mesh per inch.	Diameter of opening (inches).	Diameter of wire (inch).	Tolerances (per cent)
Army black powder:								
Grade A—								
No. 1.....	4	0.185	0.065	3	0.093	8	0.032	5
No. 3.....	10	.065	.035	3	.046	14	.025	5
No. 4.....	14	.046	.025	3	.0164	35	.0121	5
Unglazed.....	20	.0328	.0172	3	.0164	35	.0122	5
Grade B.....	6	.131	.036	3	.046	14	.025	5
Grade C.....	150	.0041	.0026	3				

Use.—The general uses of these powders are as follows:

Designation.	Uses.
Army black powder:	
Grade A—	
No. 1.....	All igniting charges. May be used instead of grade B for saluting charges.
No. 3.....	All primers, except as noted for powder No. 4; 3.2-inch shrapnel head charges.
No. 4.....	Base charges for shrapnel; base charges for fuzes; friction primers; model of 1914 obturation friction primer.
Unglazed.....	Unglazed, pellets for primers and fuzes.
Grade B.....	All saluting charges.
Grade C.....	Time train rings of fuzes; pellets for delayed-action fuzes.

METHODS OF ANALYSIS.

Sampling.—About 50 grams of the original sample is crushed in small portions in a porcelain mortar and passed through an 80-mesh sieve. All precautions are taken to avoid unnecessary exposure of the sample to the air during this treatment. If each portion is placed in a stoppered bottle as soon as sifted, there is no appreciable change in hygroscopic moisture content. The powdered sample is well mixed before its analysis is begun.

Moisture.—About 2 to 3 grams of the powdered sample is spread in a thin layer on a tared 3-inch watch glass, carefully weighed and dried over sulphuric acid in a desiccator for three days or in a drying oven at a temperature of 60° to 70° C. to constant weight (about two hours). Cooled in desiccator and weighed. Loss of weight is calculated as per cent moisture.

Potassium nitrate.—In the determination of potassium nitrate by extraction with water about 10 grams of the finely ground sample is weighed in a Gooch crucible with asbestos mat and about 200 c. c. of water, in successive portions of 15 to 20 c. c. each, is drawn through the sample by means of suction. The complete solution of the nitrate is hastened by the use of warm or hot water, although 200 c. c. of cold water is usually sufficient. The final portions of water passing through the crucible should be tested for soluble nitrate by evaporation on a glass plate, or an excess of strong sulphuric acid containing a few crystals of diphenylamine may be added to a few drops of the water, and an intense blue coloration will indicate the presence of nitrate.

The extraction is made on duplicate samples. After the complete removal of the nitrate the crucibles containing the portion insoluble in water are placed in a drying oven at a temperature of about 70° C. and dried to constant weight, usually overnight, although five hours is generally sufficient. The percentage of loss of weight, minus the moisture content found as described above, represents the total water-soluble material, and includes, in addition to sodium or potassium nitrate, a small amount of water-soluble organic material from the charcoal and the impurities in the original nitrate, such as chlorides and sulphate. As a check on this result an aliquot portion of the water extract may be evaporated to dryness on a steam bath, treated with a little nitric acid, again evaporated, heated to slight fusion, and weighed.

Sulphur.—The dried and weighed material left from the extraction with water consists of the sulphur and charcoal. The sulphur is determined by loss of weight on extraction with carbon disulphide

in the Wiley extractor, or other suitable extraction apparatus, drying the insoluble residue to constant weight at about 100° C.

Before drying this residue in a hot oven, the carbon disulphide should first be allowed to evaporate by placing the crucibles in a warm place away from any flame or other source of high temperature, as the vapors of carbon disulphide are very inflammable.

The sulphur used in black powder should be brimstone, the flowers of sulphur not being suitable on account of the invariable presence of acidity. If flowers of sulphur are present, the extraction with carbon disulphide will be incomplete, due to the presence of insoluble amorphous sulphur. In this case it is necessary to resort to extraction with hot aniline in order to remove all of the sulphur, pouring 80 to 100 c. c. of aniline heated to 130 – 135° C. through the crucible in 10 c. c. portions, finally sucking dry, washing with a little alcohol to remove all of the aniline, drying and weighing.

Charcoal.—The residue left from extraction of the sulphur is the charcoal, which is weighed direct as already noted.

Ash.—The ash of the charcoal is determined by ignition of the insoluble residue over a Bunsen burner until all of the carbon has been burned off, and weighing. The ash usually amounts to about 0.5 to 1 per cent of the total powder. An unusually high value for ash may indicate incomplete extraction with water.

Specific gravity.—A known weight of approximately 10 grams is placed in a strong 50 c. c. specific gravity bottle with a perforated glass stopper. The bottle is filled one-half to two-thirds full with clean mercury, placed under vacuum and the remaining space filled with mercury. The bottle containing the powder and mercury is weighed at 19° to 21° C. The actual weight of the bottle plus mercury, plus powder, subtracted from the gross weight of bottle full of mercury, plus the powder taken at 19° to 21° C., represents the weight of mercury displaced. This weight divided by the specific gravity of mercury at 19° to 21° C. (13.59) gives the weight of an equal volume of water. The weight of the powder used, divided by this weight of water, represents the specific gravity of the powder.

NOTE.—To displace the air from the specific gravity bottle, a piece of heavy rubber tubing about 2 feet long is attached to the bottle. The other end of the rubber tubing is attached to one leg of a Y-tube. The other leg of the tube is extended by means of a small piece of glass tubing and rubber tubing to dip into a vessel containing mercury. The stem of the Y is connected with the suction line. The rubber tube leading to the mercury vessel is closed by means of a pinch cock. The suction is applied, the specific gravity bottle evacuated, and the suction line closed by means of a pinch cock placed close to the specific gravity bottle. The pinch cock on the tubing leading to the

mercury vessel is opened to allow the mercury to flow into the specific gravity bottle. This operation is repeated until the bottle is filled with mercury.

Determination of granulation.—A sample of 65 grams of the powder is weighed out accurately, emptied into the passer screen, and shaken vigorously over a sheet of brown paper for exactly one minute. The powder which has passed through the screen is set aside. The material remaining in the sieve is emptied onto the sheet of brown paper, striking the screen sharply with the fingers to remove any adhering powder grains. The material so obtained is again sifted for exactly one minute, the sieve emptied, and any grains adhering to the mesh removed, after which the material is submitted to a third sifting. The material which has now failed to pass through the screen is collected, weighed to the nearest tenth of a gram, and the percentage of powder which failed to pass through the passer screen is calculated. All the material which has been used in the passer-screen test is now emptied onto the duster screen and sifted three times, as described above, collecting each time the material which passed through the screen. This material is collected, weighed, and the percentage of powder which passed through the duster screen calculated.

Moisture and ash free analysis.—Percentages on a moisture and ash free basis are calculated by dividing the percentages of potassium nitrate, sulphur, and carbon, respectively, by the remainder obtained by subtracting the sum of the percentages of moisture and ash from the sum total of the percentages obtained for potassium nitrate, sulphur, carbon, moisture, and ash.

Determination of potassium.—Potassium may be determined by the perchlorate method. This method depends upon the fact that potassium perchlorate is practically insoluble in alcohol, whereas the perchlorates of the other bases which might be present are more or less readily dissolved by this solvent. The water solution containing potassium salts must be free from sulphuric acid or sulphates; if it does contain them they can be removed by precipitation with BaCl_2 , and filtration. The solution is then evaporated to dryness and all acid fumes and ammonium salts driven off. The residue is dissolved in 50 c. c. of hot water containing considerably more than enough perchloric acid to combine with all the bases. Usually 5 to 6 c. c. of perchloric acid solution of 1.12 specific gravity is sufficient. This solution is obtainable from chemical dealers. The mixture is evaporated until it is thick, a little more hot water and 5 to 6 c. c. more of the perchloric acid added and the evaporation continued with stirring. The residue is heated on a sand bath until dense white fumes are evolved. The cooled residue is then stirred with 20 c. c.

of 97 per cent alcohol containing 0.2 per cent by weight of perchloric acid, and transferred to a Gooch crucible, using 20 c. c. more of the same alcohol solution. The residue of potassium perchlorate in the Gooch crucible is then washed with about 20 c. c. of a mixture of equal volumes of ether and alcohol, dried at 120° to 130° C., and weighed. The barium perchlorate is readily soluble in the alcohol used, and magnesium does not interfere if the excess of perchloric acid is large enough. Ammonium salts should be removed, as has been stated, because ammonium perchlorate is not readily soluble in alcohol.

Chlorides, chlorates, and perchlorates.—Chlorides, chlorates, and perchlorates are identified as follows: Some of the solution in water is acidified with a few drops of nitric acid, an excess of silver nitrate added, the mixture heated to boiling, shaken well to coagulate the precipitate of silver chloride, and filtered. To the clear filtrate a few cubic centimeters of formaldehyde (40 per cent solution) is added and the mixture is then boiled. The formaldehyde reduces any chlorate present to chloride, which is precipitated as silver chloride by the excess of silver nitrate present. The reaction is practically complete if the mixture is allowed to stand on the steam bath for about an hour, although a considerably longer time is required for quantitative reduction. The precipitate is filtered off and the filtrate evaporated to dryness to remove excess of nitric acid, transferred with a small volume of water to a crucible, enough dry sodium carbonate added to fill the crucible, the mixture dried carefully over a burner, and fused. The fused mass is dissolved in dilute nitric acid. If perchlorates are present, the solution will be found to contain a precipitate of silver chloride.

BLACK-POWDER STORAGE.

In the consideration of the storage of low explosives, of which black powder is an example, it must be remembered that these materials are particularly sensitive to flame or spark. The restrictions, then, relative to the carrying of matches, to the cleanliness of the floors of magazines, to smoking, and to the use of nonsparking tools in general, should be rigidly enforced and carefully supervised. It is advisable also when working in the magazines where black powder is stored to wear safety shoes, the so-called "powder shoes." When it becomes necessary to open a box or container of black powder it should always be done with a wooden wedge and mallet, at least 100 feet from the nearest magazine, and in a place which is protected from dampness or direct sunlight. No metal tools of any description may be used. If it becomes necessary to repair a magazine, all

explosives should be removed to a safe distance and the building washed before work is started.

Black powder should preferably be stored in a bullet-proof magazine. It should not be stored in the same building with dry picric acid, dynamite, or other high explosive. The kegs may be placed in the magazine either on their ends with bung down, or sides with seam down.

In view of the fact that black powder has a tendency to absorb moisture, which causes deterioration and seriously affects the properties of the powder, it is important that the storage magazines be dry and well ventilated.

PART II.—MILITARY HIGH EXPLOSIVES.

INTRODUCTION.

When the entire field of high explosives is considered, the term "military high explosive" has a restricted application to a relatively small number of substances. In determining the suitability of a high explosive for military use, careful consideration must be given to its various properties, including not only its strength but also its sensitiveness to shock or friction such as may occur in loading, its ability to withstand the shock of set-back in the gun, or, in the case of drop bomb explosives, ability to withstand penetration by bullets, its stability, hygroscopicity, action on metals, etc.

These various requirements, together with questions of availability of raw materials, have excluded many high explosives which may be used successfully for commercial purposes.

In the case of some of the explosives discussed herein, details of manufacture are not described, as such data is regarded by the manufacturers as confidential.

CHAPTER VII.

TRINITROTOLUENE (TNT).

GENERAL.

The importance of this explosive is based, first, upon its relative safety in manufacture, loading, transportation, and storage; second, on the fact that it is not hygroscopic; third, on the lack of any tendency to form unstable compounds with metals, and finally upon its powerful, brisant, explosive properties.

Although trinitrotoluene was known as early as 1863, it was first suggested as an explosive only about 1890, but its importance from a military standpoint dates only from 1904. Since this time it has appeared as the principal constituent of many explosives and has been used by itself under such various names as triton, trotyl, tolite, trilit, trinol, tritolo, etc. It is commonly known in this country by the abbreviation TNT. The term trinitrotoluol, which is more generally used than trinitrotoluene, is less correct from the chemical point of view than the latter.

PROPERTIES.

TNT usually resembles in appearance powdered maple or brown sugar, although in different grades of refinement or purity its color and appearance vary. When pure it is a crystalline powder of light yellow color. It dissolves readily in ether, acetone, alcohol, and various other solvents, but it is practically insoluble in water.

Depending upon its purity, TNT is classified by Ordnance Department specifications into three grades, designated as follows:

Grade I, with a solidification point of at least 80° C.

Grade II, with a solidification point of at least 79.5° C.

Grade III, with a solidification point of at least 76° C.

Grade III is obtained directly by the nitrating process as described below, while Grades I and II must be prepared by recrystallization or special chemical treatment of Grade III material.

All grades of TNT are poisonous under certain conditions and it is necessary that proper precaution be taken by those engaged in its manufacture or handling to avoid inhaling the vapors or dust from the hot or crystalline material. Good ventilation in manu-


facturing or shell-loading plants is highly essential, and personal cleanliness should be enforced upon the workmen. All clothing should be changed upon the beginning and completion of work.

TNT is one of the most stable of high explosives, and when properly purified may be stored over long periods of time without alteration. It is quite insensitive to blows or friction but can be detonated by severe impact between metal surfaces. When ignited by flame it burns rapidly without explosion. Rapid heating of large quantities, especially in closed vessels, may, however, cause violent detonation. It should, therefore, be melted only in water or in steam jacketed melting kettles and never subjected to such temperatures as may result from the use of a free flame.


TNT has an important advantage over picric acid in the fact that it has no tendency to form compounds with metals, thereby producing sensitive salts. It will, however, react with alkalies, such as sodium hydroxide or sodium carbonate, to form unstable sodium salts which are quite sensitive. For this reason the use of alkalies in the purification of TNT is not permissible.

TNT in crystalline form detonates readily under the influence of a No. 6 detonator (containing 1 gram of mercury fulminate). When compressed to a high density it requires a No. 8 detonator (containing 2 grams of mercury fulminate), and when cast it is necessary to employ a booster charge of pressed TNT, tetryl, or other more sensitive explosive, to insure complete detonation.

The decomposition of TNT on explosion may be regarded as occurring according to one of the following reactions, or more likely to a combination of both:



or



The deficiency in oxygen as indicated by both of these reactions is always apparent from the black smoke produced by the explosion of TNT. This deficiency of oxygen may be compensated for by the addition of such substances as ammonium nitrate or sodium nitrate in various proportions, the resulting mixtures being designated as amatol and sodatol, respectively.

Like nitroglycerine dynamite, TNT may be classed as a "quick acting" explosive. It detonates at a rate varying from about 17,000 feet per second for loosely compressed material to nearly 25,000 feet per second for material cast or compressed to its maximum density. Forty per cent dynamite has a rate of detonation of about 15,000 feet per second. Various other tests such as the ballistic pendulum test

and the Trauzl lead block test show TNT to be, in general, somewhat stronger and quicker in action than 40 per cent dynamite.

MANUFACTURE.

The manufacture of TNT involves the following processes:

First. Nitration of toluene to mononitrotoluene.

Second. The further nitration of the mononitrotoluene to the dinitro and finally to the trinitrotoluene.

Third. Washing the finished product until free of acid.

Fourth. Purification by remelting and chemical treatment or recrystallization.

Fifth. Granulation, screening, and drying.

The process of nitration of the pure toluene with a mixture of nitric and sulphuric acids may be carried out in various ways, for example:

(1) The one-stage process, where a large excess of a strong mixed acid is used and the temperature gradually raised, with the result that trinitrotoluene is produced in the one process without transfer or separation of spent acid from intermediate products.

(2) The three-stage process, where, by the use of three different acid mixtures and different conditions of temperature, etc., there are successively produced mono-, di-, and trinitrotoluene, each stage being carried out in a different nitrator.

(3) The two-stage process, where either mono- or dinitrotoluene is produced in the first stage and trinitrotoluene in the second.

The nitrator used for the single-stage process consists of a cast-iron or steel cylindrical tank having a capacity of about 1,000 gallons, equipped with a steam jacket and cooling coils. The agitation in the kettle is effected by means of baffles fastened to the side of the tank operating against a mechanically driven propeller. The mixed acid used consists of approximately 76 per cent H_2SO_4 and 23 per cent HNO_3 . After the acid has been blown into the nitrator its temperature is reduced to 30°C . and the charge of toluene slowly run in by gravity. It takes about one hour and a half for the complete addition of the toluene, during which time care is observed to keep the temperature between 30° and 50°C . Finally the steam is turned on and the temperature gradually raised over a period of several hours until a maximum of 110°C . is reached, at which temperature the charge is "cooked" for about three hours. A sample is then taken and a determination made of the solidification point. If this is below 70° it is necessary to cool the charge and add an additional amount of mixed acid. This procedure is continued until the test shows that the conversion of the dinitro to the trinitro has been completed.

In the two and three stage processes of nitration a different procedure is carried out and the nitration of the toluene to the mono-oil is effected by utilizing the spent acid recovered from a previous nitration. In fact, the nitration process consists on the one hand of the progressive nitration of the material, and on the other of the progressive denitration of the acid by utilizing the spent acid from the next higher nitration. In other words, the strongest acid is used for the third nitration. This strong acid consists of a mixture of fuming sulphuric acid and strong nitric acid.

The process is very similar to that employed for the one-stage process with the exception of the method of addition and separation of the acids. The mononitration is first accomplished by running into the nitrator a charge of spent acid from previous dinitration fortified to the proper HNO_3 content. The toluene is then added in approximately the same proportion, with continual stirring. This first nitration period is usually about 1 hour and 20 minutes and the temperature is maintained below 65°C . At the end of the operation the mixture of spent acid and mononitrotoluene is allowed to stand until the two constituents have separated enough so that the acid may be drawn off. The mono-oil is then blown over to another nitrator, where it is subjected to a second nitration similar to the one just completed, except that in this case the spent acid is that from the trinitration, properly fortified to the required HNO_3 content. The dinitrotoluene resulting from this process is usually given the third nitration in the same nitrator, using a strong mixed acid as already noted. The separation of the finished product from the spent acid is effected by gravity, the spent acid being adjusted for use in the next lower nitration as above indicated.

Humphrey (Jour. Ind. & Eng. Chem., vol. 8, November, 1916) states that, contrary to the usual belief, the yield of TNT from the di or second nitration, at a given temperature, is not the function of the water content of the mixture (except that too strong an acid tends to oxidize the material and in this manner lowers the percentage of yield), but is rather dependent upon the proper low temperature during nitration.

The mononitration yields a product containing a mixture of about 4 per cent of the meta nitrotoluene in addition to the ortho and para isomers. The subsequent nitration changes the meta mononitrotoluene chiefly into the beta and gamma trinitrotoluenes, which differ from the alpha form in chemical properties and are regarded as impurities. Small amounts of other isomers of trinitrotoluene have also been identified in the product of the complete nitration of toluene. Depending upon the completeness with which the last

nitration is performed there may be either a large amount of dinitrotoluene present if improperly carried out, or, if correctly done, a relatively small amount.

In addition to these impurities, there may also be such bodies as tetranitromethane which possesses the undesirable property of lowering the solidification point of the pure alpha TNT. If the nitration has been properly carried to completion, there should not be present more than 4 per cent beta and gamma TNT. This condition is not usually attained under manufacturing conditions and it is, therefore, necessary to recrystallize and repurify the TNT in order that the impurities may be eliminated, and a product of the required solidification point for Grade I, TNT (80.0° C.), obtained.

PURIFICATION.

The crude trinitrotoluene, which, due to the heat of reaction, is in the form of an oil, is run from the nitrator into neutralizing tubs which have the shape of a cone at the bottom. At the apex of the cone a gateway valve for regular discharge from the tub is provided. Steam coils for heating and air coils for agitation are both provided. Wash water is drawn off by means of suction through a suitable pipe which reaches the tub near the top and extends along the side wall to about 2 feet from the bottom. A small quantity of sodium sulphite can be used to assist in the purification at this point, although it is not necessary to do so. Washing is carried on until no test for acidity is shown by the use of litmus paper. The neutral TNT, in the form of oil, is now pelleted by running into cold water, for transportation to the graining house, or can be transported in the molten condition to suitable storage tanks through heated pipe lines. If pelleted, these pellets are transported to storage tanks, as above mentioned, and again melted before running into the crystallizing kettles. The storage tanks are kept at an approximate temperature of 95° C., and are provided with a gateway screw valve from which the molten charge is drawn off into the graining kettles. These kettles are made of cast iron, in one piece, and the junction of the bottom and the side walls is rounded so that plows can scrape the TNT loose from the sides. The lower part of the kettle is fitted with a jacket into which steam or cold water may be discharged. As the plows are started, the charge cools down and the crystals begin to form on the sides which increase until the whole mass becomes plastic. During the operation all moisture is driven off and the TNT produced is in a fine crystalline condition. The TNT produced is usually better than Grade III, which is 76° melting point. If it is desirable to obtain TNT of Grades I and II, recrystallization from either alco-

hol or sulphuric acid or a treatment with sodium sulphite must be made. A brief description of each is given below.

Crystallization from sulphuric acid.—The fine crystals produced in the graining kettles are dissolved in hot sulphuric acid, usually weight for weight, and cooled. The purified crystals thus settling out are washed free from acid and regained to such a degree of fineness as to pass Ordnance Department specifications. The crude material held in sulphuric acid is accumulated until such time as the amount warrants separate purification.

Crystallization from alcohol.—The fine crystals of TNT are dissolved in warm 95 per cent alcohol denatured with benzene. This alcoholic solution is filtered and cooled, and sufficient alcohol is distilled off to cause TNT of solidification point of not less than 80.0° C. to separate out. This distillate is recovered and used over again. The crude TNT, commonly known as “still residues,” is usually used up in the manufacture of commercial explosives.

Sulphite purification.—The sodium sulphite treatment is usually applied by taking the fine crystals from the graining kettles, placing them in bins or cars which are equipped with a Filtros bottom. These bins or cars are given one hot water washing, then four washings with the 5 per cent solution of sodium sulphite, then one warm water washing followed by sufficient cold water washings to remove the last traces of the red color which is formed in the treatment. The purified crystals thus obtained can be dried, sieved, and packed, or regained, as may be necessary to meet specifications.

USE.

Grade I TNT is considerably more expensive than Grades II and III, because it requires additional purification; it was therefore used only in boosters for high-explosive shell, where the best grade of material was required. At present no boosters are loaded with TNT, tetryl alone being used. Grade II is used as the bursting charge for high-explosive shell, either alone or mixed with an equal weight of ammonium nitrate to form 50/50 amatol (the TNT in either case being melted so that the shell is filled by a casting or pouring process). Grade III is used only in 80/20 amatol, where it is mixed in the molten state with four times its weight of ammonium nitrate and filled into high-explosive shell by hand stemming or by means of a screw filling machine.

A charge of about $1\frac{1}{2}$ pounds of cast TNT in a 75-mm. high-explosive shell weighing about $9\frac{1}{2}$ pounds breaks up the shell into approximately 700 fragments.

Other military uses for TNT are as a bursting charge for hand grenades, rifle grenades, aeroplane drop bombs, naval submarine

mines, and depth bombs. In aeroplane bombs it has the disadvantage that penetration of the bomb by a rifle bullet may cause an explosion of the charge. This is also true of amatol, which has been used more extensively than TNT in drop bombs. When used in grenades, the crystalline Grade II, TNT is loaded by means of vibrators which "jolt" the grenades until they are completely full. Grade III is suitable for mines or drop bombs and is loaded by casting, as in the case of high-explosive shell.

TNT is also used for military purposes in demolition work on bridges, railroads, etc., and for land mines placed under enemy trenches or fortifications. For demolition work carried on by the Engineer Corps, the TNT is made up in the form of small, highly compressed blocks which are graphited on their surfaces and then copper plated; this protects them from crumbling in handling and renders them waterproof.

TNT has been demonstrated to be suitable for all kinds of blasting work where 40 per cent dynamite is used, and to give practically equal effects. It is well adapted for "adobe" shooting or "mud capping," terms applied to the breaking up of large rocks or boulders by means of a charge of high explosive placed on the rock and confined only by means of a shovelful of mud or wet earth thrown over it. Only quick-acting explosives can be successfully used for such work. Even in drill holes containing water, TNT gives excellent results because of the fact that it is insoluble in water. Its use for blasting has, however, been negligible because of the fact that military requirements have made it unavailable and expensive as compared with commercial dynamites.

On account of its ability to act as a "booster" in bringing about the detonation of more insensitive explosives, TNT has been employed as a partial substitute for the mercury fulminate in commercial electric blasting caps or detonators. A charge of TNT is pressed into the bottom of the cap, covered by a small priming charge of fulminate and the whole charge confined by a perforated copper capsule pressed on top of the priming charge. Such TNT detonators have been extensively used abroad but have not met with great success in this country.

"Cordeau Bickford," a trade designation for detonating fuse, consists of a flexible lead tube, smaller in diameter than a lead pencil, filled with TNT. It is quite extensively used in certain blasting operations, especially for insuring the complete detonation of large charges of dynamite. The detonating fuse being passed through the entire length of the charge, and detonated at its external end by means of an ordinary blasting cap, transmits its high rate of detonation to the entire charge of dynamite.

INSPECTION.

Specifications.—The chemical and physical requirements prescribed by Ordnance Department specifications for the different grades of TNT are as follows:

	Grade I.	Grade II.	Grade III.
Solidification point — not less than.	80° C.....	79.5° C.....	76° C.
Ash—not more than.....	0.1 per cent.....	0.1 per cent.....	0.1 per cent.
Insoluble matter — not more than.	0.15 per cent.....	0.15 per cent.....	0.15 per cent.
Moisture—not more than.	0.1 per cent.....	0.1 per cent.....	0.1 per cent.
Acidity—not more than (as H_2SO_4).	0.01 per cent.....	0.01 per cent.....	0.01 per cent.
Color.....	Light yellow	Light yellow	
Fineness.....	30-mesh sieve, opening 0.0183 inch, wire 0.015 inch.	12-mesh sieve, opening 0.058 inch, wire 0.025 inch.	12-mesh sieve, opening 0.058 inch, wire 0.025 inch (or flake).

It will be noted that the specifications for the three grades vary only in solidification point and fineness.

ANALYSIS AND TESTING.

The most important test in connection with the inspection of TNT is the determination of its solidification point or "setting point." This temperature serves as an indication of the purity of the explosive, inasmuch as the presence of moisture, lower nitrated products, objectionable amounts of isomers, and other impurities all tend to lower the solidification point. In order, however, to insure the proper degree of purity, additional determinations of ash, insoluble matter, moisture, and acidity, are required by Ordnance Department specifications. The prescribed methods of conducting these tests are as follows:

Solidification point: The apparatus used consists of the following parts: A test tube 1 inch in diameter and 6 inches long is fitted through a cork into a second test tube $1\frac{1}{2}$ inches in diameter and 7 inches long, which in turn is set into a large-mouth liter bottle. Into the inner tube is fitted a cork stopper through which are three openings. One is in the center for the standard thermometer, which should be graduated in $1/10^\circ$ C. One is immediately at the side of the center hole and is for a small thermometer which is passed just through the stopper and which reading is taken as the average temperature of the exposed stem of the standard thermometer in making the stem correction. The third hole in the stopper is a small V-shaped opening at the side, through which passes a wire whose lower end is bent in a loop at right angles to the axis of the tube and which is used as a stirrer.

The test is carried out as follows: A 50-gram sample of TNT is placed in the inner tube and melted in an oven, the inner tube being separated from the rest of the apparatus for this purpose. When the temperature has reached about 90° C. the tube is replaced in the apparatus, the standard thermometer placed so that the bulb is approximately in the center of the molten TNT, and the small side thermometer put in place. The stirrer should already be in the molten TNT. Stirring is continued vigorously as the temperature falls, and the thermometer must be watched very carefully. When a point is reached where the temperature begins to rise, owing to the heat of crystallization, readings should be recorded about every 15 seconds until the maximum temperature is noted. This temperature usually remains constant for several minutes until crystallization is complete, and observation should be continued until it is certain that the maximum temperature has been reached. This takes from 5 to 10 minutes after the beginning of crystallization. This maximum temperature with the correction for emergent thread is taken as the solidification point of the sample.

Ash: A known weight, approximately 5 grams is moistened with sulphuric acid and burned in a tared crucible. To compensate for reduction of any metallic salts, a few drops of nitric acid and sulphuric acid are added and the sample again ignited and weighed.

Insoluble matter: A known weight, approximately 10 grams, is boiled with 150 c. c. of 95 per cent alcohol, filtered while hot through a tared Gooch and washed with hot alcohol. After drying to constant weight at 100 c. c., the crucible is cooled and weighed.

Moisture: A known weight, approximately 5 grams, is exposed in a desiccator over sulphuric acid in a watch glass to constant weight.

Acidity: A known weight, approximately 10 grams of the sample, is melted and shaken with 100 c. c. of neutral boiling water and allowed to cool. The sample is then remelted and again extracted with 50 c. c. of neutral boiling water. The total water extract is cooled and titrated with N/10 sodium hydroxide, using phenolphthalein as an indicator. The results are calculated as per cent sulphuric acid in the original sample.

Nitrogen: The determination of nitrogen is not required as a part of routine inspection and is only made in particular cases; e. g., where the solidification point is found to be unusually low. There are various modifications of the Kjeldahl method which give fairly accurate results with TNT; e. g., the method described in Bureau of Mines Technical Paper No. 160. For accurate determinations, however, the Dumas combustion method is considered more reliable if properly conducted.

Fineness: It is required that Grade I, TNT, should pass completely through a screen containing 30 meshes to the linear inch, the openings being 0.0183 inch and the wire 0.015 inch in diameter. Grades II and III are required to pass a 12-mesh screen having openings 0.058 inch and wire 0.025 inch.

STORAGE.

The type of magazine best designed for the storage of TNT is similar to that used for ammonium picrate and wet picric acid. The buildings should not be larger than 26 by 42 feet and may be constructed of tile, asbestos protected metal, or tile walls filled with sand.

The cleanliness both within and without the magazine should be carefully watched and the same rules applied as in the case of the storage of smokeless powder. Special regulations, however, for this material are not necessary, as is the case, for instance, with black powder or picric acid. The loading of shells, by casting or by tamping, should be performed when necessary as far from the service magazine as is possible, and in no case less than 200 feet.

The use of the automatic sprinkler system in the magazines of manufacturing and assembling plants in which TNT is stored has been recommended as protection against incipient fires by the National Board of Underwriters, the action of the sprinklers tending to prevent overheating and the subsequent possible detonation of large quantities of high explosives. (See Suggested Protection for Munition Magazines, National Board of Underwriters, Committee on Fire Protection and Engineering Standards, 76 William Street, New York City.)

CHAPTER VIII.

AMMONIUM PICRATE (EXPLOSIVE D).

GENERAL.

The use of ammonium picrate as an explosive was patented by Nobel in 1888 (Mosenthal, *Jour. Soc. Chem. Ind.*, vol. 18, p. 447, May, 1899), although even prior to that time Brugere made use of a mixture of ammonium picrate and sodium nitrate as a propellant explosive.

The importance of ammonium picrate as a military explosive is due entirely to its marked insensitiveness to shock and friction, which makes it well suited for use as a bursting charge in armor-piercing projectiles. From the standpoint of explosive strength, however, this explosive is inferior to TNT.

PROPERTIES.

Ammonium picrate is soluble in water, crystallizing from its solution in orange-yellow needles, darker in color than picric acid. It resembles picric acid in its bitter taste and property of dyeing the skin, clothing, etc., of those engaged in its manufacture or handling.

It has a much greater tendency to absorb moisture than has picric acid, samples having been found to absorb over 5 per cent by weight of water during storage for one month in an atmosphere saturated with moisture.

Like picric acid, ammonium picrate can react with metals to form metallic picrates, but it reacts with much less readiness than picric acid; in fact, when dry its action is almost negligible. Wet ammonium picrate reacts slowly, especially with copper or lead, to form picrates which are particularly sensitive and dangerous.

Ammonium picrate does not melt on heating, but explodes when heated to a temperature of about 300° C. Small traces of metallic picrates may, however, lower this ignition temperature appreciably.

Ammonium picrate is the least sensitive of all military explosives used as the bursting charge for shell. Its insensitiveness to shock accounts for it being given preference over TNT or amatol as the bursting charge for armor-piercing, base-fuzed shell. It is also more insensitive to detonation by means of mercury fulminate than is TNT. At equal densities ammonium picrate is slightly more power-

ful than TNT. At a pressure of about 12,000 pounds per square inch the two explosives have the same densities, viz. about 1.48.

Like TNT and picric acid, ammonium picrate liberates free carbon on explosion, giving a black smoke. These products of explosion, although more disagreeable in odor, are less poisonous than those from TNT and picric acid, in that they contain less carbon monoxide.

MANUFACTURE.

The manufacture of ammonium picrate consists in the main of a simple neutralization of picric acid by means of ammonia either alone or in combination with ammonium carbonate. This process is not attended with any serious manufacturing difficulties or dangers, provided one excludes the possibility of leaking ammonia pipes. The details of manufacture are as follows:

Approximately 300 pounds of picric acid is mixed with 500 gallons of water at room temperature and then slowly heated by direct steam. As the mixture warms, aqua ammonia is added at the bottom of the tank until neutralization is completed. In some factories it was the practice to add a faint excess, thus insuring complete neutralization of all the picric acid, this condition being evidenced by the formation of a reddish colored crystalline mass of ammonium picrate, although Ordnance Department specifications demand that the product shall be yellow and shall have no alkalinity. When this stage has been reached the resulting material is dropped into tanks for crystallization. These tanks are so equipped that a continual agitation of their contents can be maintained by air with the object of accelerating the crystallizing of the ammonium picrate during the cooling. When the mass has cooled to about 25° C. the crystals are separated from the mother liquor by filtering or draining. From the crystallizing tank the ammonium picrate is taken to the dry house where it is subjected to a temperature of about 45° C. for eight hours in drying bins which are so constructed that warm air circulates constantly through the mass. Finally the dried material is screened by means of a rotating barrel screen and sent directly to the packing room. The finished product is then packed in 50-pound boxes lined with waterproof paper and sent to storage.

REWORKING AMMONIUM PICRATE.

This operation consists in redissolving impure or waste ammonium picrate in water, removing the impurities by filtration, then heating the solution by steam coils until it has been evaporated sufficiently to produce crystallization. From here on the reworking operations are exactly the same as those followed out in the manufacture of the new material.

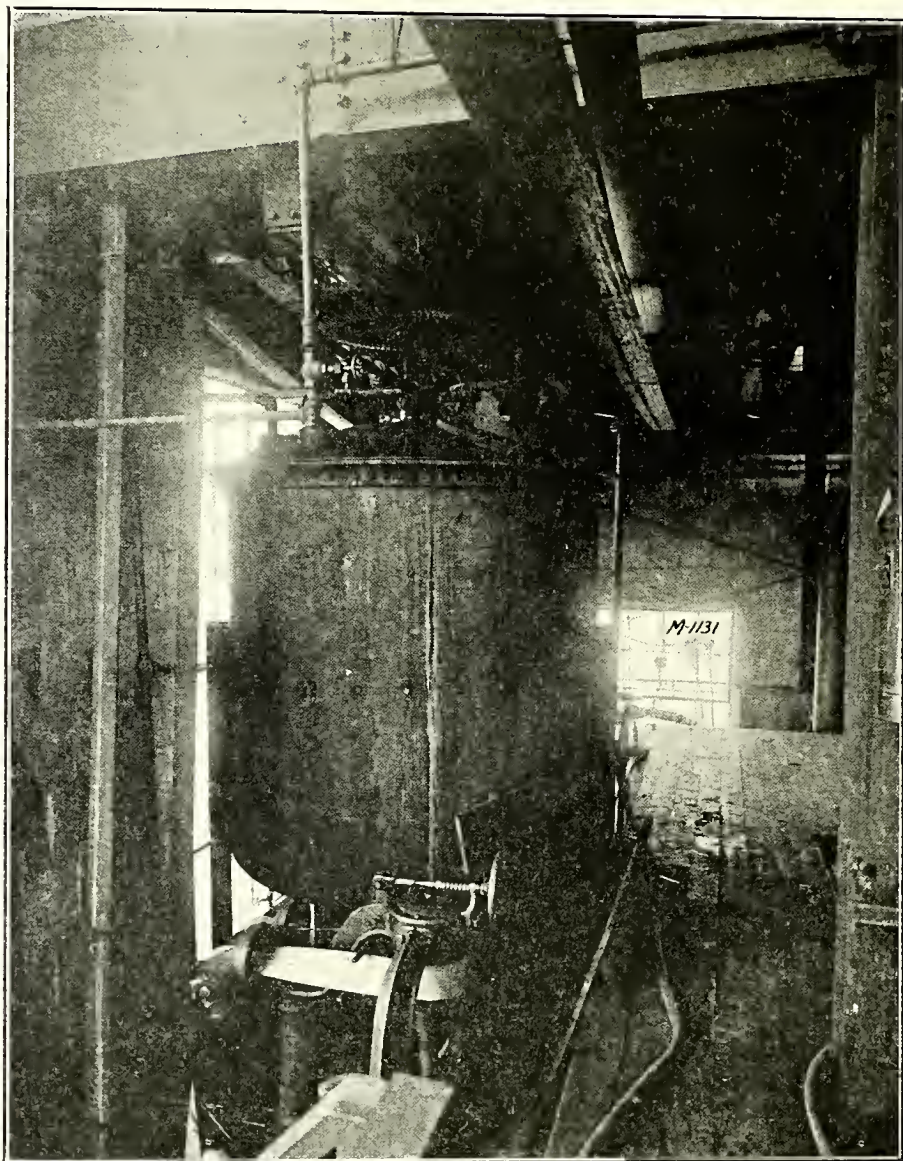


PLATE 33.—SOLUTION KETTLE FOR RECRYSTALLIZATION OF AMMONIUM PICRATE, PICATINNY ARSENAL, N. J.

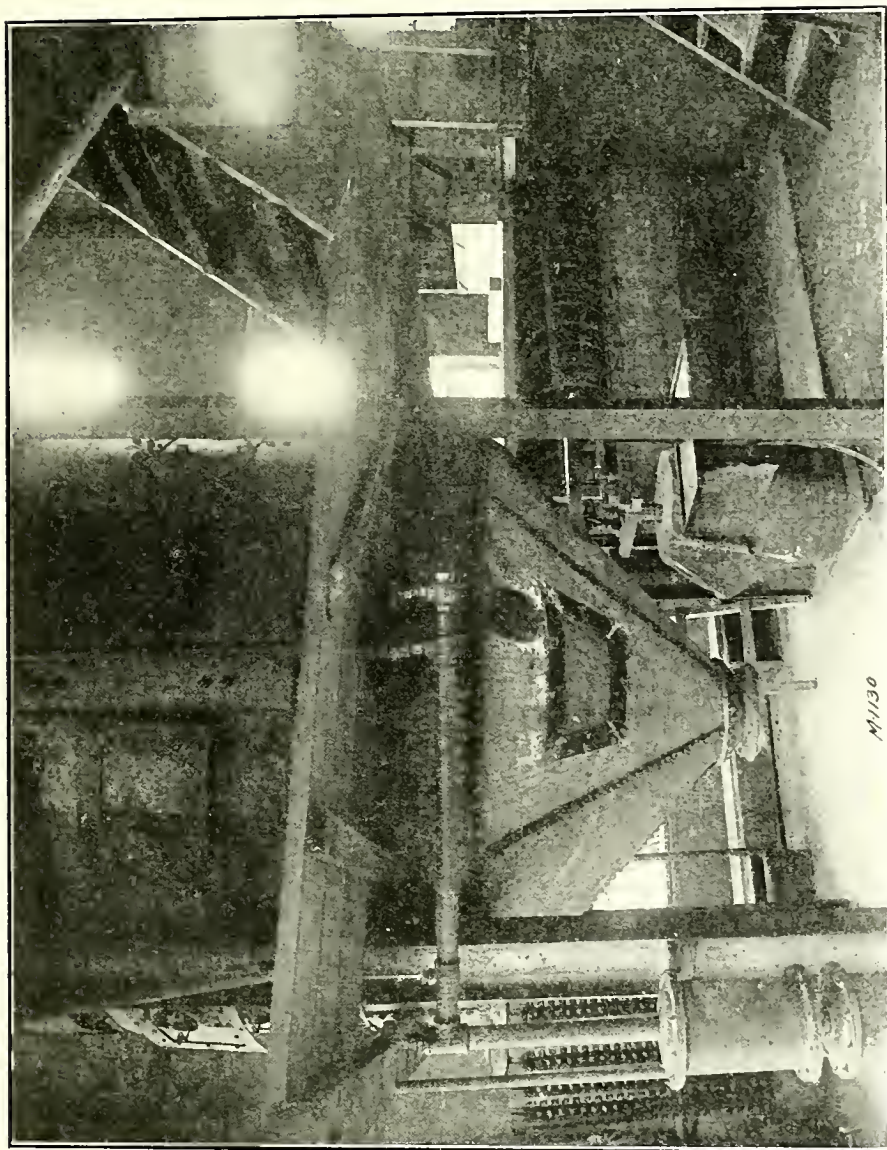


PLATE 34.—EQUIPMENT FOR DRYING AND SCREENING RECRYSTALLIZED AMMONIUM
PICRATE, PICATINNY. ARSENAL, N. J.

USE.

As has been mentioned, ammonium picrate is used as the bursting charge for armor-piercing shell on account of its superior insensitiveness to shock, which permits the shell to pass through the armor before exploding. Owing to the fact that it can not be melted without decomposing it must be loaded into the shell by hydraulic pressure. The interior of the shell is covered with a suitable non-metallic paint or varnish and a moisture-proof seal provided around the booster at the base of the charge by means of cast TNT.

Ammonium picrate has also been used to some extent in France, mixed with potassium nitrate, as a propellant explosive for use in guns.

It has no commercial use as an explosive, although it enters into the composition of numerous patented blasting explosives which have not been used to any great extent.

INSPECTION.

Specifications.—Ordnance Department specifications prescribe the following chemical requirements for ammonium picrate:

It must contain—

- (a) Not less than 5.64 per cent ammoniacal nitrogen.
- (b) Not more than 0.2 per cent moisture.
- (c) Not more than 0.2 per cent insoluble.
- (d) Not more than 0.2 per cent mineral matter (ash).
- (e) No free ammonia.

Analysis and testing.—The following tests and determinations are made on ammonium picrate to determine its suitability for military use:

Ammoniacal nitrogen: A known weight, approximately 1 gram of the ammonium picrate to be analyzed, is placed in a 400 to 500 c. c. Kjeldahl flask. The flask is equipped with a two-hole rubber stopper which carries an exit tube, leading away to a bottle containing N/10 sulphuric acid, and an ingress tube, reaching to its bottom, through which air that has already been dried and freed from ammonia by passage through concentrated sulphuric acid may be bubbled. Twenty c. c. of water is introduced into the flask, 12 c. c. of 5 per cent sodium carbonate solution added, the flask set in a boiling water bath and ammonia-free air bubbled through until the contents of the flask have been evaporated to dryness. The ammonia is absorbed by bubbling the air through 50 c. c. of N/10 sulphuric acid, a bulb full of very small holes, such as may conveniently be made with a hot platinum wire, being used for the purpose. To deal with the possibility of splashing of the sulphuric acid, the exit

tube from the bottle is equipped with a trap. The excess sulphuric acid is titrated with N/10 sodium hydroxide, using methyl red or sodium alizarine sulphonate as an indicator, the amount which has been consumed is noted, and the ammoniacal nitrogen in the sample is calculated.

Moisture: A sample of about 5 grams of the ammonium picrate is accurately weighed in a previously tared wide-mouth weighing bottle at least $1\frac{1}{2}$ inches in diameter and dried for 5 hours, or to constant weight, in a drying oven at 70° C. The loss of weight is calculated as percentage of moisture in the original sample.

Insoluble material: A known weight, approximately 10 grams, is dissolved in 150 c. c. of hot distilled water by boiling for 10 minutes. The solution is filtered through a tared Gooch filter, the insoluble residue washed thoroughly with hot water and dried to constant weight at 100° C.

Mineral matter (ash): A known weight, approximately 5 grams, is moistened with strong sulphuric acid in a tared crucible and carefully burned until all carbonaceous residue has been eliminated. To compensate for reduction of any metallic salts, a few drops of nitric acid and sulphuric acid are added, evaporated, and ignited again. It is cooled in a desiccator and weighed.

Free ammonia: A representative sample of 5 grams of the ammonium picrate is ground in a porcelain mortar with 50 c. c. of water at room temperature, and the supernatant liquid poured through a folded filter, the filtrate being caught in a 750 c. c. Erlenmeyer flask. This process is repeated until all of the ammonium picrate is brought into solution and the total volume of the filtrate is 250 c. c. Three drops of sodium alizarin sulphonate or methyl red indicator are added and the solution titrated to neutrality with tenth normal acid. A blank correction of 1 drop or 0.05 c. c. is subtracted from the amount of acid used and the remainder calculated as ammonia.

STORAGE.

The storage of ammonium picrate is governed by the same rules as are applicable for the storage of TNT, both as to type of magazine and rules for handling, and special regulations governing this particular explosive are not necessary. It is to be noted, however, that ammonium picrate which has been repressed at a shell-loading plant and removed from a shell is very much more sensitive to shock or blow than new material, and there are cases on record where serious accidents have happened in the loading of shells with ammonium picrate so treated. If it becomes necessary then to store this material, special precautions should be observed to protect it against

a shock, or fire, and it preferably should be stored in a building by itself.

Although less sensitive than TNT ammonium picrate can be exploded by severe shock or friction, is highly inflammable, and when heated to a high temperature may detonate. It is therefore necessary that it be treated with proper care as a high explosive.

Since it absorbs moisture it should be stored in dry magazines and protected from dampness. Moisture, however, has no effect on ammonium picrate except to reduce its explosive strength and its sensitiveness to detonation.

Ammonium picrate is always stored in wooden containers because of the possibility of its forming sensitive metallic picrates in contact with metals, especially when moist.

CHAPTER IX.

PICRIC ACID.

GENERAL.

Picric acid or trinitrophenol was first adopted as a military high explosive by the French Government in 1886, under the name of melinite, and has since been used to a greater or less extent by almost all countries, with or without the addition of various materials intended to reduce its melting point or increase its strength. The British explosive designated as Lyddite, and the Japanese explosive Schimose, are both cast picric acid, and various names are given to other shell explosives, the chief component of which is picric acid.

The fact that picric acid readily forms dangerously sensitive salts with metals has practically precluded any extensive use of it as an explosive in this country, its present interest to the United States Government being that it is the raw material used in the manufacture of ammonium picrate.

PROPERTIES.

Picric acid is a lemon-yellow crystalline solid, only slightly soluble in water but soluble in alcohol, benzene, and other organic solvents. A very small amount is, however, sufficient to color a large volume of water a distinct yellow color. It likewise stains the skin of workmen, colors clothing, hair, and everything else with which it comes in contact, and has an exceedingly persistent, disagreeable, bitter taste. Its property of coloring is utilized in the dye industry, and, in fact, picric acid was long known as a dyestuff before its explosive nature was discovered. It has no tendency to absorb moisture from the air.

Picric acid melts at a temperature of about 122° C. when pure, and is usually required for explosive use to have a melting (or solidifying) point of at least 120° C. (248° F.).

Being an acid, it has the property of combining with ammonia and alkalies and with many of the metals, forming salts which are called picrates. Most of the picrates are much more dangerous than picric acid itself, and it is therefore necessary that metals be kept from direct contact with picric acid by means of suitable varnishes or lacquers. Tin is the only common metal which is not attacked by picric acid.

Picric acid is a weak poison, the chief danger in connection with its use being probably the fumes given off from the molten explosive used in shell loading. Practically no trouble from poisoning results in the manufacture or handling of picric acid; care must be taken, however, to avoid the breathing of the large amounts of picric acid dust that may arise in screening or packing dry picric acid.

Picric acid is entirely stable if kept from contact with materials with which it can combine, such as alkalies or metals. It has no tendency to decompose at any temperatures which it might meet in storage. On sudden heating at temperatures much above its melting point (122° C.), it may explode, although many cases are noted where considerable quantities of picric acid have burned without explosion. The presence of any trace of explosive that will detonate more readily, such as metallic picrates, may cause the sudden detonation of burning picric acid.

It has about the same sensitivity to shock or friction as TNT, and is somewhat more readily detonated by means of a detonator. For such reasons, transportation regulations require that for bulk shipment picric acid must contain at least 10 per cent of water, because in this condition it is regarded as an inflammable only. Wet picric acid is, of course, thoroughly dried before use for explosive purposes.

Picric acid is one of the most powerful of military explosives. Its high strength or concussive effect is due to its high rate of detonation, which, for the cast or highly compressed explosive, is about 25,000 feet per second—slightly greater than that of TNT under the most favorable conditions. By both the Trauzl lead block test and the ballistic pendulum test, picric acid shows appreciably greater strength than TNT, being exceeded only by tetryl and TNA. The results of these methods of testing are confirmed by actual fragmentation tests of high explosive shell, where it is found that a larger number of shell fragments is produced from picric acid than from TNT at equal loading densities.

MANUFACTURE.

The raw material from which picric acid is derived is benzene (often called benzol). This substance must not be confused with benzine, which is essentially gasoline, obtained by the distillation of petroleum. Benzene is an inflammable liquid obtained as a by-product in the manufacture of coke by recovery from illuminating gas or by "cracking" oils at high temperatures.

Picric acid may be manufactured from benzene by three distinct processes, designated respectively as the phenol process, the chlor-benzene process, and the catalytic process.

Phenol process.—Practically all of the picric acid produced in this country during the war was made from phenol (carbolic acid). Phenol is prepared from benzene as a raw material by first treating pure benzene with strong sulphuric acid and heating the mixture in jacketed iron kettles provided with agitation at a temperature of about 90° C. (194° F.) for several hours. The resulting benzene sulphonate is usually treated with lime, which converts it to calcium benzene sulphonate, which, in turn, is converted to sodium benzene sulphonate by means of sodium carbonate (soda ash). The sodium benzene sulphonate is dried and heated in fusion kettles with caustic soda which converts it into sodium phenate. The fusion mixture is dissolved in water and treated with either carbon dioxide or sulphuric acid, which causes the phenol to separate out as a distinct layer. This layer is drawn off and distilled in order to separate the pure phenol from water and other impurities. Pure phenol is a white crystalline solid which melts at about 40° C. (104° F.).

For conversion to picric acid the phenol is melted into large jacketed iron kettles and treated with sulphuric acid of about 93 per cent strength, the mixture heated with stirring at a temperature of about 95° C. (203° F.) from four to six hours. The resulting phenol sulphonic acid is diluted with water and treated in a large acid-proof, brick-lined nitrator with 42° Baumé nitric acid (about 70 per cent). The reaction generates heat, and the mixing is therefore carried on very slowly, the maximum temperature being about 110° C. After cooling the mixture, the crystallized picric acid is separated from the spent acid on a vacuum filter, washed with water, and dried.

Chlorbenzene process.—Although this process has been quite extensively used abroad, its use in this country has been rather limited. Briefly the process involves, first, the treatment of benzene with gaseous chlorine, whereby monochlorbenzene results. This product is purified by distillation, and then nitrated with a mixture of nitric and sulphuric acids to give dinitrochlorbenzene. The latter on treatment with lime or soda loses its chlorine and becomes calcium or sodium dinitrophenolate, which on acidifying is converted to dinitrophenol. The dinitrophenol is readily nitrated to picric acid (trinitrophenol) by means of nitric and sulphuric acids.

Catalytic process.—The catalytic process is only in its experimental stage in this country. It consists in converting benzene into either dinitrophenol or picric acid direct in one operation by means of weak nitric acid in the presence of mercury nitrate which acts as a catalyst.

USE.

The fact already noted, that picric acid combined readily with practically all metals to form picrates which are unduly sensitive to

friction, shock, or heat, has been detrimental to the use of picric acid for military purposes, in spite of the fact that it is a stronger explosive than TNT. When a nonmetallic lining is used for the shell cavity—as, for instance, certain lacquers, varnishes, or paints—the danger of the formation of these salts is obviated to a great degree. The introduction of TNT as a military explosive has resulted in the gradual abandonment of picric acid by practically every country except France, where it was largely used during the war. In the United States it has been used only for conversion into “explosive D” or ammonium picrate, which is largely used in base-fuzed shell for seacoast cannon. Picric acid has also found use as a booster explosive and even as a substitute for part of the mercury fulminate charge in detonators. It has been used to a limited extent as a component of many explosive mixtures proposed or patented for military or commercial use.

INSPECTION.

Specifications.—The chemical requirements prescribed for picric acid by Ordnance Department specifications are as follows:

It must have a solidification point of not less than 120° C.

It must contain—

- (a) Not more than 0.2 per cent moisture if purchased as dry picric acid and not more than 22 per cent if purchased as wet picric acid.
- (b) Not more than 0.1 per cent sulphuric acid, both free and combined.
- (c) No free nitric acid.
- (d) Not more than 0.2 per cent ash.
- (e) Not more than 0.2 per cent of material insoluble in water.
- (f) Not more than 0.0004 per cent soluble lead.

It must be of a lemon-yellow color.

Analysis and testing.—The methods prescribed for testing are as follows:

Solidification point: A sample of the picric acid to be used for this test must be dried to constant weight at a temperature not exceeding 50° C. The apparatus used consists of the following parts: A test tube 1 inch in diameter and 6 inches long is fitted through a cork into a second test tube $1\frac{1}{2}$ inches in diameter and 7 inches long, which in turn is set into a large-mouth liter bottle. Into the inner tube is fitted a cork stopper through which are three openings. One is in the center for the standard thermometer, which should be graduated in $1/10^{\circ}$ C. One is immediately at the side of the center hole and is for a small thermometer which is passed just through the stopper and

which reading is taken as the average temperature of the exposed stem of the standard thermometer in making the stem correction. The third hole in the stopper is a small V-shaped opening at the side, through which passes a wire whose lower end is bent in a loop at right angles to the axis of the tube and which is used as a stirrer. The inner test tube is removed and charged with approximately 50 grams of the sample. It is then immersed in a bath of glycerin at a temperature of 130°C . until the picric acid has attained the temperature of the bath throughout. The tube is then assembled in the apparatus for cooling, the standard thermometer graduated in one-tenth degrees immersed in the picric acid with its bulb in the center of the molten mass, and stirring continued vigorously as the temperature falls. The temperatures of both thermometers should be recorded every 15 seconds, in order to note the maximum temperature reached on the slight rise of temperature which results during crystallization. This maximum temperature, corrected for emergent mercury column, is taken as the solidification point.

Moisture: A sample of about 5 grams of the picric acid is accurately weighed in a previously tared wide-mouth weighing bottle at least $1\frac{1}{2}$ inches in diameter, and dried for 5 hours, or to constant weight, in a drying oven at 70°C . The loss of weight is calculated as percentage of moisture in the original sample.

Sulphuric acid: A known weight of picric acid, approximately 10 grams, is dissolved in 250 c. c. boiling distilled water, filtered and washed with 25 c. c. of hot distilled water, acidulated with hydrochloric acid and the solution heated. A slight excess of hot solution of barium chloride is then added with constant stirring, the precipitate allowed to settle and filtered while hot on a tared Gooch crucible. The latter is washed thoroughly with hot water, dried to constant weight at 100°C . and the weight of BaSO_4 calculated as H_2SO_4 in the original sample.

Nitric acid: A water solution of picric acid is tested with a solution of diphenylamine in concentrated sulphuric acid. No coloration should result.

Ash: A known weight, approximately 5 grams, is moistened with strong sulphuric acid in a tared crucible and carefully burned until all carbonaceous residue has been eliminated. To compensate for reduction of metallic salts, a few drops of nitric acid and sulphuric acid are added, carefully evaporated, the crucible again ignited, cooled in a desiccator, and weighed.

Insoluble material: 10 grams of the sample is dissolved in 150 c. c. of boiling water, boiling continued for 10 minutes. The solution is filtered while hot through a tared Gooch crucible, which is washed thoroughly with hot water, and dried to constant weight at 100°C .

Soluble lead: A known weight, approximately 300 grams of the picric acid, is placed in a 2-liter flask and allowed to soak in 100 c. c. of a hot saturated solution of barium hydroxide in 65 per cent alcohol. The flask is well shaken, 1,400 c. c. of 95 per cent alcohol added, and the whole allowed to digest at a temperature below the boiling point of alcohol until all the picric acid has been dissolved with the exception of small particles of insoluble matter. The solution is shaken thoroughly and allowed to stand in the cold until most of the picric acid has crystallized out, then filtered. It is not necessary to disturb the crystalline picric acid at the bottom of the flask as only 500 c. c. of the solution is used for the completion of the tests and this amount can be decanted. To 500 c. c. of this filtered solution, which represents 100 grams of picric acid, 4 or 5 drops of nitric acid and 10 c. c. of a 1 per cent mercuric chloride solution are added and a slow stream of hydrogen sulphide passed through this solution for 15 minutes. After allowing to settle 20 minutes, the solution is filtered and the precipitate washed with alcohol saturated with hydrogen sulphide, the filter paper dried and ignited in a porcelain crucible: 9 c. c. of nitric acid, specific gravity of 1.42, is added and the solution warmed on a hot plate. Enough warm water is then added to make up the volume to 50 c. c. The solution is electrolyzed with a current of 0.4 ampere and $2\frac{1}{2}$ volts, temperature 65° C. After one hour, the electrode is washed by replacing the beaker with another one full of distilled water without interrupting the current. The tared anode is dried and weighed. The weight of lead peroxide found by difference multiplied by 0.8661 gives the per cent of soluble lead.

STORAGE.

The rules governing the storage of dry picric acid are the same as those which apply to the storage of black powder, dynamite, and dry guncotton. Wet picric acid being considered less hazardous, falls under the same classification as TNT and ammonium picrate. The dimensions of the magazines in either case should not exceed 42 by 26 feet. They should be of the ordinary hollow tile construction, and the walls, except in the case of wet picric acid, filled with sand. It is necessary that all dust accumulating from dry picric acid should be carefully removed from any point in or around the buildings, conveyers, or cars. Although dust originating from this source is not as dangerous as that from black powder, it is nevertheless a matter of record that serious explosions have been caused from this source. Safety shoes must be worn in every instance where picric acid is being handled.

CHAPTER X.

NITROSTARCH EXPLOSIVES.

GENERAL NATURE

Under this classification are included "Trojan grenade explosive," "Trojan trench mortar shell explosive," and "Grenite." These explosives are frequently referred to as "nitrostarch," but it should be noted that up to this time pure nitrostarch has not been used as either a military or a commercial explosive, the nearest approach to it for military purposes being "Grenite," which is about 95 per cent nitrostarch with the addition of binding material added for the purpose of granulating. The two Trojan explosives, which are practically identical in composition, contain only approximately 40 per cent nitrostarch, together with ammonium nitrate, sodium nitrate and small amounts of materials added for the purpose of stabilizing, reducing sensitiveness and hygroscopicity, and neutralizing any possible acidity of other ingredients.

REASONS FOR ADOPTION.

These nitrostarch explosives were adopted by the Ordnance Department mainly for the reason that at the time the United States entered the war a decided shortage of TNT, owing to deficient toluene supply, was indicated. A thorough investigation showed that nitrostarch explosives, properly manufactured, seemed to be not only entirely suitable for trench warfare purposes, but to offer certain advantages over TNT, namely, low cost, insensitiveness to rifle bullet fire and to friction or impact, ample supply of raw materials, etc.

MANUFACTURE.

Nitrostarch is prepared by treating starch with a mixture of nitric and sulphuric acids, just as nitrocellulose results from similar treatment. It can be prepared from any variety of starch, but it is claimed that cassava or tapioca starch gives a slightly more stable product than ordinary corn starch. The starch must first be freed from impurities such as fats and oils and water-soluble matter, then carefully dried at low temperatures, screened, etc. It is fed slowly into the acid mixture in an iron nitrator provided with suitable

agitation and cooling surface, in order to avoid overheating from violent local action. This treatment converts the starch into starch nitrate (commonly but incorrectly referred to as nitrostarch), without any change in appearance, but a decided change in chemical properties.

The nitrated product is separated from the excess of spent nitrating acid, drowned in water, washed thoroughly to remove all traces of free acid, then separated from the water in filters or centrifugal wringers, and finally spread out on trays to dry in suitable dry houses heated with warm air to a temperature not exceeding approximately 35° to 40° C. (about 100° F.).

The drying operation, especially the handling of the warm, dry product, is the only really dangerous operation connected with the manufacture, the dry nitrostarch being highly inflammable, capable of being ignited by the slightest spark such as might result from a static charge, and when once ignited, burning with explosive violence.

The mixing of the dry nitrostarch with the "dope" materials, as the inert ingredients of such explosive mixtures are frequently called, is a simple operation, carried out in large revolving mixing barrels. All of the "dope" materials must first be ground to the proper degree of fineness and dried to the proper moisture content, so that the moisture content of the finished explosive will not be in excess of the prescribed amount. Granular nitrostarch explosives, such as "Grenite," are usually prepared by spraying the dry material with a solution of the binding material while the mixture is being agitated in a revolving mixer. The resulting granules are dried and screened to proper size.

CHEMICAL AND PHYSICAL PROPERTIES.

Nitrostarch itself is a white, finely divided material, quite similar in appearance to ordinary powdered starch. When observed even under the microscope there is no appreciable difference between nitrated and unnitrated starch until the granules are treated with iodine, which colors the unnitrated starch blue but does not affect the nitrated product.

Nitrostarch is insoluble in water and does not gelatinize or form a paste when heated with water, thereby differing from starch. The grade of nitrostarch ordinarily employed contains from about 12.50 to 12.75 per cent nitrogen; that prescribed for military purposes contains at least 12.80 per cent. All nitrostarch is readily soluble in acetone, the solubility in ether-alcohol, in general, increasing as the nitrogen content decreases. It has no great tendency to absorb moisture from the atmosphere beyond the amount of 1 to 2 per cent.

Trench grenade or trench mortar shell explosive differs greatly in appearance and certain of its properties from straight nitrostarch, being of grayish-black color and of about the consistency of ordinary brown sugar, having a slightly damp feel and tendency to pack under compression, due to the small amount of mineral oil contained as an ingredient. This oil, besides decreasing the sensitiveness of the explosive to ignition and to shock or friction, helps to reduce its attraction for moisture, the mixture of ammonium nitrate and sodium nitrate which it contains being very hygroscopic. In spite of this coating of oil, the Trojan explosive, when spread out in a thin layer in a damp atmosphere, will rapidly absorb moisture to such extent that it becomes decidedly wet. Under ordinary working conditions, therefore, great care must be taken in loading this explosive to avoid the absorption of an undesirable amount of moisture.

Grenite, which is almost entirely pure nitrostarch with the addition of a small amount of oil and a binding material, differs greatly in appearance from Trojan explosive, being in the form of small white, hard granules which run freely without sticking together. Since it contains no ammonium nitrate or other hygroscopic materials, grenite has no particular tendency to absorb moisture even in damp atmospheres.

SENSITIVENESS.

Pure dry nitrostarch is more sensitive to impact than TNT but less sensitive than dry guncotton or nitroglycerin. As mentioned above, it is highly inflammable and readily ignited by the slightest spark such as may result from friction and, like black powder, burns with explosive violence. It is readily detonated by a mercury fulminate detonator.

Trojan explosive and Grenite are both much less sensitive than straight nitrostarch, being required to pass the pendulum friction test of the United States Bureau of Mines and the rifle bullet test, when packed in pasteboard containers. In heavy metal containers these explosives frequently ignite and burn when penetrated by a rifle bullet, and in rare instances have exploded under this test.

Trojan explosive is especially insensitive to ignition, being rather difficult to ignite with the flame of a match when spread out unconfined. When once ignited, however, especially in any quantity, it burns fiercely, with a light-colored smoke.

Nitrostarch explosives are readily detonated by mercury fulminate detonators, a No. 6 detonator, containing 1 gram of fulminate composition, producing complete detonation, unless the explosive has been rendered unduly insensitive by the absorption of excessive moisture or by other cause.

An important consideration in the case of military explosives, especially those intended for trench warfare purposes, is their sensitiveness to explosion by influence; that is, their tendency to detonate from the shock of a near-by explosion. The Trojan explosive has been found especially insensitive to such effects, as shown by the following tests:

Three malleable iron hand grenades were loaded with Trojan grenade explosive, and packed in a small wooden box, divided by means of light wooden partition into three compartments, into each of which a grenade fit snugly in upright position. The two grenades in the end compartments were provided with plugs closing the filling holes and the center grenade with a No. 6 detonator and black powder fuse, the fuse passing out through a small hole in the wooden cover of the box. The center grenade was then detonated by means of the detonator and fuse. On collecting the fragments it was found that, while the center grenade had been broken into hundreds of small fragments indicating normal detonation, the adjacent ones had been merely broken into several large pieces by the force of this explosion, a large part of the powder in them being recovered unconsumed, indicating that only the central grenade had detonated.

In another test, fifteen 3-inch Stokes trench mortar shells were loaded with Trojan explosives, and packed in the usual manner—three in each of five of the regular wooden shipping cases. These cases were placed on end in a row, broad sides in contact, in a pit 5 feet deep, and the pit filled with earth. A fuse and detonator were inserted in the shell farthest removed from the center of this assembly. The detonation of this shell was complete, as indicated by the fragments dug out of the small crater produced. Of the other 14 loaded shell, 9 were recovered uninjured, 1 was broken into several large fragments indicating a low order of explosion, and the remaining 4 were merely split open by the shock of the adjacent explosion, the explosive contained in them having been burned. A similar test of 15 shells loaded with 50/50 amatol resulted in complete detonation of the 15 shells, as indicated by the fact that a very large crater was produced and no unexploded shell or large fragments recovered.

STABILITY.

Early attempts to manufacture nitrostarch resulted in the production of material which was decidedly unstable, and numerous statements found in the literature of explosives refer to nitrostarch as being unsatisfactory for use as an explosive because of sensitiveness and instability. The manufacturers in this country, however, succeeded a number of years ago in placing on the market nitrostarch

explosives which proved highly satisfactory in these respects and found considerable application as blasting explosives. More recent developments led to a product which entirely met the strict requirements prescribed for military explosives, and there is every reason to believe that the nitrostarch explosives adopted by the Ordnance Department have excellent keeping properties if properly stored in dry atmosphere at reasonable temperatures.

The Trojan explosive, however, if allowed to absorb undue quantities of moisture, especially in a warm atmosphere, may tend to deteriorate owing to gradual decomposition. Such deterioration can not result in a dangerous condition because it is accompanied by a continual loss of explosive strength and sensitiveness. No instance of actual decomposition of Trojan grenade or trench mortar explosive made during the war has been noted, all instances of deterioration having been caused by absorption of moisture, which, when in sufficient quantity will render the explosive inert or in any event less sensitive to detonation.

EXPLOSIVE PROPERTIES.

Pure nitrostarch detonates, when properly compressed, at a rate of probably at least 20,000 feet per second. In the case of Trojan explosive, containing only about 25 per cent nitrostarch, the rate of detonation is lower, but the large gas volume and energy content makes this explosive quite suitable for the purpose, as is indicated by the result of fragmentation tests simulating as nearly as possible service conditions.

In judging the suitability of a grenade explosive from the results of fragmentation tests, consideration is given to the number of fragments of an "effective" size, rather than to the total number of fragments, for the reason that it is considered that the smaller fragments would have an almost negligible effect against personnel. As a result of actual penetration tests it has been concluded that fragments which are retained on a screen having four openings to the linear inch can be considered as the most effective and in reporting the results of fragmentation tests these fragments are sometimes designated as "effective" fragments.

Fragmentation results in grenades vary over a considerable range, depending on the exact qualities of the metal. With a charge of approximately 2.5 ounces of Trojan grenade explosive the "effective" fragments will vary from about 100 to 150 and total fragments from 200 to 500. Grenite, being nearly pure nitrostarch, gives greater fragmentation, about $1\frac{1}{2}$ ounces of the explosive giving fragmentation equal to the 2.5 ounce charge of Trojan powder. A charge

of $2\frac{1}{2}$ ounces of TNT gives fragmentation only slightly inferior to that of the Trojan powder.

In general, it may be said that the nitrostarch explosives are approximately equal to TNT or 40 per cent dynamite in explosive strength.

USE, MILITARY AND COMMERCIAL.

The Trojan nitrostarch explosive has been used as the bursting charge for hand grenades, rifle grenades, and Stokes trench mortar shell. It is well adapted to such purposes but has not been considered for use as a bursting charge for high explosive gun shell. Its physical consistency is such that it must be loaded into grenades through the small filling hole, by means of vibrating machines, the explosive being "jarred" into the grenade through small funnel openings. Trench mortar shell are loaded by hand-stemming and have also been loaded with the Trojan explosive by means of a screw-filling machine.

Grenite has been approved only for grenades and is considered too sensitive for use as a trench mortar shell explosive. Being granular and "free-running" it is readily loaded into the grenades through funnel openings, no attempt being made to pack it to a high density.

Nitrostarch has been considered for the manufacture of smokeless propellant powder, and numerous attempts have been made to develop a satisfactory powder of this type, but the problem can not as yet be considered solved.

Nitrostarch explosives similar to Trojan grenade explosive have been used for a considerable number of years as blasting explosives for use in mining, quarrying, and other engineering operations, and have met with considerable success as substitutes for the more expensive nitroglycerin explosives. Among the numerous advantages of nitrostarch explosives may be noted the fact that, unlike nitroglycerin explosives, they are nonfreezing.

CARE IN STORAGE AND HANDLING.

The storage of nitrostarch explosives in general is mainly a fire risk. That is to say, the danger accompanying storage is more one of fire than of explosion. Burning may, however, proceed at such rate as to be almost explosive in nature, and the fact that nitrostarch can be exploded by impact must not be overlooked.

Storage magazines must be kept at as low temperatures as possible in order to avoid as much as possible the tendency of nitrostarch to undergo decomposition on heating. A reasonably dry atmosphere in magazines is also highly essential, as Trojan explosive especially, on account of its ammonium nitrate content, has a considerable affinity

for moisture. This explosive is not suitable for storage in bulk in wooden containers, because of its hygroscopicity. Even when loaded into grenades it tends to absorb moisture. Long contact of the explosive with the metal parts of the grenade, either iron, brass, or copper, results in corrosion, which is produced by contact with the moist ammonium nitrate.

There is no danger of poisoning of any kind connected with the handling of nitrostarch explosives.

INSPECTION.

Specifications.—The chemical composition of Trojan explosive as prescribed by Ordnance Department specifications is as follows:

	Not less than—	Not more than—
	<i>Per cent.</i>	<i>Per cent.</i>
Nitrostarch	23.0	27.0
Ammonium nitrate	31.0	25.0
Sodium nitrate	36.0	40.0
Charcoal	1.5	2.5
Heavy hydrocarbons5	1.5
Antiacid5	1.5
Diphenylamine2	.4
Moisture		1.2

The chemical composition of Grenite is prescribed as follows:

	Not less than—	Not more than—
	<i>Per cent.</i>	<i>Per cent.</i>
Nitrostarch	95.5	98.25
Petroleum oil75	2.00
Gum arabic75	2.00
Moisture		1.00

METHODS OF ANALYSIS.

The Ordnance Department specifications prescribe the following methods for the analysis of Trojan explosive:

(a) *Moisture:* Approximately 5 grams of the sample, accurately weighed out, shall be spread evenly on a 90 mm. watch glass ($3\frac{1}{2}$ inches diameter) and placed in a desiccator over concentrated sulphuric acid. Loss in weight after 48 hours is taken as moisture. As an alternative method, a vacuum desiccator may be used with sulphuric acid (specific gravity, 1.84) as a desiccating agent and employing a vacuum of at least 700 mm. of mercury. After 24 hours the vacuum shall be slowly relieved and the loss in weight taken as moisture. The percentage of moisture shall not exceed 1.2 per cent.

(b) *Ether extract:* Approximately 10 grams of the sample is accurately weighed out and placed in a porous crucible (Gooch crucible, with thin asbestos mat, or an alundum filtering crucible)

and extracted with pure petroleum ether of 0.640 to 0.660 specific gravity. After complete extraction, the crucible and contents are dried by means of a stream of dry air until complete removal of the petroleum ether, after which the crucible shall be placed in a steam oven and dried to constant weight at approximately 70°C . The difference in weight between the original weight of the sample, after deducting weight of moisture, and the weight after extraction is taken as the heavy hydrocarbon oil present, together with the diphenylamine. The diphenylamine in this mixture may be determined by means of the Dumas method for determining nitrogen.

(c) Water extract: The material in the crucible after removal of the heavy oil consists of nitrostarch, ammonium nitrate, sodium nitrate, charcoal, and sodium bicarbonate. By treatment with warm distilled water, the ammonium nitrate, sodium nitrate, and sodium bicarbonate are removed, and the material in the crucible after drying at 80°C . for several hours consists of nitrostarch and charcoal. The loss in weight in the water extraction is determined and also the weight of the crucible plus nitrostarch and charcoal. These two factors are then used in the subsequent calculations.

(d) Sodium bicarbonate: The water extract is made up to a fixed volume. One portion is taken for the determination of the sodium bicarbonate present. This is determined by titration with N/10 sulphuric acid, using methyl orange as an indicator and the alkalinity so found is calculated to sodium bicarbonate.

(e) Ammonium nitrate: At the option of the inspector, the percentage of ammonium nitrate is determined by taking an aliquot portion of the water extract, adding caustic soda until the solution is strongly alkaline, and then distilling in an apparatus as used for ammonia determinations and collecting the distillate in a known volume of standard sulphuric acid. The excess acid is titrated with standard alkali, methyl orange being used as an indicator, and the result is then calculated to ammonium nitrate.

(f) Sodium nitrate: An aliquot part of the water extract is acidified with nitric acid and the solution evaporated to dryness in a platinum dish. It is then ignited at a low red heat over a suitable flame, using care to avoid loss of the contents. The weight is then taken and a correction made for the amount of sodium bicarbonate present and the results regarded as sodium nitrate present. Following this procedure, the ammonium nitrate would be taken by difference, in order to avoid the determination of ammonia.

(g) Charcoal: The residue in the crucible after the water extraction consists of nitrostarch and charcoal. This material is best extracted in a Wiley extractor with warm acetone until no further soluble material is obtained. The crucible is then dried in a stream of dry air and further dried for several hours at 100°C . The weight

of the charcoal is taken as the increase in weight of the crucible over its original weight empty.

(*h*) Nitrostarch: The difference between the sum of nitrostarch and charcoal content as determined in paragraph (*c*), and the percentage of charcoal as found by paragraph (*g*), represents the nitrostarch present.

The analysis of Grenite is carried out in a similar manner, the ether extraction removing the oil, the water extraction dissolving the gum arabic and leaving the nitrostarch.

CHAPTER XI.

TETRYL.

The high explosive commonly known as tetryl (sometimes as tetralite or pyronite) is designated by the chemist as tri-nitro-phenyl-methyl-nitramine and also frequently improperly called tetra-nitro-methyl-aniline. It is closely related to TNA (tetra-nitroaniline), resembles it in many of its properties, and may be used for similar purposes.

MANUFACTURE.

Tetryl is a derivative of benzene and is therefore in the same class of aromatic nitro compounds as TNT and TNA. Although the explosive manufacturer usually starts with dimethylaniline as his raw material, the entire process, beginning with benzene, is indicated as follows: Benzene is nitrated to nitrobenzene by means of a mixture of nitric and sulphuric acids and the resulting nitrobenzene reduced with iron filings and hydrochloric (muriatic) acid to aniline. Aniline is then combined with methyl alcohol (wood alcohol) by heating these ingredients under pressure in the presence of sulphuric acid or iodine, yielding dimethylaniline.

The dimethylaniline is a yellowish oily liquid of slightly lower specific gravity than water. Prior to nitrating it is dissolved in a large excess of 98 per cent sulphuric acid because if treated direct with mixed acid a very violent reaction results. This solution in sulphuric acid is now added to nitric acid or a mixture of nitric and sulphuric acids in a nitrator provided with means for cooling and agitation. The temperature of nitration is approximately 55° to 60° C.

The tetryl separates out from the acid mixture and is freed from the acid by filtration. The acid and tetryl is drained and the sour water removed by filtration.

The tetryl is given a short boiling treatment, and is then ground to pass through a 150 mesh screen. The ground tetryl is given a final boiling treatment with fresh water, after which it is dried in a current of warm air until its moisture content is not more than 0.10 per cent.

CHEMICAL AND PHYSICAL PROPERTIES.

Tetryl is a fine crystalline powder of a yellow color, practically insoluble in water, but soluble in acetone, benzene, and other solvents. It is readily recrystallized and can therefore be obtained in very pure condition if desired. It melts, when pure, between 129° and

130° C. Tetryl is poisonous when taken internally, and precaution is necessary in its manufacture, especially as regards the dust encountered in handling and packing the dry material. With the exception of TNA, it has a higher nitrogen content (24.4 per cent) than any other military explosive. Tetryl is practically nonhygroscopic absorbing less than 0.1 per cent moisture when stored for several days in a saturated atmosphere.

STABILITY AND SENSITIVENESS.

Tetryl is stable at all temperatures which may be met with in storage. When heated above its melting point it undergoes gradual decomposition and explodes at about 186° C. (367° F.). It is more sensitive to shock or friction than TNA, being of about the same order of sensitiveness as picric acid. It is more sensitive to detonation by means of mercury fulminate than is TNT, resembling TNA in this respect. Like TNA, it is also readily exploded by the penetration of a rifle bullet.

Unlike TNA, tetryl does not undergo decomposition when heated with water at temperatures somewhat higher than ordinary storage temperatures.

EXPLOSIVE PROPERTIES.

Tetryl has been found to have a rate of detonation somewhat higher than the maximum rate obtained with TNT (24,000 feet per second). Strength tests, such as the Trauzl lead block test, show tetryl to be stronger than any other military high explosive except TNA, the average expansion produced in the lead block for the more common military high explosives being as follows:

TNA, 380 cubic centimeters.

Tetryl, 320 cubic centimeters.

Picric acid, 300 cubic centimeters.

TNT, 260 cubic centimeters.

USE, MILITARY AND COMMERCIAL.

The high explosive strength and quickness (or "brisanee") of tetryl would seem to adapt it for use as a bursting charge, but its sensitiveness to mechanical shock is such that if used as a shell filler it would not withstand the shock of discharge of the gun. It is, however, sufficiently insensitive that when compressed in columns of short length into a booster it is perfectly safe. In this condition it is readily detonated by the charge of mercury fulminate in the fuze of the shell, and the violence of its detonation insures a high order of detonation of the bursting charge.

Tetryl is therefore generally adopted in this country as a booster explosive. Formerly it was combined with TNT (Grade I), the two explosives being usually loaded separately into the booster casing in the form of highly compressed pellets perforated with a central hole of suitable size for the detonator of the fuze.

It is also used in detonators for both military and commercial purposes, as a partial substitute for the mercury fulminate charge, the tetryl being pressed into the bottom of the detonator shell, covered with a small priming charge of fulminate, and the entire charge partly confined by a perforated inner capsule of copper.

PRECAUTIONS TO BE OBSERVED IN HANDLING AND STORAGE.

The same precautions should be observed in the handling and storage of tetryl as in the case of other sensitive high explosives. It should be kept dry because moisture interferes with its effectiveness. It must be properly protected from bullet fire in brick or hollow tile magazines with iron doors and window shutters. Detonators, blasting caps, fuzes, dynamite, etc., must not be stored with tetryl. Rubber-soled shoes should be worn in magazines and every precaution taken to prevent ignition or explosion from friction or blows due to rough handling.

INSPECTION.

Specifications.—Ordnance Department specifications require that tetryl shall have the following properties:

- (a) Melting point: Not less than 128.5°C .
- (b) Acidity: Not more than 0.01 per cent of surface acidity and not more than 0.10 per cent occluded acidity, calculated as H_2SO_4 .
- (c) Insoluble in benzene: Not more than 0.40 per cent.
- (d) Moisture and other volatile matter: Not more than 0.10 per cent.
- (e) Color: Light yellow or buff.
- (f) Fineness: At least 95 per cent through 14-mesh (screen openings 0.046 of an inch, wire 0.025 of an inch).
- (g) Sand test: 0.4 gram of tetryl primed with 0.23 gram mercury fulminate shall crush not less than 35 grams standard Ottawa sand to pass a 30-mesh sieve on each of five trials.

Methods of testing.—The prescribed methods of testing tetryl for acceptance are as follows:

Melting point: A portion of about five grams of the tetryl is ground in a mortar to pass a 100-mesh screen, and this finely ground material used for the test after drying for two hours at 100°C . or in a sulphuric acid desiccator for forty-eight hours. The capillary tubes used must be of uniform external diameter of about 0.30

mm. to 0.80 mm., with light walls, and long enough to extend out of the bath of liquid used for heating. The thermometer must be accurately standardized and the mercury column completely immersed at the temperature of the observed melting point, or accurate corrections for emergent stem applied, the bulb being not less than $1\frac{1}{2}$ inches from the bottom of the bath. The capillary tube is filled to a depth of 3-4 mm. with the sample, compacted by tapping, and fastened to the thermometer with its bottom end in contact with the bulb of the thermometer. The thermometer is then suspended in the bath, with its bulb at least $1\frac{1}{2}$ inches from the bottom of the bath. The bath being provided with efficient agitation, its temperature is raised rapidly to about 120° C., and then very gradually so that the rise in temperature is about 1° in five minutes. The point taken as the melting point is the temperature which is observed at the instant that the first meniscus of melted material appears across the capillary tube.

Insoluble matter: A known weight, approximately 5 grams, of the sample is dissolved in 75 c. c. of benzene and filtered through a tared Gooch crucible. The residue in the crucible is washed with 25 c. c. of benzene, dried to constant weight at 100° C., and weighed.

Acidity: (a) **Surface acidity:** A known weight, approximately 10 grams, of the finely ground sample is shaken for five minutes with 50 c. c. of cold boiled distilled water, the solution filtered off, and the residue washed with not more than 50 c. c. of cold boiled distilled water. The entire filtrate is titrated with standardized N/20 sodium hydroxide solution, using phenolphthalein as an indicator, and the result calculated as sulphuric acid.

(b) **Occluded acidity:** The wash liquors from the insoluble matter determination are combined and washed by shaking thoroughly in a separatory funnel with 100 c. c. of cold boiled distilled water. The liquids are allowed to separate and the water layer drawn off. The benzene solution is similarly washed with a further portion of 50 c. c. of cold boiled distilled water. The two wash waters are combined, titrated with standard N/20 sodium hydroxide solution, using phenolphthalein as an indicator, and the result calculated as H_2SO_4 . This method gives the total acidity. By subtracting the value for the surface acidity from that for the total acidity the figure for occluded acidity is obtained.

Moisture and volatile: A sample of about 5 grams of the tetryl is accurately weighed in a previously tared wide-mouth weighing bottle at least $1\frac{1}{2}$ inches in diameter, and dried for 2 hours in a drying oven at 100° C., or in a desiccator over sulphuric acid for 48 hours. The loss of weight is calculated as percentage of moisture and other volatile matter in the original sample.

Sand test: (a) Loading the five caps: 0.4 gram of tetryl, weighed to the nearest milligram, shall be placed in the empty shell of a commercial No. 6 blasting cap (composed of copper or gilding metal, and 37 mm. long by 5.5 mm. inside diameter) which is held in a loading block. A plunger 5 mm. in diameter is inserted in the shell and a pressure of approximately 3,000 pounds per square inch applied to the tetryl for three minutes.

0.23 gram of mercury fulminate weighed to the nearest milligram is placed in the shell and covered with a reinforcing cap (having a diameter of approximately 5 mm. at the lower end and a hole of not less than 2 mm. nor more than 3.5 mm. diameter in the top). The same pressure of approximately 3,000 pounds per square inch is applied for one minute.

The powder train in one end of a piece of miner's fuse (such as Ensign Bickford Crescent brand) 8 or 9 inches long is pricked with a pin, and a loaded cap crimped on to this pricked end of the fuse. Care should be taken to crimp near the mouth of the cap in order to avoid the danger of squeezing the fulminate. The cap should be held away from the body when the crimp is being made.

(b) Making the test: 40 grams plus or minus 0.1 gram of standard Ottawa sand, which have been previously sieved through a 20-mesh screen and retained on a 30-mesh standard screen are poured into the cavity of the sand test bomb (see plate 35) and leveled by striking the bomb two or three times. The fuse is inserted through the hole in the cover of the bomb, and the cap lowered into the bomb cavity until the bottom touches the sand. Sixty grams plus or minus 0.1 gram more of the sand (making a total of 100 grams) are then poured round the cap and the bomb tapped as before.

To avoid possible loss of sand caused by the explosion blowing the burned fuse out of the hole in the cover, a piece of rubber tubing about one-eighth inch long and of such inner diameter that it fits the fuse snugly is slipped over the fuse and adjusted at a point on the fuse in such a manner that when the detonator is in position the rubber will be against the inner side of the bomb cover.

The cover is then securely fastened to the bomb, taking care not to displace the cap in the sand. The fuse is lighted and after the explosion has taken place the sand is emptied onto a smooth (glazed) piece of paper, care being taken to remove completely any sand adhering to the sides of the bomb or to pieces of the detonator, shell, or burnt fuse. All of the sand is emptied onto the 30-mesh sieve, and the amount which passes through after shaking for two minutes is weighed.

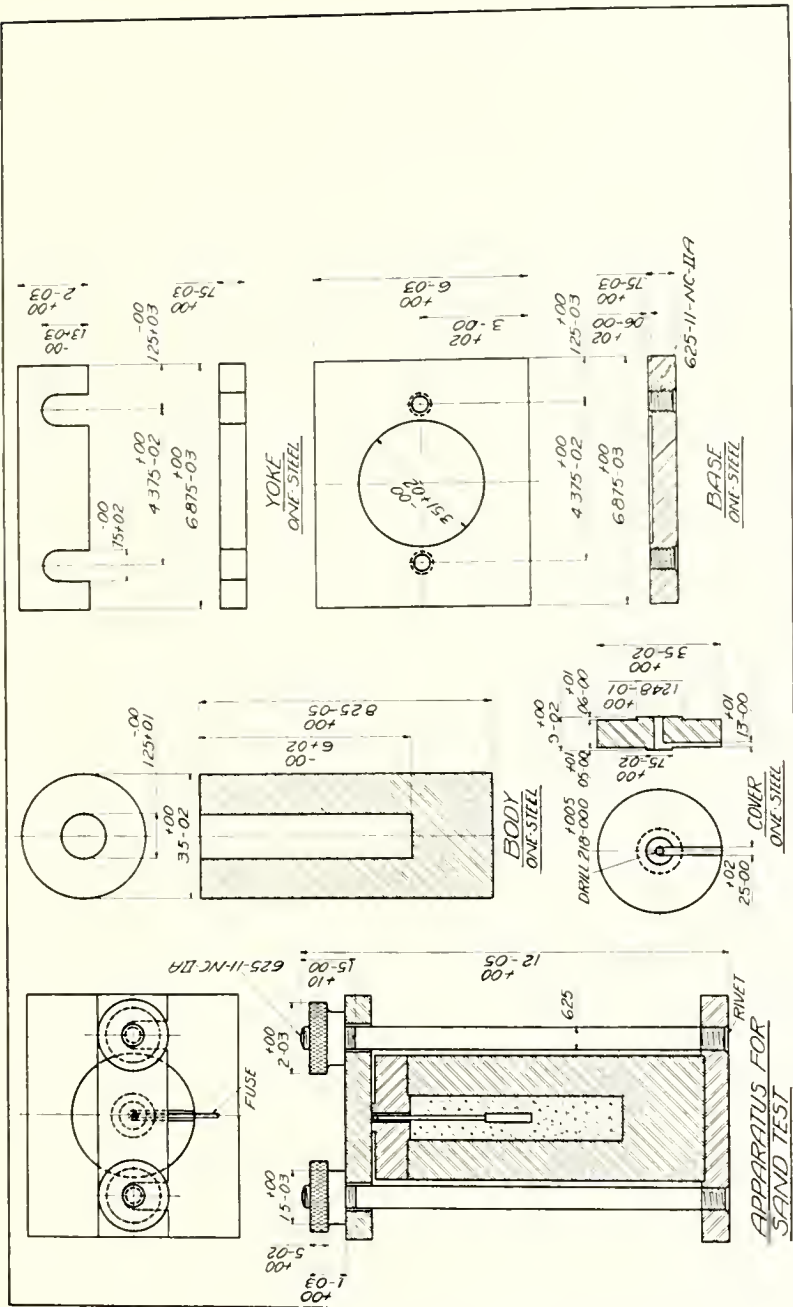


PLATE 35.—APPARATUS FOR LAND TEST.

CHAPTER XII.

TETRANITROANILINE (TNA).

Tetranitroaniline, commonly known by the abbreviation TNA, is a high explosive derived from benzene, the process of manufacture and use of which in this country is patented by Dr. B. J. Flurscheim, an English chemist, under United States Patents Nos. 1045011 and 1045012, November 19, 1912, and No. 1074545, September 30, 1913.

MANUFACTURE.

It is manufactured by a rather complicated process, beginning with benzene as a raw material. Benzene is first nitrated by means of a mixture of nitric acid and sulphuric acid to dinitrobenzene (DNB), which, in turn, is converted by treatment with a solution of sodium sulphide to metanitriline (MNA): the metanitriline, on treatment with sulphuric acid, is converted to metanitriline sulphate (MNAS), which is finally nitrated by means of a mixture of strong nitric and sulphuric acids to tetranitroaniline (TNA). In this final nitration the MNAS is dissolved in a large excess of strong sulphuric acid, and a mixed acid added with stirring and cooling. The finely crystalline TNA separates out from the acid mixture as the reaction proceeds, and is finally recovered by filtration, washed thoroughly with water to remove all free acid, filtered again from the water and finally dried in a current of air at a low temperature.

CHEMICAL PROPERTIES.

TNA is generally admitted to be practically the strongest of all solid high explosives. It is a finely crystalline material varying in color from greenish yellow to olive green, the fine crystals, which appear under the microscope as square plates, being small enough to pass through a sieve of about 80 mesh to the linear inch. Owing to the fact that it has no tendency to absorb moisture from the atmosphere, it does not cake in containers.

When dry, TNA is not in the least affected by exposure for considerable periods to temperatures as high as even 75° C.; in fact, such treatment improves its apparent stability as indicated by the usual "heat test" with potassium iodide—starch paper—for the reason that such heating probably eliminates traces of acid impurities. When moist, however, heating at temperatures as low as 50° C. (122°

F.) will cause a very gradual decomposition of TNA, which, however, is not of a dangerous nature, but probably only results in a loss of explosive strength. Traces of acid decomposition products are liberated by such treatment.

TNA when properly manufactured and thoroughly dried passes satisfactorily all of the usual tests for stability, including the 65.5° C. heat test and the 135° C. test.

Like TNT, TNA has no action on metals with which it may be in contact, differing in this respect from picric acid, which tends to form metallic salts with almost all metals.

TNA is practically insoluble in water, but readily soluble in acetone. It melts only at a temperature of about 210° to 215° C., and then only with decomposition. On heating rapidly to higher temperatures it undergoes rapid decomposition or deflagration with flame, but does not detonate. It contains a higher percentage of nitrogen than any of the well-known military explosives—25.6 per cent—as compared with 24.4 per cent for tetryl, 18.5 per cent for TNT, and 18.3 per cent for picric acid.

TOXIC PROPERTIES.

Although the manufacture of TNA involves the preparation of intermediate products which are of a poisonous nature, such as dinitrobenzene and metanitriline, TNA itself is not poisonous. This has been demonstrated by experimentation in which TNA was administered internally to small animals with no bad results. In contact with the skin it produces yellow stains, similar to that resulting from picric acid, but no poisoning results from this.

SENSITIVENESS TO HEAT, SHOCK, AND DETONATION.

Mention has already been made of the fact that TNA melts only at very high temperatures (210° to 215° C.) and then only with decomposition. It is therefore obvious that this explosive, unlike TNT, is never used in cast form, but always in its original crystalline condition or highly compressed.

TNA is more sensitive to the shock of blows or friction than is TNT.

The effect of penetration of a rifle bullet serves to show a striking difference in the sensitiveness of TNT and TNA. Bullets fired from a service rifle into a box of TNT at a range of about 100 feet show no effect whatever, while, under similar conditions, TNA detonates with great violence.

TNA is more sensitive to the effect of detonators than is TNT. Under certain conditions a confined charge of TNT was found to

require 0.26 gram of mercury fulminate to produce complete detonation, while a similar charge of TNA required only 0.20 gram of fulminate. Under general conditions of use, TNA invariably detonates readily and completely with a No. 6 detonator (containing 1 gram or 15.4 grains of mercury fulminate or its equivalent).

Even when moistened with as much as 6 per cent of water, TNA detonates completely with a No. 6 detonator, and with 16 per cent water, detonation was obtained with a No. 6 detonator and a small priming charge of dry TNA.

EXPLOSIVE PROPERTIES.

TNA, when compressed to a density of about 1.5, has been found to have a rate of detonation of approximately 7,500 meters (25,000 feet per second). The explosive strength has been determined by other tests, such as the Trauzl lead block test, which measures the expansion produced in a cylindrical hole in a cast lead cylinder about 8 by 8 inches, by the explosion of 10 grams (about $\frac{1}{3}$ ounce) of the explosive. In this test it has been found that TNA gives an expansion of about 380 cubic centimeters, as compared with the following approximate results on other high explosives: Tetryl 320 c. c., picric acid 300 c. c., TNT 260 c. c. On the basis of this comparison TNA may be regarded as at least 40 per cent stronger than TNT.

USE.

TNA is considerably more expensive to manufacture than TNT, and for this reason, as well as because of its greater sensitiveness to shock, it is not considered suitable for use as a bursting charge for high explosive shell, drop bombs, etc. Its sensitiveness is greatly reduced by the addition of as little as 5 per cent of paraffin, or of 25 per cent of dinitrobenzene, and such mixtures have been loaded in shell and fired through armor plate without explosion. Such additions to TNA necessarily cause a reduction in explosive strength, and these mixtures have therefore not been adopted for use as shell explosives.

The high cost of TNA constitutes a drawback to its commercial as well as its military use. It has, however, been successfully used as an ingredient of cheap, relatively insensitive blasting explosives, for the purpose of increasing both strength and sensitiveness to detonation. It has also been used to advantage as a partial substitute for mercury fulminate in commercial blasting caps or electric detonators, where it has the advantage that it can be compressed to very high densities without losing its sensitiveness to detonation under the influence of a small priming charge of fulminate.

PRECAUTIONS TO BE OBSERVED IN HANDLING AND STORAGE.

Because of the fact that in the presence of moisture TNA undergoes a gradual decomposition even at relatively low temperatures, it is important that it be kept dry in storage. Efficient ventilation in the magazine is of great assistance in avoiding dampness.

The fact that TNA is readily detonated by the effect of rifle bullets makes it highly important that it be stored only in bullet-proof magazines. Hollow tile construction has been found to be bullet proof. Magazines of lighter type containing TNA should be protected by barricades. Exposed doors and window shutters should be of heavy iron.

It must be remembered that TNA can be exploded by friction or blows of sufficient force and proper care should be taken to avoid unduly rough handling. The wearing of rubber-soled shoes in magazines is advisable.

Detonators, blasting caps, dynamite or similar highly sensitive explosives, must not be stored in the same magazine with TNA.

INSPECTION.

The specifications covering the chemical requirements for TNA, together with the methods for testing, are as follows:

Nitrogen content: Nitrogen content shall be not less than 25.25 per cent when tested by the Dumas method.

Melting point: Melting point shall be not less than 208° C. when heated in a capillary tube with a temperature increase of 5° C. per minute.

Insoluble in acetone: The percentage of material in the sample which is insoluble in C. P. acetone shall not exceed 0.75 per cent when tested as follows: Five grams of the material are thoroughly extracted with C. P. acetone in a filtering crucible and the residue dried to constant weight at 95° to 100° C.

Moisture: The material shall contain not more than 0.30 per cent of moisture when tested as follows: A known weight, approximately 10 grams, of the sample is weighed out onto a 3-inch watch glass and dried in an oven at 95° to 100° C. for one hour.

Acidity: The acidity shall not exceed 0.05 per cent when tested as follows: A known weight, approximately 10 grams, of the sample is weighed into a stoppered bottle of approximately 250 cubic centimeters capacity, 150 cubic centimeters of neutral distilled water is added and the mixture allowed to stand at room temperature with frequent shaking for 30 minutes. The water is filtered off and the residue washed with two successive 20 cubic centimeter portions of cool neutral distilled water, adding the washings to the preceding filtrate. The filtrate is titrated with N/50 NaOH solution, using 15 drops of 0.5 per cent phenolphthalein solution as indicator.

CHAPTER XIII.

MERCURY FULMINATE.

Mercury fulminate is the explosive most commonly used for bringing about the detonation of high explosives. It detonates completely and with great violence on mere ignition by means of a flame such as the spit from a fuse or by means of an electrically heated wire. This fact, together with its property of starting the detonation of other explosives, makes it a most suitable detonator material.

MANUFACTURE.

It is prepared, generally on a relatively small scale, by the action of alcohol on mercury nitrate in nitric acid solution. The raw materials required are, therefore, only metallic mercury, nitric acid, and ethyl alcohol (common grain alcohol of 95 per cent strength). All of these materials must be of high purity, in order to produce a satisfactory product. The process of manufacture is quite simple and may be carried out as follows:

About 1 pound of pure mercury is weighed carefully, added to a weighed charge of from 8 to 10 pounds of strong nitric acid in a suitable bottle or acid pitcher, and allowed to stand until completely dissolved, giving a solution of mercury nitrate in the excess of nitric acid. A large number of such charges are usually prepared and allowed to stand over night until dissolved.

The acid solution of mercury is then poured into about 8 to 10 pounds of 95 per cent alcohol which has previously been measured into a large thin glass flask or balloon of about 10-gallon capacity supported in a suitable rack under an open shed or in the open air. A violent reaction results, usually within two or three minutes, the mixture in the balloons appearing to be boiling violently as a result of the evolution of great quantities of vapors and fumes. These vapors, at first white, become brownish red in color toward the end of the reaction, as the heat generated drives off nitric acid. At this point a small amount of dilute alcohol is usually added to prevent excessive heating, which would decompose the mercury fulminate produced. The reaction usually lasts about one hour, when the fuming ceases and the liquid remaining in the balloon is found to contain the crystalline fulminate.

In some plants the balloons are placed in troughs of water in order to control the temperature, and the necks of the balloons are con-

nected with a suitable condenser system where the alcohol driven off in the fumes is recovered.

After cooling, the charge in the balloons is dumped onto a cloth screen and washed with cold running water until all free acid is removed and the fine impurities in the form of "fulminate mud" washed away. The washed fulminate is then drained and packed in cloth bags, which are usually stored in crocks of water in vaults, or in underground concrete tanks of water, until required for use. For shipment, the bags are packed in barrels of wet sawdust.

When required for use, the fulminate is removed from the bags, the water drained off, and the wet fulminate spread on cloth to dry in dry houses carefully regulated at a temperature of about 43° C. (110° F.). One pound of mercury produces approximately 1½ pounds of dry mercury fulminate.

CHEMICAL AND PHYSICAL PROPERTIES.

Mercury fulminate is a heavy, crystalline solid, white when pure, but ordinarily of a faint brownish yellow or grayish tint. It has practically no tendency to absorb moisture from the atmosphere. It is only slightly soluble in water, 100 parts of water at 15.5° C. (60° F.) dissolving less than 0.01 part of fulminate, and may be kept in contact with water for long periods of time without undergoing change.

The size of the crystals of mercury fulminate is an important factor, since it has been determined that very finely divided fulminate, consisting mostly of fragments of crystals and usually containing an excessive amount of impurities, is less efficient in detonating value and strength than larger crystals. In specifying the size of crystals desired, however, consideration has been given to the possibilities of controlling this feature in manufacture and also to the fact that there is some reason to believe that very large crystals of fulminate are more sensitive to friction or shock than smaller ones. As indicated below, Ordnance Department specifications for mercury fulminate prescribe definite limits for the size of the crystals.

IMPURITIES.

Mercury fulminate is required by Ordnance Department specifications to be at least 98 per cent pure and the amounts of impurities which it may contain are strictly limited. The most objectionable impurities are (1) free metallic mercury, for the reason that it readily attacks the copper or brass with which it may be in contact when loaded into fuzes, detonators, or primers, causing the metal to become brittle; (2) acidity, which would cause deterioration of the explosive composition and corrosion of metal parts;

(3) insoluble material, such as sand and grit, which might cause explosion of the dry fulminate in the loading operations. If improperly manufactured or incompletely washed, the fulminate may also contain various compounds of mercury which might produce decomposition and would certainly diminish the explosive efficiency of the fulminate.

ACTION ON METALS.

Dry mercury fulminate has very little tendency to react with metals at ordinary temperature, although to avoid the amalgamating effect of any small amounts of free mercury present, the brass or copper of the containers is usually varnished or lacquered. Wet mercury fulminate, however, reacts with certain metals, especially brass, with much greater readiness.

STABILITY AND SENSITIVENESS.

Mercury fulminate has been kept for long periods both dry and wet, and is believed to undergo practically no change when properly manufactured and stored. It is never stored in quantity in the dry condition except when loaded into detonators, fuzes, or primers, for the reason that when dry it is readily detonated by friction or shock. Whereas the great majority of high explosives will burn without detonating when ignited by a flame, especially if a relatively small amount of the explosive is ignited, mercury fulminate is one of the so-called "primary" or "initiating" explosives which detonate completely on being heated to their ignition point by means of a flame or hot wire, thereby becoming suitable for use as detonators for other less sensitive explosives.

The presence of even small amounts of moisture in mercury fulminate greatly reduces its efficiency, and as little as 1 per cent is said to cause failure to detonate. Fulminate completely saturated with water may, however, be detonated by the detonation of dry fulminate in contact with it.

By the usual methods of determining ignition temperature, mercury fulminate detonates at a temperature of about 180° C. (about 356° F.), but under varying conditions detonation may result at much lower temperatures. The sensitiveness to shock is much greater at elevated temperatures than under storage conditions.

When loaded into commercial detonators, mercury fulminate is usually compressed at pressures of about 2,000 or 3,000 pounds per square inch. In this condition its explosive properties are not appreciably different from those of loosely compressed material. At greater densities obtained by higher pressures, there is a gradual reduction in strength, until at such extreme pressures as 75,000

pounds per square inch fulminate entirely loses its property of detonating and will only burn. In this condition it is referred to as "dead pressed."

Although fulminate can be pressed under very high pressures without explosion, the presence of any particles of sand or grit is very dangerous in any pressing operation. Presses for loading are always carefully protected by heavy barricades, and no one is permitted to be near the press during operation.

The readiness with which dry mercury fulminate detonates from the effect of blows or friction is the chief reason for the fact that its transportation and storage in the dry state is not permitted. Tests with a special type of impact machine showed that mercury fulminate detonated from the blow of the falling weight dropped from a height of only two centimeters (about 0.8 inch), while TNT in the same apparatus required a drop of about 120 centimeters (48 inches).

EXPLOSIVE PROPERTIES.

The efficiency of mercury fulminate as a detonator for other explosives can not be judged by its behavior when submitted to the usual tests for high explosives. For example, it has been found by the usual methods that mercury fulminate has a rate of detonation of only about 12,700 feet per second, as compared with the nearly double rate for TNT under proper conditions. In the Trauzl lead block test, mercury fulminate produces an expansion of only 213 cubic centimeters, TNT giving about 260 cubic centimeters.

The results of many investigations have led to numerous theories for explaining the unique properties of detonators such as mercury fulminate, the general conclusion being that its ability to detonate other explosives is due to the rapid development of a very high initial rate of detonation which subjects the adjacent mass of explosive to a severe shock or blow, "upsetting" its condition of equilibrium, this effect being rapidly transmitted throughout the explosive by a sort of wave action which results in complete detonation at a high rate.

USE.

Mercury fulminate is used only for the purpose of bringing about the detonation of other high explosives or the explosion of propellant explosives. In detonators for commercial or military use it may be used alone but is generally mixed with from 10 to 20 per cent of potassium chlorate, whereby greater efficiency is obtained.

The usual grades of detonators contain from 15 to 30 grains of fulminate or its equivalent.

The explosion of propellant explosives, as, for example, the smokeless or black powder in small-arms cartridges, is effected by the flame

from a primer or cap, the charge of which is usually a composition containing mercury fulminate mixed with other flame-producing materials such as potassium chlorate with sulphur or antimony sulphide. The primer is exploded by the impact of the firing pin.

PRECAUTIONS TO BE OBSERVED IN HANDLING AND STORAGE.

Mercury fulminate is always stored thoroughly saturated with water.

When left in the barrels during storage, regular inspection must be made to insure that the barrels are kept always full of water and are not leaking.

Fulminate must not be stored with any other explosives, for the reason that the explosion of even a relatively small amount of dry fulminate may cause detonation of the wet material, the effect of which might be to detonate any other high explosives in the vicinity.

In case of breakage or other cause by which wet fulminate may be spilled on the floor, it should not be allowed to dry out before cleaning up. Dry fulminate is very sensitive to friction and must be handled with extreme care. Spilled fulminate may be destroyed by washing floors, benches, etc., with a saturated solution of sodium thiosulphate.

INSPECTION.

Specifications.—The chemical and physical requirements and methods of testing mercury fulminate as prescribed by the Ordnance Department are as follows:

(a) It shall be of such a degree of fineness that not more than 15 per cent by weight shall be retained on a standard 100-mesh screen scale sieve opening 0.0058 inch diameter of wire 0.0042 inch, and that not more than 75 per cent shall pass through a standard 200-mesh screen scale sieve, opening 0.0029 inch and diameter of wire 0.0021 inch.

(b) It shall contain no acidity.

(c) It shall contain not more than 2 per cent of material insoluble in sodium thiosulphate.

(d) It shall contain not more than 1 per cent free mercury.

(e) It shall contain not more than 0.05 per cent chlorine.

(f) It shall contain not less than 98 per cent mercury fulminate.

(g) Sand test: Not more than twenty-seven one hundredths of a gram (0.27 gram) shall be required to detonate completely four-tenths of 1 gram (0.4 gram) of TNT, having a melting point of at least 80.5° C., and of such granulation that it will completely pass through an 80-mesh screen.

Methods of analysis.—Screen test: A known weight, approximately 10 grams of the dried fulminate, obtained by drying at a tem-

perature not exceeding 60° C. to constant weight is added to water and transferred to a 6-inch or some convenient size 100-mesh standard sieve (opening 0.0058, diameter of wire 0.0042 inch), provided with a brass pan and thoroughly shaken for 10 minutes under water. The residual fulminate is transferred from the 100-mesh sieve to a small tared beaker, washed twice by decantation with alcohol and once with ether, and dried at 50° C. to constant weight. The fulminate which passes through the 100-mesh sieve is washed on to a 200-mesh standard sieve (opening 0.0029 inch, diameter of wire 0.0021 inch), and well shaken under water for 10 minutes. The fulminate passing through the sieve is transferred to a tared beaker and dried in the same manner as the fulminate which remains on the 100-mesh sieve.

Acidity: A known weight, approximately 10 grams of the thoroughly dried material, is placed in a porcelain Gooch crucible provided with a filter paper disc in place of the customary asbestos mat and washed with two successive 25 c. c. portions of boiled distilled water. The filtrate so obtained shall show no red tinge upon the addition of three drops of methyl orange solution prepared by dissolving 1 gram of methyl orange in water and making up to one liter.

Insoluble matter: A known weight of mercury fulminate, approximately 2 grams, is transferred to a 250 c. c. beaker. One hundred and fifty c. c. of freshly filtered 20 per cent C. P. sodium thiosulfate solution at room temperature is added and the solution stirred for about one minute, or until the mercury fulminate is apparently in solution. It is then filtered at once through a tared Gooch crucible. Any free mercury remaining in the beaker is completely washed into the crucible with distilled water. The crucible is washed with three or four 10 c. c. portions of cold water to free it from sodium thiosulfate and dried at 70° C. to constant weight.

Free mercury: The residue in the Gooch crucible obtained from the insoluble determination is treated with 60 c. c. of a sodium thiosulphate-potassium iodide solution, containing 6 grams sodium thiosulphate and 3 grams potassium iodide dissolved in water and made up to 50 c.c. The solution is decanted through the Gooch crucible containing the insoluble material and the crucible thoroughly washed with distilled water and dried at 80° to 90° C. for 2 hours and weighed. The residue remaining is taken as the mercury content and the percentage so determined.

Chlorides: A known weight, approximately 5 grams of the thoroughly dried materials, is placed in a porcelain Gooch crucible having in its bottom a filter paper disk and washed with two successive 25 c. c. portions of distilled water, having a temperature between 90° and 100° C. To the filtrate, which is most conveniently

caught in a test tube, three drops of pure nitric acid, having a specific gravity of approximately 1.40, and 10 drops of a 10% solution of silver nitrate are added. No greater turbidity shall appear than when a solution containing 0.0042 gram of pure sodium chloride dissolved in 50 c. c. of distilled water is treated exactly as the filtrate from the sample of fulminate. This represents 0.05 per cent of chlorine.

Mercury fulminate: Exactly 0.3 gram of the thoroughly dried material is placed in a wide-mouthed Erlenmeyer flask of approximately 250 c. c. capacity, containing approximately 50 c. c. distilled water.

Thirty c. c. of a 20 per cent sodium thiosulphate solution, at room temperature, is added quickly and the mixture shaken for exactly one minute and then titrated with standard N/10 HCl solution, using three drops of methyl orange as indicator.

It is important that the titration begin exactly one minute after the addition of the thiosulphate. The bulk of the HCl should be added immediately, and the total time of titration should not exceed one minute. A blank determination should be run and the necessary correction made.

The calculation is as follows:

$$\frac{(A-B)0.00711565}{E} \times 100 = \% \text{ mercury fulminate}$$

where A=c. c. of HCl used.

B=c. c. required for blank.

C=Normality factor for HCl.

E=Weight of sample taken.

Sand test: (a) **Loading** the five caps: 0.4 gram TNT weighed to the nearest milligram, shall be placed in the empty shell of a No. 6 blasting cap (composed of copper or gilding metal, and 37 mm. long by 5.5 mm. inside diameter), which is held in a loading block. A plunger 5 mm. in diameter is inserted in the shell and a pressure of approximately 3,000 pounds per square inch, equivalent to 100 pounds actual load, is applied to the TNT for three minutes.

0.27 gram of mercury fulminate weighed to the nearest milligram is placed in the shell and covered with a reinforcement cap (having a diameter of approximately 5 mm. at the lower end and a hole of not less than 2 mm. nor more than 3.5 mm. diameter in the top). The same pressure of approximately 3,000 pounds per square inch is applied for one minute.

The powder train in one end of a piece of miner's fuse (such as Ensign Bickford crescent brand) 8 or 9 inches long is pricked with a pin, and a loaded cap crimped on to this pricked end of the fuse.

Care should be taken to crimp near the mouth of the cap in order to avoid the danger of squeezing the fulminate. The cap should be held away from the body when the crimp is being made.

(b) Making the test: Forty plus or minus 0.1 grams of standard Ottawa sand which has been previously sieved through a 20-mesh screen and retained on a 30-mesh standard screen (opening 0.0223 inch diameter of wire, 0.011 inch), are poured into the cavity of the sand test bomb and leveled by striking the bomb two or three times. (See plate 35.) The fuse is inserted through the hole in the cover of the bomb and the cap lowered into the bomb cavity until the bottom touches the sand. Sixty plus or minus 0.1 grams more of the sand (making a total of 100 grams) are then poured around the cap and the bomb tapped as before.

To avoid possible loss of sand caused by the explosion blowing the burned fuse out of the hole of the cover, a piece of rubber tubing about one-eighth inch long and of such inner diameter that it fits the fuse snugly, is slipped over the fuse and adjusted at a point on the fuse in such a manner that when the detonator is in position the rubber will be against the inner side of the bomb cover.

The cover is then securely fastened to the bomb, taking care not to displace the cap in the sand. The fuse is lighted and after the explosion has taken place the sand is emptied onto a smooth glazed piece of paper, care being taken to remove completely any sand adhering to the sides of the bomb, or to pieces of the detonator or shell, or burnt fuse. All of the sand is emptied onto the 30-mesh sieve and the amount which passes through after shaking for two minutes is weighed. The TNT shall be considered as having been completely detonated if the average amount of sand passing through the 30-mesh sieve in five trials is not less than 33 grams.

CHAPTER XIV.

AMATOL.

GENERAL.

Amatol is a mixture of ammonium nitrate and TNT. Due to the shortage of toluene during the early stages of the war with Germany, the British Government developed this explosive and adopted it after exhaustive tests as a bursting charge for high explosive shells.

The United States Government shortly after its entrance into the war and for similar reasons authorized its use as follows: 50/50 for shells from 75 mm. up to and including 4.7 inches; 80/20 for shells from 4.7 inches up to and including 9.2 inches. The ingredients are mixed by weight. The first figure refers to ammonium nitrate, the second to TNT.

PROPERTIES.

Amatol is hygroscopic, insensitive to blows or friction, yet can be detonated by severe impact, has no tendency to form dangerous compounds with metal other than copper or tin, is more insensitive to explosion by influence than TNT, and has approximately the same rate of detonation and strength as TNT.

MANUFACTURE OR METHOD OF MIXING.

The TNT is melted and incorporated with the ammonium nitrate in a jacketed mixer for a length of time sufficient to insure each grain of the ammonium nitrate being thoroughly coated with the TNT. The 50/50 mixture is sufficiently fluid to admit of its being poured or cast. The 80/20 mixture is plastic, resembling moist brown sugar, and must be loaded into the shell by tamping or screw filling.

ANALYSIS.

Raw materials.—The ammonium nitrate and TNT used in the preparation of amatol must conform to Ordnance Department specifications governing these materials, as impurities in both have harmful effects on the resulting product. Oily impurities in the TNT will cause exudation or leakage, while impurities in ammonium nitrate, such as pyridine, cyanide, etc., will cause formation of gas or frothing, resulting in probable cavitation in the shell. Methods

of analysis governing the inspection of these materials are given elsewhere in this book.

Sampling.—Samples should be taken from the mixer while the stirrers are rotated, as the TNT and ammonium nitrate have a tendency to segregate. It is desirable to take the sample in an aluminum of thin sheet-iron vessel, a circular piece of stout cardboard being placed in the bottom. To obtain concordant results with duplicate analyses, experience will show that extreme care must be taken with the samples.

Moisture.—Dish and dome method: An aluminum dish and dome (cover) is heated for 15 minutes, cooled in the desiccator and weighed. Approximately 5 grams of the sample is added to the dish which is placed on the top of a water oven for 3 hours. After cooling in a desiccator for 20 minutes, the weight is taken. Loss in weight equals moisture present in the original sample. A small quantity of TNT sublimes but condenses on the inside of the cover, which should be cleaned thoroughly before using in another test.

TNT.—Extraction with benzene: A dry filter paper folded so as to leave a small cavity in the center is weighed in a tared weighing bottle. About 2 grams of powdered amatol is placed in the filter paper without removing it from the bottle and the bottle reweighed. The paper and amatol are transferred to a small funnel and washed with approximately 75 c. c. hot benzene, adding enough at a time to cover the powder. After about one-half of the benzene has been added the remainder can be poured in rapidly, taking care to wash the sides of the filter paper thoroughly. The filter paper and residue are transferred from the funnel to the top of a steam oven in order to remove the greater portion of the benzene and dried in a tared weighing bottle for one hour. Loss in weight equals TNT plus moisture.

Ammonium nitrate.—Extraction with water: A known weight, approximately two grams, is extracted with 50 c. c. hot water, at a temperature not less than 85° C. After cooling, the solution is filtered and the process repeated three times with 50 c. c., 30 c. c., and 20 c. c. successive quantities of hot water. The combined filtrates are evaporated just to dryness in a tared dish and left in a vacuum desiccator overnight. The residue is rinsed two or three times with anhydrous ether, dried on top of the oven to remove ether vapors, cooled and weighed. The residue equals ammonium nitrate present in the sample.

BIBLIOGRAPHY.

AUTHOR INDEX.

- ANONYMOUS. Charcoal for the preparation of explosive mixtures. 1907. Chem. Absts., v. 1, p. 2825. Black powder.
- ANONYMOUS. Concrete protecting walls in explosive factories. 1913. Chem. Absts., v. 7, p. 3841. Black powder.
- ANONYMOUS. Lightning protection for powder and explosives factories and also for powder and explosives magazines. 1907. Chem. Absts., v. 1, p. 2826. Black powder.
- ANONYMOUS. British smokeless powders. 1917. Arms and Explosives, v. 25, p. 76. E. C. blank fire.
- ANONYMOUS. Improved E. C. powder. 1897. Arms and Explosives, v. 6, p. 36. E. C. blank fire.
- ANONYMOUS. Smokeless powder generalities. 1917. Arms and Explosives, v. 25, p. 54. E. C. blank fire.
- ANONYMOUS. High explosive shells. 1901. Engineering, v. 57, pp. 156-7. Picric acid.
- ANONYMOUS. Picric acid and hexanitrodiphenylamine. 1910. Chem. Absts., v. 4, p. 961. Picric acid.
- ANONYMOUS. Picric acid works explosion. 1915. Chem. Absts., v. 9, p. 716. Picric acid.
- ANONYMOUS. Transportation of picric acid. 1913. Chem. Absts., v. 7, p. 3664. Picric acid.
- ANONYMOUS. Sporting powder developments. 1914. Arms and Explosives, v. 22, p. 43. Sporting ballistite.
- ANONYMOUS. Accidents in German explosives factories in 1912. 1913. Chem. Absts., v. 7, p. 3542. TNT.
- ANONYMOUS. Death from TNT fumes. 1915. Arms and Explosives, v. 23, p. 121. TNT.
- ANONYMOUS. Hough TNT nitrator. 1918. Chem. Absts., v. 12, p. 2440. TNT.
- ANONYMOUS. Health of munition worker's committee. Industrial diseases. 1916. Jnl. Soc. Chem. Ind., v. 35, p. 486. TNT.
- ANONYMOUS. Regulations issued for better protection of workers engaged in making or hauling TNT. 1916. Arms and Explosives, v. 24, p. 136. TNT.
- ANONYMOUS. TNT. 1910. Jnl. Soc. Chem. Ind., v. 29, p. 1038.
- ANONYMOUS. TNT loading factor. 1914. Chem. Absts., v. 8, p. 2622. TNT.
- ANONYMOUS. TNT. 1915. Engineering, v. 100, p. 122. TNT.
- ANONYMOUS. TNT. 1918. The Travelers' Standard, v. 6, pp. 98-100, 124-36. TNT.
- ANONYMOUS. Wrecking of Halifax by TNT. 1917. Chem. Engr., v. 26, p. 45. TNT.
- ALLEN, ALFRED H. Commercial organic analysis. 1907. Pp. 236-8. Phenol.
- ASSHETON, R., and COY. American table of distances. 1915. Chem. Absts., v. 9, p. 2150. Black powder.

- AYLESWORTH, J. W. Phenol. (Pat.) 1917. Chem. Absts., v. 11, p. 868. Phenol.
- AYLESWORTH, A. M., and SAVINGS INVESTMENT & TRUST Co. Chemical apparatus; heating liquids; phenol. (Pat.) 1918. Chem. Absts., v. 12, p. 443. Phenol.
- BADERMANN. Gesetze und Verordnungen. 1915. Z. ges. Schiess-Sprengstoffw., v. 10, p. 185. TNT.
- BARAB, J. (See under Cope, W. C., and Barab, J.) Ammonium picrate. Picric acid.
- BERGUIS. (See under Meyer and Berguis.) Phenol.
- BERTHELOT, M. Explosives and their power. 1892. Pp. 466-7. Ammonium picrate.
- BERTHELOT. On the explosive decomposition of picric acid and nitro compounds. 1888. Jnl. Soc. Chem. Ind., v. 7, p. 642. Picric acid.
- BERTHELOT. Picric acid as an explosive. 1888. Jnl. Soc. Chem. Ind., v. 7, p. 48. Picric acid.
- BERTHELOT, D., and GAUDECHON, H. Photolytic decomposition of smokeless powder, picric acid, and ammonium picrate by ultraviolet rays. Chem. Absts., v. 6, p. 2530, 1912. Picric acid. Ammonium picrate.
- BICHEL, C. Increasing the density of fusible nitro compounds. (Pat.) 1909. Chem. Absts., v. 3, p. 2227. Picric acid.
- BLUCHER, H. Auskunftsbuch für die chemische Industrie. 1915. Pp. 950-1. Phenol.
- BLUME. (See under Busch and Blume.) Picric acid.
- BOETERS and WOLFFENSTEIN, R. Manufacture of picric acid. (Pat.) 1909. Chem. Absts., v. 3, p. 2227. Picric acid.
- BOON, A. A., and OGILVIE, JAMES. Quantitative estimation of picric acid. 1916. Chem. Absts., v. 10, p. 3047. Picric acid.
- BONNET. New method of preparing explosives. 1901. Jnl. Soc. Chem. Ind., v. 20, p. 932. Picric acid.
- BRADSHAW, G. B. Picric acid. (Pat.) 1916. Chem. Absts., v. 10, p. 823. Picric acid.
- BRAVETTA, E. Bemerkungen über die Ladung von Geschossen mit starken Sprengstoffen. 1911. Z. ges. Schiess-Sprengstoffw., v. 7, p. 124. Picric acid.
- BROON, T. F. Use of picric acid in war surgery. 1918. Chem. Absts., v. 12, p. 68. Picric acid.
- BRUNSWIG, H. Explosives. 1912. Pp. 294-15. TNT.
- BUCHNER, G. Explosivstoffe. 1915. Z. ver. deut. Ing., v. 59, pp. 469-72, 489-92, 511-4. Black powder.
- BUREAU OF THE CENSUS. Census of manufactures for 1905. 1908. Govt. Printing Office, pt. 4, pp. 468-75. TNT.
- BUSCH and BLUME. The quantitative estimation of picric acid. 1908. Chem. Absts., v. 2, p. 1540. Picric acid.
- CHALON, P. F. Les explosifs modernes. 1911. Pp. 134-41. Picric acid. P. 145. Ammonium picrate.
- CHARBONNEAUX, A. E. Explosive. (Pat.) 1916. Chem. Absts., v. 10, p. 1435. Picric acid.
- CHANDELON, T. Improvements relating to the manufacture of explosives. (Pat.) 1888. Jnl. Soc. Chem. Ind., v. 7, p. 868. Picric acid.
- CLAESSEN, C. Explosives. (Pat.) 1913. Chem. Absts., v. 7, p. 3843. Picric acid.
- COLVER, E. DE W. S. High explosives. 1918. Pp. 6, 10, 11, 13, 15-6, 292-300. Picric acid.

- COMBY, A. M. True melting point of TNT. 1910. *Jnl. of Ind. and Eng. Chem.*, v. 2, p. 103. TNT.
- COMBY, ARTHUR, and FLETCHER, B. H. Use of the ballistic mortar for determining strength of explosives. 1913. *Chem. Absts.*, v. 7, p. 253. TNT.
- COOPER-KEY, A. Picric acid explosion. 1915. *Chem. Absts.*, v. 9, p. 965. Picric acid.
- COOPER-KEY, A. Explosives. 1918. *Chem. Absts.*, v. 12, pp. 2054-5. Picric acid, TNT.
- COPE, W. C., and BARAB, J. "Nitron" as a gravimetric reagent for the analysis of substances used in explosives. 1917. *Jnl. Am. Chem. Soc.*, v. 39, pp. 504-14. Picric acid, Ammonium picrate.
- COPE, W. C., and TAYLOR, G. B. Determination of nitrogen in substances used in explosives. 1917. *Bur. of Mines, Technical Paper 160*, pp. 5-20. Ammonium picrate, Black powder, Picric acid, TNT.
- COPISAROW, M. Action of alkalies on TNT. 1915. *Chem. News*, v. 112, pp. 283-4. TNT.
- COPISAROW, M. TNT. 1915. *Chem. News*, v. 112, pp. 147-8. Purification of TNT. 1916. *Chem. News*, v. 113, pp. 37-8. TNT.
- CORBIN, Coating difficultly inflammable explosives with a thin layer of black powder. 1912. *Chem. Absts.*, v. 6, p. 3525. Black powder.
- CRAIG, R. A., ROBERTSON, R., FARMER, R. C., ROTTER, G. Manufacture of explosives. (TNT.) (Pat.) 1915. *Jnl. Soc. Chem. Ind.*, v. 34, p. 985. TNT.
- CRONQUIST, A. W. Powders and explosives: old and new studies. 1908. *Chem. Absts.*, v. 2, p. 899. Black powder.
- CURPHEY, W. S. Alkali inspector's report for 1917. 1918. *Chem. Absts.*, v. 12, p. 2234. Picric acid.
- DAUTRICHE, M. H. Some properties of picric acid, TNT, and trinitrobenzene. 1912. *Chem. Absts.*, v. 6, p. 1226. TNT, Picric acid.
- DELVIGNE, M. Explosive. (Pat.) 1911. *Chem. Absts.*, v. 5, p. 786. Ammonium nitrate.
- DOW, H. H. Phenol synthetically. (Pat.) V. 12, p. 1969. Phenol.
- DU PONT, FRANCIS. Apparatus for forming black gunpowder. 1910. *Chem. Absts.*, v. 4, p. 2733. Black powder.
- DU PONT. Apparatus for solidifying crystallizable mixtures (e. g., black gunpowder mixture) without substantial crystallization and forming strips thereof. (Pat.) 1911. *Chem. Absts.*, v. 5, p. 3911. Black powder.
- DU PONT. Method of forming explosive black powder into spherical grains. 1913. *Official Gaz.*, v. 205, p. 175. Black powder.
- DU PONT. Making black gunpowder having approximately spherical grains. 1914. *Chem. Absts.*, v. 8, p. 3228. Black powder.
- DU PONT. Apparatus for shaping gunpowder into approximately spherical grains. (Pat.) 1914. *Chem. Absts.*, v. 8, p. 3238. Black powder.
- DU PONT. Gunpowder corning mill. 1915. *Chem. Absts.*, v. 9, p. 153. (Pat.) Black powder.
- DU PONT DE NEMOURS & Co. High explosives. Catalogue. Section I. 1915. pp. 27-9, 30. Black powder.
- DU PONT DE NEMOURS & Co. High explosives. (Catalogue.) Section II. 1915. p. 25. Black powder.
- DYNAMITE ACT GES. V. A. NOBEL. Process of obtaining a liquid mixture of aromatic compounds suitable for manufacture of explosives. (Pat.) 1913. *Jnl. Soc. Chem. Ind.*, v. 32, p. 1088. TNT.
- EISENMANN, E. Improvements in the manufacture of picric acid. 1890. *Jnl. Soc. Chem. Ind.*, v. 9, p. 385. Picric acid.

- ELLIS, CARLETON, RABINOVITZ, LOUIS, and WELLS, A. A. The preparation of picric acid and other nitrated phenols. 1917. Chem. Engr., v. 25, pp. 22-6. Picric acid.
- ESCALES, R. Improvements in TNT explosives. 1908. Chem. Absts., v. 2, p. 2862. TNT.
- ESCALES, R. Schwarzpulver und Sprengsalpeter. 1914. Pp. 376-80, 381-403, 475. Black powder.
- ESCALES, R. Nitrosprengstoffe. 1915. Pp. 145-161. TNT. Pp. 177-9, 336-8, 347-52. Picric acid. Pp. 180, 369. Ammonium picrate.
- FARMER, R. C. (See under Craig, R., Robertson, R., Farmer, R. C., Rotter, G.) TNT.
- FAY, ALBERT H. Production of explosives in the United States during the year 1913. 1914. U. S. Bur. of Mines, Technical Paper 85, pp. 5-, 6-13. Black powder.
- FAY, A. H. Production of explosives in the United States during the calendar year 1912. 1914. U. S. Bur. Mines. Technical Paper 69, pp. 3-7. Black powder.
- FAY, A. H. Production of explosives in the United States during 1914. 1915. U. S. Bur. of Mines, Technical Paper 107. Pp. 5, 6-14. Black powder.
- FAY, A. H. Production of explosives in the United States during 1915. 1916. Bur. of Mines, Technical Paper 159, p. 5. Black powder.
- FAY, A. H. Production of explosives in the United States during 1916. 1917. U. S. Bur. of Mines, Technical Paper 175, pp. 5, 6-22. Black powder.
- FAY, A. H. Production of explosives in the United States during 1917. 1918. U. S. Bur. of Mines, Technical Paper 192, pp. 8, 6-14. Black powder.
- FLETCHER, B. H. (See under Arthur and Fletcher, B. H.) TNT.
- FLURSCHHEIM, B. J. Nitrating toluene containing paraffin hydrocarbons. (Pat.) 1917. Chem. Absts., v. 11, p. 2045. TNT.
- GARDNER, H. A. Picric acid. (Pat.) 1917. Chem. Absts., v. 11, p. 2407. Picric acid.
- GAUDECHON, H. (See under Berthelot, D., and Gaudechon, H.) Ammonium picrate.
- GAUDECHON, H. (See under Berthelot, D., and Gaudechon, H.) Picric acid.
- GEWERKSCHAFT DES STEINKOHLENBERGWERKS LOTHINGEN UND UHDE. Pure ammonium nitrate. (Pat.) 1911. Chem. Absts., v. 6, p. 3009. Ammonium nitrate.
- GIRARD. New method of preparing picrates. 1900. Jnl. Soc. Chem. Ind., v. 19, p. 1141. Picric acid.
- GIRARD, C. Explosive. (Pat.) 1908. Chem. Absts., v. 2, p. 3283. Picric acid.
- GIUA, M. The TNT industry in Italy and its conditions of development. 1915. Chem. Absts., v. 9, p. 3361. Preparation of TNT, 1916. Chem. Absts., v. 10, p. 969. TNT.
- GUTENSOHN, A. Producing picric. (Pat.) 1901. Jnl. Soc. Chem. Ind., v. 20, p. 837. Picric acid.
- GUTTMANN, O. The dangers in the manufacture of explosives. 1892. Jnl. Soc. Chem. Ind., v. 11, p. 210. Picric acid.
- GUTTMANN, OSCAR. The manufacture of explosives. V. II. 1895. P. 236. E. C. blank fire.
- HALL, C. Apparatus and methods for physical tests of explosives. 1911. U. S. Bur. Mines, Bul. 15, pp. 79-82, 88-117. Picric acid, Black powder. Permissible explosives. 1912. U. S. Bur. Mines, Cir. 6, pp. 9-10. TNT.
- HALL, C. (See under Munroe, C. E., and Hall, C.) Phenol, Picric acid.
- HALL, C., and HOWELL, S. P. Tests of permissible explosives. 1913. Bur. of Mines, Bul. 66, pp. 4-12, 15-22. Black powder, Picric acid, Ammonium picrate.

- HAMILTON, ALICE. Industrial poisons encountered in the manufacture of explosives. 1917. Chem. Absts., v. 11, p. 2043. Price acid, TNT.
- HAÜSSERMANN, C. Explosive properties of TNT, 1914. Chem. Absts., v. 8, p. 249. TNT.
- HEDEN, J. Wood pulp, oxalic acid, and picric acid. (Pat.) 1909. Chem. Absts., v. 3, p. 3009. Picric acid.
- HESSE, BERNHARD. TNT, 1917. Oil, Paint and Drug Reporter, v. 92, p. 87, No. 7. TNT.
- HIBBARD. Black powder. (Pat.) 1914. Chem. Absts., v. 8, p. 3629. Black powder.
- HIGGINS. Prevention of accidents from explosives in metal mining. 1914. Bur. of Mines, Circ. 19, 16 pages. Black powder.
- HOFFMAN, E. J. Nitration of toluene. 1916. U. S. Bur. of Mines, Technical Paper 146, pp. 5, 8-12. TNT.
- HOWELL, S. P. (See under Hall, C., and Howell, S. P.) Ammonium picrate, Black powder, Picric acid.
- HOWELL, S. P., and TIFFANY, J. E. Methods for routine work in the explosives physical laboratory of the Bureau of Mines. 1918. Bur. of Mines, Technical Paper 186. 63 pp. Ammonium picrate, Black powder, Picric acid, and TNT.
- HUMPHREY, IRWIN. Nitration of toluene to TNT, 1916. Jnl. Ind. & Eng. Chem., v. 8, pp. 998-9. TNT.
- IMRAY, O. Manufacture of explosives. (Pat.) 1892. Jnl. Soc. Chem. Ind., v. 12, p. 709. Picric acid.
- JOHNSON, F. M. G. Separating TNT from spent acid. (Pat.) 1918. Chem. Absts., v. 12 p. 2055. TNT.
- KÖHLER, H. Herstellung von Pikrinsäure. (Pat.) 1893. Jahresber. d. Leist. d. Chem. Technologie, v. 24, p. 524. N. F. Picric acid.
- KOLOWRATNIK, R. Picric acid explosive. (Pat.) 1913. Chem. Absts., v. 7, p. 3665. Picric acid.
- KULLGREN, CARL. Action of atmospheric moisture on moisture content and rate of combustion of black powder. 1912. Chem. Absts., v. 6, p. 425. Black powder.
- LANFREY, A. C. Preventing the reactivity of moist picric acid. 1912. Chem. Absts., v. 6, p. 2533. Picric acid.
- LANGENSCHIEDT, F. Preparation of TNT, 1913. Chem. Absts., v. 7, p. 1416. TNT.
- LA SUEUR, E. A. N. Y. meeting of American Inst. of Chem. Engrs. 1914. Chem. and Met. Eng., v. 12, p. 55-6. TNT.
- LEGG, T. M. TNT poisoning. 1917. Jnl. Soc. Chem. Ind., v. 37, pp. 326-7. TNT.
- LEITCH, J. W. Nitration process. (Pat.) 1917. Chem. Absts., v. 11, p. 1304. TNT.
- McHUTCHINSON and WRIGHT, R. The precipitation of TNT from concentrated acid solution by means of water. 1915. Jnl. Soc. Chem. Ind., v. 34, pp. 781-2. TNT.
- MACDONALD, G. W. Nobel's patents. 1911. Chem. Absts., v. 5, p. 2331. Sporting ballistite.
- MAGNIN. Action of Roentgen rays on various kinds of powders. 1914. Chem. Absts., v. 8, p. 3859. Black powder.
- MARCKWALD, W. Color of picric acid and its solutions. 1900. Jnl. Soc. Chem. Ind., v. 19, p. 433. Picric acid.
- MARDICK, J. R. Nitro-compounds from tar. (Pat.) 1917. Chem. Absts., v. 11, p. 2154. TNT. Black powder.

- MARSHALL, A. Explosives. 1917. 2d ed. Ammonium picrate, v. 1, pp. 746-7. Black powder, v. 1, pp. 8-9. E. C. blank fire powder, v. 1, p. 48. Picric acid, v. 1, pp. 219, 277-281. Sporting ballistite, v. 1, pp. 322-32. TNT, p. 260.
- MARTIN, G. Industrial nitrogen compounds. 1915. P. 114. E. C. powder.
- MATTER, O. Detonating caps for explosives. (Pat.) 1917. Chem. Absts., v. 11, p. 3438. TNT.
- MEYER and BERGUIS. Preparation of phenol from chlorobenzene. 1915. Chem. Absts., v. 9, p. 627. Phenol.
- MOLINARI, E., and QUARTIERI, F. TNT, 1914. Chem. Absts., v. 8, p. 422. TNT.
- MORRIS, F. History of the E. I. Du Pont Powder Co. 1912. Chem. Absts., v. 6, p. 3183. Black powder.
- MOSENTHAL, H. Life work of Alfred Nobel. 1899. Jnl. Soc. Chem. Ind., v. 18, p. 447. Ammonium picrate, Sporting ballistite.
- MUNROE, CHARLES. Chemicals and allied products produced in the United States. 1908. Chem. Absts., v. 2, p. 1748. Black powder.
- MUNROE, C. E., and HALL, C. A primer on explosives for coal miners. 1911. Bur. Mines, Bul. 17, p. 22. Picric acid, Phenol.
- MURRAY, ALEXANDER. Manufacture of Picric acid. 1919. Chem. Absts., v. 13, p. 442. Picric acid.
- MYRIN, O. Several modern military explosives. 1916. Intern. Mil. Digest, p. 294. TNT.
- NATHAN, F. L., RINTOUL, W., and BAKER, F. Explosives. 1913. Chem. Absts., v. 7, p. 3842. Nitrostarch.
- NATHIURST, JALMAR. TNT mixture for use in explosives. (Pat.) 1910. Chem. Absts., v. 4, p. 3300. TNT.
- NEY, A. H. Synthetic phenol and picric acid. 1915. Met. and Chem. Eng., v. 13, pp. 686-90. Phenol, Picric acid.
- NITROGLYCERINE AKTINS. (NAUCKHOFF.) Ammonium nitrate. (Pat.) Chem. Absts., v. 11, p. 1732. Ammonium nitrate.
- NOBEL'S RESEARCHES. 1910. Chem. Absts., v. 4, p. 1544. Sporting ballistite.
- OBERSCHLESISCHE AKT. GES. F. FABRIKATION VON LIGNOSE SCHIESSWOLFFABRIK FÜR ARMEE U. MARINE. TNT, (Pat.) 1914. Chem. Absts., v. 10, p. 276. TNT.
- ODDO, B. Determination of nitrogen in nitric ester explosives. 1918. Chem. Absts., v. 12, p. 1124. TNT.
- OGILVIE, JAMES. (See under Boon, A. A., and Ogilvie, James.) Picric acid.
- ORDER IN COUNCIL. Picric acid. 1875. Explosives act. 1905. Jnl. Soc. Chem. Ind., v. 24, p. 359. Picric acid.
- OSBORNE, THOS. Picric acid: its manufacture and liability to explode. 1915. Chem. Eng., v. 21, pp. 158-9. Picric acid.
- OST, H. Lehrbuch der Chemischen Technologie. 1911. Pp. 201-3. Black powder.
- PENNA. DEPT. OF LABOR AND INDUSTRY. Safety standards of the Industrial Board. 1917. Penna. Dept. of Labor and Industry, pp. 12-16. TNT.
- POPE, FREDERICK. Mechanical engineering of a synthetic phenol plant. 1916. Chem. and Met. Eng., v. 15, pp. 185-92. Phenol.
- PORTER, H. C., and STORM, C. G. Coal tar products. 1915. Bur. of Mines. Technical paper 89, p. 147. Ammonium picrate, Picric acid, TNT, pp. 14, 16-17. Phenol.
- QUARTIERI, F. (See under Molinari, E., and Quartieri, F.) TNT.
- QUARTIERI, F., and SOC. ITALIANA PRODETTI EXPLODENTI. Explosives. (Pat.) 1916. Chem. Absts., v. 10, p. 694. TNT.

- RABINOWITZ, LOUIS. (See under Ellis, Carleton, Rabinowitz, Louis, and Wells, A. A.) Picric acid.
- REUTER, O. Liquid explosive. (Pat.) 1916. Chem. Absts., v. 10, p. 694. TNT.
- RICE, ARCHIE. Risk and avoidance of TNT poisoning. 1918. Chem. Absts., v. 12, p. 2441. TNT.
- RINTOUL, W. Melting point of 1, 2, 4, 6, trinitrotoluene. 1915. Jnl. Soc. Chem. Ind., v. 34, pp. 60-1. TNT.
- RITTMAN, W. The utilization of aromatic compounds derived from cracked petroleum. 1915. Jnl. Ind. and Eng. Chem., v. 7, p. 1014. TNT.
- ROBERTS, D. C., and STUART, O. TNT. (Pat.) 1916. Jnl. Soc. Chem. Ind., v. 35, p. 199. TNT. (Pat.) 1917. Chem. Absts., v. 11, p. 100. TNT.
- ROBERTSON, R. (See under Craig, R., Robertson, R., Farmer, R. C., Rotter, G.) TNT.
- ROGERS, ALLAN. Industrial chemistry. 1915. P. 399, 477. Phenol.
- ROTTER, G. (See under Craig, R., Robertson, R., Farmer, R. C., Rotter, G.) TNT.
- RUDELOFF, J. Explosion in TNT factory at Schönebeck. 1910. Chem. Absts., v. 4, p. 1238. TNT.
- RUNGE, W. Primer for explosives. (Pat.) 1916. Chem. Absts., v. 10, p. 822. TNT.
- RUTLEDGE, J. J. The use and misuse of explosives in coal mining. 1913. U. S. Bur. of Mines, Cir. 7, pp. 7-9, 11. Black powder.
- RUTLEDGE, J. J., and HALL, C. Use of permissible explosives. 1912. Bur. Mines, Bul. 10, pp. 7-34. Black powder.
- SANFORD, P. G. Nitroexplosives. 1898. Pp. 146-147. TNT, pp. 153-155 Picric acid, pp. 186-187. E. C. blank-fire powder.
- SCHERESCHESKY, J. W. TNT, practical points in its safe handling. 1918. Chem. Absts., v. 12, p. 996. TNT.
- SCHUPPERT, Fires in gunpowder (black powder) factories. 1910. Chem. Absts., v. 4, p. 963. Black powder.
- SHRÖTTER, F. TNT, 1913. Chem. Absts., v. 7, p. 3663. TNT.
- SINGTON, T. Explosions of picric acid. 1917. Met. and Chem. Eng., v. 17, pp. 134-135. Picric acid.
- SNELLING, W. O., and COPE, W. C. The rate of burning of fuse. 1912. Bureau of Mines, Technical Paper 6, pp. 4, 5, 6-8. Black powder.
- SNELLING, W. O., and STORM, C. G. The analysis of black powder and dynamite. 1913. U. S. Bureau of Mines, Bul. 51, pp. 66-78. Black powder.
- SPARRE, F. Granulated black gunpowder. (Pat.) 1915. Chem. Absts., v. 9, p. 153. Black powder.
- STETTBACHER, A. Vergleichende Explosionswirkungen. 1915. Z. ges. Schiess-Sprengstoffw., v. 10, pp. 214-218. Picric acid.
- STETTBACHER, A. Comparative action of explosives. 1916. Chem. Absts., v. 10, p. 118. TNT.
- STEVENS, K. K. Inspection and testing of TNT. 1917. Jnl. Ind. and Eng. Chem., v. 9, pp. 801-803. TNT.
- STORM, C. G. Analysis of permissible explosives. 1916. U. S. Bur. of Mines, Bul. 96. Pp. 10-12, 27-30, 39-41, 50; Ammonium picrate, nitrostarch, dinitrobenzene. Pp. 10-12, 27-30, 39-41, 50; TNT.
- STORM, C. G. (See under Porter and Storm.) Ammonium picrate. Phenol. Picric. TNT.
- STORM, C. G., and COPE, W. C. Sand test for determining strength of detonators. 1916. Bur. of Mines, Technical Paper 125, 68 pp. Picric acid.

- TARNOW, T. B. T. Explosives. (Pat.) 1916. Chem. Absts., v. 10, p. 276. TNT.
- TAYLOR, G. B. (See under Cope, W. C. and Taylor, G. B.) Ammonium picrate. Black powder. Picric acid. TNT.
- THOMPSON, W. P. Process for manufacture of picric acid from crude phenols. (Pat.) 1890. Jnl. Soc. Chem. Ind., v. 9, p. 1032. Picric acid.
- THORPE, EDW. Dictionary of applied chemistry. 1912. P. 6569. Vol. 1. Phenol.
- TYRER, D. Phenol. (Pat.) 1917. Chem. Absts., v. 11, p. 277. Phenol.
- U. S. Navy Department Specifications for TNT. 1917. Jnl. Soc. Chem. Ind., v. 36, p. 164. TNT.
- UTZ. A new method for the evaluation of picric acid. 1908. Chem. Absts., v. 2, p. 1670.
- VENDER, VEZIO. Purifying TNT, 1911. (Pat.) Chem. Absts., v. 5, p. 198. TNT.
- VENNIN, L., and CHESNEAU, G. Les poudres et explosifs. 1914. Pp. 260-3 TNT, p. 271. Picric acid. Pp. 281-2. Ammonium picrate, phenol.
- VEROLA, M. Decomposition of TNT under influence of heat. 1912. Chem. Absts., v. 6, p. 932. TNT.
- VOIGT, A. Grounding of machinery for powder manufacture. 1911. Chem. Absts., v. 5, p. 3341. Black powder.
- WALLACE, R. N. Phenol. (Pat.) 1918. Chem. Absts., v. 12, p. 1969. Phenol.
- WALLER, E. Phenol or carbolic acid: Qualitative and quantitative tests. 1881. Chem. News, v. 43, p. 150. Phenol.
- WALLER, C. E. Method of calculating comparative strength and efficiency of high explosives from their composition and apparent densities. Jnl. Ind. and Eng. Chem., 1918, v. 10, pp. 448-53. TNT.
- WEAVER, E. M. Notes on military explosives. 1917. Pp. 77-8. Picric acid, pp. 80-1. Ammonium picrate, pp. 81a-f. TNT, pp. 98-103. Black powder, p. 134. E. C. powder.
- WEDEKIND, R. Ammonium nitrate. (Pat.) 1908. Chem. Absts., v. 2, p. 2434.
- WEISS, J. M. Safety of TNT as an explosive. 1918. Jnl. Ind. and Eng. Chem., v. 10, p. 1028. TNT.
- WELLS, A. A. (See under Ellis, Carleton, Rabinowitz, Louis, and Wells, A. A.) Picric acid.
- WENGHÖFFER. Process for manufacturing picric acid. 1901. Jnl. Soc. Chem. Ind., v. 20, p. 570. Picric acid.
- WEST, F. O. The manufacture of picric acid from the medical standpoint. 1917. Jnl. Ind. and Eng. Chem., v. 9, pp. 303-5. Picric acid.
- WIARD. The grading of graphite, gunpowder, and malt. 1917. Chem. Absts., v. 11, p. 2264. Black powder.
- WICHARDT, O. Process for preparing picric acid in the cold. (Pat.) 1904. Jnl. Soc. Chem. Ind., v. 23, p. 1238. Picric acid.
- WILKINSON, T. S. Military explosives. 1916. Chem. Absts., v. 12, p. 68. Picric acid.
- WILL, W. Progress on the manufacture of explosives since the development of organic chemistry. 1904. Jnl. Soc. Chem. Ind., v. 23, p. 269. Picric acid.
- WÖHLER, L. Detonator for explosives. (Pat.) 1909. Chem. Absts., v. 3, p. 717. Picric acid.
- WOLFFENSTEIN, R. (See under Boeters and Wolffenstein, R.) Picric acid.
- WOODBURY. Varying the velocity of detonation of explosives containing ammonium nitrate. (Pat.) 1914. Chem. Absts., v. 8, p. 3860. Ammonium nitrate.

- WOODBURY, C. A. Process of varying velocity of detonation of explosives. (Pat.). 1914. Jnl. Soc. Chem. Ind., v. 3, p. 1116. Ammonium nitrate.
- WOODBURY, C. A. Explosive. (Pat.) 1915. Chem. Absts., v. 9, p. 717. Ammonium nitrate.
- WORDEN, EDW. C. Nitrocellulose industry. 1911. V. 2, p. 955. Sporting ballistite, pp. 955-6, 959-60. E. C. Blank-fire powder, p. 957. Black powder, (Lesmok.)
- WRIGHT, R. (See under McHutchinson and Wright.) TNT.
- YOUNG, CLINTON. Gaseous decomposition products of black powder with special reference to use of black powder in coal mines. 1910. Am. Inst. of Min. Engrs., Bul., v. 44, p. 637. Black powder.
- ZSCHOKKE, BRUNO. Handbuch der militärischen Sprengtechnik. 1911. P. 17. Black powder, pp. 38-9. Picric acid.

ADDITIONAL COPIES
OF THIS PUBLICATION MAY BE PROCURED FROM
THE SUPERINTENDENT OF DOCUMENTS
GOVERNMENT PRINTING OFFICE
WASHINGTON, D. C.
AT
25 CENTS PER COPY



